

Guillermo Gosset *Editor*

Melanins: Functions, biotechnological production, and applications



Springer

Melanins: Functions, Biotechnological Production, and Applications

Guillermo Gosset

Editor

Melanins: Functions, Biotechnological Production, and Applications



Springer

Editor

Guillermo Gosset
Instituto de Biotecnología/Universidad
Nacional Autónoma de México
Cuernavaca, Morelos, Mexico

ISBN 978-3-031-27798-6 ISBN 978-3-031-27799-3 (eBook)
<https://doi.org/10.1007/978-3-031-27799-3>

© The Editor(s) (if applicable) and The Author(s), under exclusive license to Springer Nature Switzerland AG 2023

This work is subject to copyright. All rights are solely and exclusively licensed by the Publisher, whether the whole or part of the material is concerned, specifically the rights of translation, reprinting, reuse of illustrations, recitation, broadcasting, reproduction on microfilms or in any other physical way, and transmission or information storage and retrieval, electronic adaptation, computer software, or by similar or dissimilar methodology now known or hereafter developed.

The use of general descriptive names, registered names, trademarks, service marks, etc. in this publication does not imply, even in the absence of a specific statement, that such names are exempt from the relevant protective laws and regulations and therefore free for general use.

The publisher, the authors, and the editors are safe to assume that the advice and information in this book are believed to be true and accurate at the date of publication. Neither the publisher nor the authors or the editors give a warranty, expressed or implied, with respect to the material contained herein or for any errors or omissions that may have been made. The publisher remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

This Springer imprint is published by the registered company Springer Nature Switzerland AG
The registered company address is: Gewerbestrasse 11, 6330 Cham, Switzerland

Preface

Melanin is the common name for a unique class of natural polymeric pigments found in most organisms, including bacteria, fungi, plants, and animals. These pigments are generated as a result of the enzyme-catalysed oxidation and subsequent random polymerization of diverse precursor molecules. The most common precursors include L-tyrosine, cysteinyl-dopa, homogentisate, dihydroxynaphthalene, and phenolic compounds, yielding the eumelanin, pheomelanin, pyomelanin, and the allomelanins. These polymers play very diverse roles related to the survival of organisms. Functions provided by these pigments include photoprotection, thermoregulation, visual signalling, mechanical strengthening, and antioxidation. In several organisms, the production of melanins also influences immunity and virulence.

These complex polymers display unique chemical and physical properties including broadband optical absorption, structural stability, metal chelation, redox activity, paramagnetism, and semiconductivity. As a result of these properties, melanins are considered valuable functional materials for multiple applications in industry. Recent advances in the development of biotechnological processes to produce these pigments at large scale are enabling the generation of novel melanin-based products. The melanins have physical and chemical characteristics that have been found useful in the optical, electronic, material, agriculture, cosmetic, pharmaceutical, and medical industries. These polymers are also considered eco-friendly and biocompatible materials that can be produced sustainably.

The objective of this book is to provide an up-to-date overview of the biological functions of melanins, their biotechnological production, and selected applications. This book is expected to become a source of reference for researchers and students interested in this field. The chapters were written by leading experts that include up-to-date information and in-depth analysis of the current issues and challenges in this field. This work offers a better understanding of the biological roles of melanins and insights into the current and future industrial applications.

The topics in this book comprise the evolution of melanin in vertebrates as well as the properties, biogenesis, and evolution of melanosomes. Melanins are also synthesized by several species of microorganisms. The metabolic pathways involved in

the synthesis of several types of polymeric pigments in microorganisms as well as their role in survival are reviewed. A chapter is devoted to reviewing the role of melanin in virulence and pathogenicity. This pigment aids the fungus during infection and persistence in the host.

The large-scale production and purification of melanins to provide this product for industrial applications is a formidable challenge. Two chapters in this book present and discuss the state-of-the-art technologies used for the generation of microbial melanin-production strains as well as the processes for the biotechnological synthesis and purification of these pigments. Melanin is a polymer that can interact with metals, a chapter reviews this capacity in the context of technological applications, including electrochemical energy storage and metal recovery. The melanins are materials having favourable characteristics for photonic applications, including UV blocking and broadband absorption. The current advances in the application of these pigments in optically active materials are presented and discussed.

Support from the Universidad Nacional Autónoma de México is gratefully acknowledged by the editor.

Cuernavaca, Mexico
December 9, 2022

Guillermo Gosset

Contents

Melanin Synthesis in Bacteria: Who, How and Why	1
María Julia Pettinari, María Elisa Pavan, and Nancy I. López	
The Role of Melanin in Fungal Disease	27
Rosanna P. Baker, Arturo Casadevall, Emma Camacho, Radames J. B. Cordero, Aryan Waghmode, Livia Liporagi-Lopes, Amy Liu, Ellie Rose Mattoon, Nathan Mudrak, and Daniel F. Q. Smith	
Melanosome Origins, Diversity and Functional Relevance Across Animals	45
Liliana D’Alba	
Biotechnological Production of Melanins with Recombinant Microorganisms	67
Luz María Martínez, Alejandro Miguel Cisneros-Martínez, Georgina Hernández-Chávez, Alfredo Martinez, and Guillermo Gosset	
Extraction, Purification, and Characterization of Microbial Melanin Pigments	91
Vishal A. Ghadge, Sanju Singh, Pankaj Kumar, Doniya Elze Mathew, Asmita Dhimmarr, Harshal Sahastrabudhe, Apexa Gajjar, Satish B. Nimse, and Pramod B. Shinde	
Exploiting Melanin-Metal Interactions for Emerging Technologies	111
Yasser Matos-Peralta, Zhaojing Gao, Afzal Ahmed Dar, and Clara Santato	
Fundamentals and Applications of Optically Active Melanin-Based Materials	127
Ming Xiao and Weiyao Li	

Melanin Synthesis in Bacteria: Who, How and Why



María Julia Pettinari, María Elisa Pavan, and Nancy I. López

1 Introduction

Melanins were described hundreds of years ago as the main component of the ink of the cuttlefish *Sepia* (Bizio 1825). These pigments that result from the oxidative polymerization of indolic or phenolic compounds have been found not only in animals but also in plants, fungi, and bacteria (Solano 2014; Toledo et al. 2017). In animals, melanins have been proposed not only to offer protection against UV radiation and free radicals but also to play a role in animal behavior and communication (Carletti et al. 2014). Fungi are known to produce many different types of melanin that have been shown to protect them against environmental factors and to have an important role in fungal pathogens (Belozerskaya et al. 2017). In plants, melanin production is mostly associated with the darkening of damaged tissue, and although it is normally present on the dark surface of many seeds, it remains poorly studied (Glagoleva et al. 2020). In the early twentieth century, Beijerinck described dark pigments derived from tyrosine metabolism produced by some bacteria (Beijerinck 1900, 1911), and since then, many different bacteria have been reported to produce melanins using a variety of metabolic pathways (Pavan et al. 2020). The fact that melanin synthesis is observed in organisms with such a broad phylogenetic distribution suggests that these pigments are relevant to different aspects of their physiology.

M. J. Pettinari (✉) · M. E. Pavan · N. I. López

Departamento de Química Biológica—IQUIBICEN, Facultad de Ciencias Exactas y Naturales,
Universidad de Buenos Aires, Buenos Aires, Argentina

e-mail: jul@qb.fcen.uba.ar; mepavan@qb.fcen.uba.ar; nan@qb.fcen.uba.ar

2 Melanin Biosynthesis Pathways in Bacteria

Melanins are heteropolymers of different types of quinones that rise from the oxidation of hydroxylated aromatic compounds. Most known melanins, including DOPA and homogentisate melanin, are related to tyrosine metabolism, and a few are derived from malonyl-CoA (Pavan et al. 2020) or other substrates.

2.1 Eumelanin (DOPA Melanin)

This kind of melanin is the best known and characterized, thus denominated eumelanin, and is synthesized by polyphenol oxidases with tyrosinase or laccase activities.

Tyrosinases (EC 1.14.18.1) are a type of copper-containing polyphenol oxidases that catalyze the orthohydroxylation of tyrosine to L-3,4-dihydroxyphenylalanine (L-DOPA) and its oxidation to dopaquinone. This compound suffers cyclization and oxidation and is finally converted into indole-5,6-quinone in another reaction catalyzed by the tyrosinase. The reactive indole-5,6-quinone, or its 2-carboxylated form (5,6-dihydroxyindole-2-carboxylic acid, DHICA), spontaneously oxidizes and polymerizes to form eumelanin or DOPA melanin. As bifunctional polyphenol oxidases, tyrosinases can catalyze both the monooxygenation of monophenols to o-diphenols (monophenolase /monophenol hydroxylase /cresolase activity) and the oxidation of o-diphenols to the corresponding o-quinone (catechol oxidase/catecholase/diphenolase activity) (Sanchez-Amat et al. 2010). Different tyrosinases can have different monophenol and diphenol substrate specificities (Shuster and Fishman 2009; Harir et al. 2018). Bacterial tyrosinases and their relevant applications have been the subject of several comprehensive reviews (Faccio et al. 2012; Zaidi et al. 2014).

Another type of polyphenol oxidases involved in melanin synthesis are laccases (EC 1.10.3.2), that lack monophenol hydroxylase activity, but oxidize a variety of diphenols (Reiss et al. 2011). Just like tyrosinases, laccases have copper ions bound to conserved histidine residues in the active site (Shuster and Fishman 2009). Laccases are frequent and well known in plants and fungi (Sharma et al. 2018) but have only recently been studied in depth in bacteria (Singh et al. 2011).

Bacterial tyrosinases related to melanin synthesis were initially described in *Streptomyces* species. In 1972 the tyrosinase of *S. glaucescens* was purified and its molecular properties were compared with those of tyrosinases from eukaryotic organisms (Lerch and Ettinger 1972). *Streptomyces* tyrosinases are encoded by a bicistronic operon that includes genes coding for the tyrosinase (MelC2) and a chaperone (MelC1) involved in the incorporation of copper in the active site of the tyrosinase and its secretion (Leu et al. 1992).

Tyrosinases were also related to melanin synthesis in *Bacillus* species, such as *Bacillus megaterium* (Shuster and Fishman 2009) and *Bacillus thuringiensis* (Liu

et al. 2004; Ruan et al. 2004). Many proteobacteria also synthesize DOPA melanin through the action of tyrosinases such as MepA in *Sinorhizobium meliloti* (Mercado-Blanco et al. 1993), and Mel in *Stenotrophomonas maltophilia* (Wang et al. 2000).

Other bacteria produce DOPA melanin through the action of a laccase. The laccase of *Azospirillum lipoferum* was purified and characterized as a multimeric enzyme consisting of one catalytic chain and one or two heavy chains whose role is to be elucidated (Diamantidis et al. 2000).

In some melanogenic bacteria, tyrosinases and laccases activities coexist. *Marinomonas mediterranea* MMB-1 possesses a cytoplasmic tyrosinase (PpoB1) (López-Serrano et al. 2004) and also a membrane-bound polyphenol oxidase (PpoA) with tyrosinase and laccase activities, but only PpoB1 is involved in melanin synthesis in this bacterium (Solano et al. 2000). A tyrosinase and a laccase have been purified and biochemically characterized from cellular extracts of *Pseudomonas putida* F6 (McMahon et al. 2007), a strain that produces reddish-brown melanin in liquid cultures supplemented with tyrosine (Nikodinovic-Runic et al. 2009), yet the exact pathway for melanin synthesis in this strain remains unknown. A gene encoding for a tyrosinase (VIBNI_B1404), with the common central domain of tyrosinases, is present in the genome of *Vibrio nigripulchritudo* SFn1, a strain that forms brown pigmented colonies. This tyrosinase, together with a laccase (VIBNI_B0280), would be involved in melanin production in this emerging pathogen of farmed shrimp, as the deletion of each gene decreased colony pigmentation (Goudenège et al. 2013).

2.2 *Pyomelanin (Homogentisate Melanin)*

Early studies of bacterial melanin assumed that their synthesis was always related to tyrosinases leading to DOPA-melanin, but due to results observed with several tyrosine-containing media Arai and Mikami (1972) suggested that diffusible dark brown melanins produced by *Streptomyces* could have a different chemical nature and that other enzymes distinct from the tyrosinase could be involved in pigment formation. Two decades later it was found that a 4-hydroxyphenylpyruvate dioxygenase directed the production of a pigment derived from homogentisate in *S. avermitilis* (Denoya et al. 1994). A pigment of this kind had already been described in *Pseudomonas aeruginosa* and denominated “pyomelanin” (Yabuuchi and Ohyama 1972). This pigment is also found in the urine of human patients with alkaptonuria. This hereditary disorder results from the absence of the homogentisate 1,2 dioxygenase, the enzyme responsible for the breakdown of homogentisate in the tyrosine degradation pathway (Fernández-Cañón et al. 1996).

In the so called homogentisate pathway, tyrosine is catabolized in five successive steps. First, tyrosine is converted into 4-hydroxyphenylpyruvate by aromatic amino acid aminotransferases. The 4-hydroxyphenylpyruvate dioxygenase (EC 1.13.11.27) acts on this compound to generate homogentisate in what can be considered one of the most complex reactions catalyzed by a single enzyme, as it involves dioxygen

addition, decarboxylation and rearrangement/migration of the side chain on the aromatic ring (He and Moran 2009). If the homogentisate 1,2-dioxygenase enzyme is missing the final degradation of the homogentisate to fumarate and acetoacetate is precluded. The accumulation and spontaneous autooxidation and polymerization of homogentisate lead to the synthesis of the pigment.

The formation of this kind of melanin has been also related to the homogentisate 1,2-dioxygenase in bacteria. Some *Aeromonas* produce dark diffusible pyomelanins, and in all of them *hmgA*, the gene coding for this enzyme, is mutated (Pavan et al. 2015). For example, in *A. salmonicida* subsp. *salmonicida* A449 *hmgA* is a pseudogene due to a frameshift caused by a single base pair deletion while in *A. salmonicida* subsp. *pectinolytica* 34mel^T *hmgA* is interrupted by a transposase associated with IS21 family insertion sequences. The same gene is discontinued by a transposase belonging to the IS66 family in *A. media* WS and by a nonsense codon in the strain RM^T (Pavan et al. 2015; Wang et al. 2015). In contrast, *Vibrio cholera* HTX-3, *Shewanella colwelliana* D, and a strain of *Hyphomonas* accumulate homogentisate due to increased amounts of the 4-hydroxyphenylpyruvate dioxygenase and not to a mutation in the homogentisate 1,2-dioxygenase gene (Kotob et al. 1995). Additionally, homogentisate accumulation and melanin formation was observed in highly clonal strains of *V. cholerae* that display an identical 15-bp deletion in *hmgA* (Wang et al. 2011), and a single amino acid substitution (G378R) in the homogentisate 1,2-dioxygenase is responsible for pigmentation in *Burkholderia cepacia* isolates (Gonyar et al. 2015). Transposon insertions in *hmgA* (Rodríguez-Rojas et al. 2009) or large chromosomal deletions that include *hmgA* (Hocquet et al. 2016) result in the accumulation of homogentisate and production of pyomelanin in clinical isolates of *P. aeruginosa*. In the photosynthetic betaproteobacterium *Rubrivivax benzoatilyticus* JA2^T, which displays multiple anaerobic and aerobic L-phenylalanine catabolic pathways, the absence of the homogentisate dioxygenase leads to homogentisate accumulation in aerobic conditions and thereby to pyomelanin synthesis (Mekala et al. 2019).

2.3 Polyketide Derived Melanin (PK Melanin)

A unique way of melanin synthesis in bacteria is through polyketide synthases, thought to be exclusive to plants until the first bacterial one was found in *Streptomyces griseus* in 1999 (Funa et al. 1999). By sequential decarboxylative condensation of five molecules of malonyl-coenzyme A, the structurally simple homodimeric type III polyketide synthase RppA catalyzes the synthesis of a pentaketide that is then cyclized to 1,3,6,8-tetrahydroxynaphthalene (THN). A member of the cytochrome P450 family whose gene lies in an operon with *rppA* catalyzes the oxidative dimerization of two THN subunits to yield 1,4,6,7,9,12-hexahydroxyperylene-3,10-quinone (hexahydroxyperylenequinone, HPQ) (Funa et al. 2005). The air oxidation and autopolymerization of this unstable precursor lead to the formation of brownish melanin (Funa et al. 2005). Genome analysis of *Streptomyces avermitilis* has

described several polyketide synthase clusters, including a type II polyketide synthase proposed to catalyze the synthesis of polyketide-derived melanin from malonylCoA (Omura et al. 2001). The bacterial melanin biosynthetic pathway found in *Streptomyces* is different from that of some fungi in which THN, synthesized by the evolutionarily different large and complex type I polyketide synthases, is an intermediate in the synthesis of 1,8-dihydroxynaphthalene (DHN) that then polymerizes to form melanin.

2.4 Allomelanins

Finally, the oxidation of aromatic compounds such as phenol, catechol, protocatechualdehyde, and 1,8-dihydroxynaphthalene (1,8-DHN), can lead to the formation of pigments collectively known as allomelanins, commonly found in fungi and plants (Martínez et al. 2019), and also described in bacteria.

Some bacteria can synthesize these aromatic compounds as end products or as intermediary metabolites during the degradation of aromatic substrates, so their accumulation could provide the substrates for the formation of melanins through oxidation and polymerization.

Black melanin derived from catechol was described in *Azotobacter chroococcum* (Shivprasad and Page 1989). Although catechol is formed in low or high aeration conditions, melanization only occurs in the presence of oxygen. The formation of melanin during the encystment stage of this microorganism is related to a membrane-bound laccase (Herter et al. 2011).

Serratia marcescens can produce brown melanin by spontaneous oxidation and polymerization of homoprotocatechuate (3,4-dihydroxyphenylacetate), an isomer of homogentisate (2,5-dihydroxyphenylacetate) (Trias et al. 1989). Homoprotocatechuate is a metabolite produced during tyrosine degradation in a pathway present in many bacteria such as *Paraburkholderia xenovorans* that leads to the formation of Krebs cycle intermediates (Méndez et al. 2011). The low activity of the enzyme that catalyzes homoprotocatechuate degradation, the 3,4-dihydroxyphenylacetate 2,3-dioxygenase (EC 1.13.11.15) leads to the accumulation of this metabolite in *S. marcescens* (Trias et al. 1989). The metabolic process that leads to homoprotocatechuate accumulation is comparable to the one that leads to the formation of homogentisate melanin covered in Sect. 2.2, found in a great number of bacteria (Table 1). Although (i) the homoprotocatechuate pathway is present in many bacteria (Méndez et al. 2011), and (ii) mutations in the gene that codes for the 3,4-dihydroxyphenylacetate 2,3-dioxygenase would be expected to lead to homoprotocatechuate melanin synthesis in other bacteria, this kind of melanin has only been described in *S. marcescens*.

Table 1 Bacteria producing different kinds of melanin

Phylum	Class	Order	Family	Species	Melanin type	References		
Proteobacteria	Alpha	Rhodospirillales	Azospirillaceae	<i>Azospirillum brasilense</i> <i>Azospirillum lipoferum</i>	HMG? DOPA	Gowri and Srivastava 1996 Givaudan et al. 1993		
		Caulobacteriales	Caulobacteraceae	<i>Brevundimonas vitisensis</i> <i>Brevundimonas</i> sp.	HMG DOPA	Jiang et al. 2021 Surwase et al. 2013		
		Hyphomonadales	Hyphomonadaceae	<i>Hyphomonas</i> sp.	HMG	Kolob et al. 1995		
			Rhizobiaceae	<i>Rhizobium elii</i>	DOPA	Piñero et al. 2007		
				<i>Rhizobium leguminosarum</i>	DOPA	Cubo et al. 1988		
				<i>Rhizobium phaseoli</i>	DOPA	Borthakur et al. 1987		
				<i>Rhizobium radiobacter</i>	DOPA	Wu et al. 2022		
				<i>Sinorhizobium fredii</i>	DOPA	Cubo et al. 1988		
				<i>Sinorhizobium meliloti</i>	DOPA	Cubo et al. 1988		
		Beta	Alcaligenaceae	<i>Alcaligenes faecalis</i> <i>Bordetella parapertussis</i>	HMG HMG	Singh et al. 2018 Hiramatsu et al. 2021		
			Burkholderiales	Burkholderiaceae	<i>Burkholderia cenocepacia</i> <i>Burkholderia cepacia</i> <i>Ralstonia solanacearum</i> <i>Ralstonia pickettii</i>	HMG HMG HMG HMG	Keith et al. 2007 Gonyar et al. 2015 Ahmad et al. 2016 Seo and Choi 2020	
	Comamonadaceae				<i>Rubrivivax benzoatilyticus</i>	HMG	Mekala et al. 2019	
	Aeromonadales				Aeromonadaceae	<i>Aeromonas media</i> <i>Aeromonas salmonicida</i> subsp. <i>pectinolytica</i> <i>Aeromonas salmonicida</i> subsp. <i>salmonicida</i>	HMG HMG HMG	Wang et al. 2015 Pavan et al. 2015 Pavan et al. 2015
						Alteromonadales	Pseudoalteromonadaceae	<i>Pseudoalteromonas aliena</i> <i>Pseudoalteromonas distincta</i> <i>Pseudoalteromonas lipolytica</i>
			Shewanellaceae	Shewanellaceae				<i>Shewanella algae</i> <i>Shewanella colwelliana</i> <i>Shewanella oneidensis</i>

Enterobacteriales	Enterobacteriaceae	<i>Klebsiella pneumoniae</i> <i>Klebsiella</i> sp. <i>Enterobacter</i> sp.	HMG	Singh et al. 2018
			DOPA	Sajjan et al. 2010
			HMG	Singh et al. 2018
			DOPA	Agodi et al. 1996
	Morganeliaceae	<i>Providencia mirabilis</i>	ND	Laxmi et al. 2016
		<i>Providencia rettgeri</i>	ND	Vijayan et al. 2017
		<i>Providencia sreebia</i>	ND	Vijayan et al. 2017
	Yersiniaceae	<i>Providencia vermicola</i>	ND	Vijayan et al. 2017
		<i>Serratia marcescens</i>	HPC	Trias et al. 1989
	Legionellales	<i>Legionella pneumophila</i>	HMG	Flydal et al. 2012
Pseudomonadales	Oceanospirillales	<i>Marinomonas mediterranea</i>	DOPA	Solano et al. 2000
	Moraxellaceae	<i>Acinetobacter baumannii</i>	HMG	Coelho-Souza et al. 2014
		<i>Pseudomonas aeruginosa</i>	HMG	Yabuuchi and Ohyama 1972
		<i>Pseudomonas syringae</i> pv. <i>pari</i>	DOPA	Samson et al. 1998
	Pseudomonadaceae	<i>Pseudomonas guinea</i>	DOPA	Tarangini and Mishra 2013
		<i>Pseudomonas korensis</i>	DOPA	Eskandari and Elemadifar 2021a
		<i>Pseudomonas otitidis</i>	DOPA	Seelam et al. 2021
		<i>Pseudomonas putida</i>	DOPA	McMahon et al. 2007
		<i>Pseudomonas stutzeri</i>	HMG; DOPA	Kurian and Bhat 2018a; Ganesh Kumar et al. 2013
		<i>Azotobacter chroococcum</i>	DOPA; CAT	Banerjee et al. 2014; Shivprasad and Page 1989
Xanthomonadales	Cellvibrionaceae	<i>Azotobacter salinestris</i>	CAT	Page and Shivprasad 1991
		<i>Saccharophagus degradans</i>	DOPA	Kelley et al. 1990
		<i>Stenotrophomonas maltophilia</i>	DOPA	Wang et al. 2000
	Xanthomonadaceae	<i>Xanthomonas campestris</i> pv. <i>phaseoli</i>	HMG	Goodwin and Sopher 1994
		<i>Lysobacter oligotrophicus</i>	DOPA	Kimura et al. 2015
		<i>Vibrio alginolyticus</i>	DOPA + HMG	Kurian and Bhat 2018b
	Vibrionales	<i>Vibrio anguillarum</i>	ND	Vijayan et al. 2017
		<i>Vibrio cholerae</i>	HMG	Kobayashi et al. 1995
		<i>Vibrio parvulus</i>	ND	Vijayan et al. 2017
		<i>Vibrio nigrificans</i>	DOPA	Goudenège et al. 2013
		<i>Vibrio vulnificans</i>	ND	Vijayan et al. 2017
Caryophanales	Bacillaceae	<i>Bacillus altitudinis</i>	ND	Vijayan et al. 2017
		<i>Bacillus cereus</i>	ND	Zhang et al. 2007

(continued)

Table 1 (continued)

Actinobacteria	Actinobacteria			<i>Bacillus haynesii</i>	HMG	Marin-Sanhueza et al. 2022
				<i>Bacillus licheniformis</i>	DOPA	Gamal Shalaby et al. 2019
				<i>Bacillus megaterium</i>	DOPA	Shuster and Fishman 2009
				<i>Bacillus safensis</i>	DOPA	Tarangiri and Mishra 2014
				<i>Bacillus subtilis</i>	DOPA	Chadge et al. 2020
				<i>Bacillus thuringiensis</i>	DOPA; HMG	Ruan et al. 2004; Cao et al. 2018
				<i>Bacillus weihenstephanensis</i>	DOPA	Drewnowska et al. 2015
				<i>Cyrobacillus firmus</i>	ND	Vijayan et al. 2017
			Staphylococcaceae	<i>Salinicoccus roseus</i>	ND	Vijayan et al. 2017
				<i>Mammaliococcus scuri</i>	ND	Vijayan et al. 2017
				<i>Planococcus maritimus</i>	ND	Vijayan et al. 2017
		Pseudonocardiaceae	Pseudonocardiaceae	<i>Actinoalbidichus</i> sp.	DOPA	Manivasagan et al. 2013
				<i>Dietzia schimae</i>	DOPA	Eskandari and Etemadifar 2021b
		Frankiaceae	Frankiaceae	<i>Frankia</i> sp.	DOPA	Yuan et al. 2007
		Micrococcales	Micrococccaceae	<i>Glutamicibacter creatinolyticus</i>	ND	Vijayan et al. 2017
		Geodermatophilales	Geodermatophilaceae	<i>Modestobacter versicolor</i>	ND	Reddy et al. 2007
		Streptosporangiales	Nocardiolesaceae	<i>Nocardopsis alba</i>	DOPA	Kiran et al. 2014
				<i>Nocardopsis dassonvillei</i>	ND	Kamaruddeen et al. 2019
Bacteroidetes	Flavobacteria			<i>Streptomyces avermitilis</i>	HMG; HMG+ DOPA + PK	Denoya et al. 1994; Omura et al. 2001
				<i>Streptomyces castaneoglobisporus</i>	DOPA	Ikeda et al. 1996
				<i>Streptomyces cyaneofuscatus</i>	DOPA	Al Khalib et al. 2018
				<i>Streptomyces glaucescens</i>	DOPA	El-Naggar and El-Ewasy 2017
				<i>Streptomyces griseus</i>	PK	Funa et al. 1999
		Streptomycetales	Streptomycetaceae	<i>Streptomyces kathirae</i>	DOPA	Guo et al. 2014
				<i>Streptomyces lavendulae</i>	DOPA	Mencher and Heim 1962
				<i>Streptomyces michiganensis</i>	DOPA	Held and Kutzner 1990
				<i>Streptomyces parvus</i>	DOPA	Bayram et al. 2020
		Flavobacteriales	Flavobacteriaceae	<i>Streptomyces parvus</i>	DOPA	Bayram et al. 2020
				<i>Flavobacterium kingsejongi</i>	HMG	Lee et al. 2022

DOPA : Eumelanin, DOPA derived melanin; HMG: pyomelanin, homogentisate derived melanin; PK: polyketide derived melanin; CAT: allomelanin, catechol derived melanin; HPC: allomelanin, homoprotocatechuate derived melanin; ND: not determined. Species in which more than one kind of melanin have been described are highlighted in gray. Semicolons are used for cases in which different kinds of melanin have been described for a given species in separate studies.

3 Phylogenetic Distribution of Melanin Synthesis in Bacteria

3.1 *Actinobacteria*

The ability to synthesize melanin is a common property among *Streptomyces* (Table 1) and is used for the classification and identification of these filamentous soil-dwelling microorganisms (Arai and Mikami 1972). Although these bacteria mostly synthesize DOPA melanin through the action of tyrosinases (Manivasagan et al. 2013), several species are known to produce other kinds of melanin. The production of homogentisate melanin in bacteria was first related to 4-hydroxyphenylpyruvate dioxygenase in *S. avermitilis* (Denoya et al. 1994). Synthesis of melanins through type III polyketide synthases was also described in this genus and studied extensively in *S. griseus* (Funa et al. 2005). Synthesis of melanin in this microorganism shares regulatory control with spore formation and provides *S. griseus* enhanced protection from UV irradiation suggesting HPQ melanin would play a role in protection against environmental stress (Funa et al. 2005; Takano et al. 2007). Some bacteria from this genus, such as *S. avermitilis*, can synthesize three different kinds of melanin, two of them (DOPA melanin and homogentisate melanin) related to tyrosine, and a third (polyketide-derived melanin) from malonyl CoA. Analysis of its genome revealed that it contains two clusters coding for tyrosinases, a type II polyketide synthase (Omura et al. 2001), and genes leading to homogentisate synthesis (Denoya et al. 1994).

3.2 *Firmicutes*

Several species of *Bacillus* also synthesize melanin (Table 1). Some like *B. thuringiensis* and *B. megaterium* produce DOPA melanin through the action of tyrosinases (Shuster and Fishman 2009), while a recent study has described a thermophilic *B. haynesii* that produces homogentisate melanin (pyomelanin) when submitted to stress (Marín-Sanhueza et al. 2022). *B. thuringiensis* strains produce melanin when cultures are exposed at 42 °C (Liu et al. 2004; Ruan et al. 2004), and *B. cereus* isolates were also observed to produce melanin (Zhang et al. 2007). The melanin produced by these bacteria protects the spores and insecticidal crystals from UV exposure (Ruan et al. 2004; Zhang et al. 2007). A large screening study also identified psychrophilic melanin-producing *B. weihenstephanensis* (Drewnowska et al. 2015). However, this study that screened nearly a thousand isolates of the *B. cereus* group from different origins found that only six of them (all strains of *B. weihenstephanensis*) produced melanin, suggesting that the ability to produce this pigment is not widespread among this group (Drewnowska et al. 2015).

3.3 *Proteobacteria*

Many proteobacteria synthesize DOPA melanin (Table 1). Its synthesis has been studied in several of them and has been related to tyrosinase coding genes such as *mepA* in *S. meliloti* (Mercado-Blanco et al. 1993), and *mel* in *S. maltophilia* (Wang et al. 2000). Some proteobacteria only produce melanin in certain conditions, so it is possible that the capability to produce this pigment has been overlooked in many of them. For example, the plant pathogen *Ralstonia solanacearum*, that in standard growth conditions does not produce melanin, synthesizes DOPA melanin through the action of a tyrosinase when grown in the presence of tyrosine if deprived of some other nutrients (Hernández-Romero et al. 2005). DOPA melanin production has also been described in several species of *Pseudomonas*, including animal and plant pathogens, and environmental strains (Table 1).

In contrast to DOPA melanin which involves special enzymes, the synthesis of melanin derived from the oxidation and polymerization of homogentisate is due to deficiencies in the degradation of homogentisate. In species belonging to the genus *Pseudomonas*, the production of homogentisate melanin was detected 50 years ago in clinical isolates of *P. aeruginosa*, giving rise to the name pyomelanin (Yabuuchi and Ohyama 1972).

As discussed in the previous section, the synthesis of homogentisate-derived melanin, which has been extensively studied in *Aeromonas* (Pavan et al. 2015), is common among many groups of proteobacteria, including *Shewanella* (Kotob et al. 1995; Turick et al. 2009), *Burkholderia* (Keith et al. 2007), *Ralstonia* (Hernández-Romero et al. 2005; Seo and Choi 2020), *Brevundimonas* (Jiang et al. 2021), *Xanthomonas* (Goodwin and Sopher 1994), *Klebsiella*, *Alcaligenes*, and *Enterobacter* (Singh et al. 2018) among others (Table 1).

Homogentisate melanin was also described in *Vibrio cholerae* (Kotob et al. 1995), although other species of this genus like *V. nigrapulchrutudo* have been proposed to synthesize DOPA melanin based on the presence of a tyrosinase and a laccase (Goudenège et al. 2013). In addition, the simultaneous synthesis of both DOPA melanin and homogentisate-derived melanin has been reported in *V. alginolyticus* (Kurian and Bhat 2018a) and in *P. stutzeri* strains (Kurian and Bhat 2018b; Ganesh Kumar et al. 2013).

Although DOPA melanins and homogentisate-derived melanins are the most common types of melanins produced by proteobacteria, some cases of the production of melanins derived from other substrates have been described in this taxon. *A. chroococcum* produces black melanin derived from catechol proposed to fulfill a role in aeroadaptation by minimizing oxidative stress, allowing this soil-dwelling bacterium to fix nitrogen in an aerobic environment (Shivprasad and Page 1989), and *S. marcescens* produces a pigment derived from homoprotocatechuate (Trias et al. 1989), the only bacterium in which this kind of melanin has been described.

3.4 Other Bacterial Phyla and Archaea

Recent studies have characterized melanin produced by bacteria belonging to other phyla. For example, *Flavobacterium kingsejongi* was found to produce high levels of homogentisate-derived melanin (Lee et al. 2022).

An *in silico* search predicted that laccases are widespread in bacteria as putative laccases were identified in members of *Aquificales*, high G+C Gram-positive bacteria, and α -, γ - and ϵ -*Proteobacteria*, but their relationship to melanin synthesis in many of these microorganisms remains nearly unknown (Alexandre and Zhulin 2000).

Although melanin synthesis has never been observed in archaea up to our knowledge, it is noteworthy that applying *in silico* data mining putative laccases were identified in *Haloarcula marismortui*, *Halorubrum lacusprofundi*, and *Natronomonas pharaonis* (phylum *Euryarchaeota*), *Pyrobaculum aerophilum* (phylum *Crenarchaeota*), and *Nitrosopumilus maritimus* (phylum *Thaumarchaeota*) (Sharma and Kuhad 2009). Moreover, a psychrophilic tyrosinase from the marine *Candidatus Nitrosopumilus koreensis* was expressed in *Escherichia coli* and found to exhibit a high monophenolase/diphenolase activity ratio (Kim et al. 2016).

Taking into account the different metabolic pathways related to melanin production, there is no apparent association of melanin synthesis mechanisms with any particular phylogenetic groups of prokaryotes (Table 1). It can be stated that the production of this pigment appears in different groups of bacteria, both gram-positive and gram-negative. Likewise, the capability to synthesize melanin does not include all the members of a hierarchical phylogenetic group, but rather seems to have appeared sporadically.

4 Control of Melanin Synthesis in Bacteria

Despite the diverse melanin synthesizing pathways, in most bacteria melanin formation is stimulated in the presence of tyrosine and Cu. In the case of DOPA melanins, this effect can be obviously attributed to the fact that tyrosinases contain this metal in their structure. This explanation would not apply to cases in which melanin synthesis is not related to tyrosinases or other Cu-containing enzymes, so the mechanism through which Cu and other metals enhance melanin in these bacteria remains unknown (Pavan et al. 2020).

As discussed in previous sections, many bacteria synthesize melanin in specific growth conditions, or a certain growth phase, indicating that pigment formation is regulated, even in bacteria that produce the pigment through an apparently non-dedicated pathway (Pavan et al. 2020).

Pigmentation in rhizobacteria depends on several nutritional factors and is related to nitrogen fixation. *Rhizobium leguminosarum* bv. *phaseoli*, which carries melanin-related genes in the symbiosis plasmid, produces melanin in a rich medium but not in

a minimal medium even when both tyrosine and Cu are added (Borthakur et al. 1987). Transcription of the tyrosinase coding gene in this microorganism is activated by the regulator of nitrogen fixation, especially at low oxygen availability (Hawkins and Johnston 1988). Melanin formation has been linked to several kinds of stress or to the formation of resistance structures in different bacteria. *M. mediterranea* (Lucas-Elfo et al. 2002) and *R. solanacearum* (Ahmad et al. 2016) synthesize melanin when they reach the stationary phase while in *Azospirillum* (Gowri and Srivastava 1996) and *Azotobacter* (Herter et al. 2011) melanin production is related to cyst formation. Other bacteria such as *B. thuringiensis* (Ruan et al. 2004) and *Pseudoalteromonas* (Zeng et al. 2017a) produce melanin at high temperatures. Both high temperatures and hyperosmotic stress increased pigment formation in *V. cholerae*, especially in nutrient-poor growth media (Coyne and Al-Harthi 1992). Melanin synthesis is also related to biofilm formation, as seen in *Pseudoalteromonas* (Zeng et al. 2017a) and in *Vibrio anguillarum*. In this last microorganism, both biofilm formation and pigment production are controlled by a Lux-R-like transcriptional regulator (Croxatto et al. 2002). Studies of melanin synthesis in *R. solanacearum* reveal that it is controlled by transcriptional regulators OxyR, RpoS, and HrpG, involved in the regulation of stress response and pathogenicity (Ahmad et al. 2016).

In several *Streptomyces* species, melanin formation is under the control of the transcriptional regulator AdpA, which controls morphological development in response to A factor levels. This regulator activates tyrosinase (Zhu et al. 2005) and also regulates the synthesis of the type III polyketide synthase RppA, responsible for polyketide-derived melanin formation, along with many genes required for both morphological development and secondary metabolism (Takano et al. 2007).

In contrast to the melanins synthesized by special dedicated biosynthetic pathways, melanin formation from degradation intermediates such as homogentisate is due to the accumulation of these compounds caused by alterations in catabolic pathways. In the homogentisate pathway, phenylalanine or tyrosine are degraded to 4-hydroxyphenylpyruvate that is converted to homogentisate by Hpd. In the complete pathway, homogentisate is further degraded by HmgA to acetoacetate and fumarate. The genes that code for the enzymes in this pathway are controlled by transcriptional regulators in response to the presence of phenylalanine or tyrosine (Herrera et al. 2009; Palmer et al. 2010).

Accumulation of homogentisate has been shown to be due to overproduction, e.g. due to an increase in the expression of Hpd that converts 4-hydroxyphenylpyruvate to homogentisate (Kotob et al. 1995), or to lack of degradation, linked to the absence (Pavan et al. 2015) or decreased activity (Sanchez-Amat et al. 1998) of HmgA, the enzyme that leads to homogentisate degradation. Apart from the enzymes involved in the synthesis and degradation of homogentisate, several transcriptional regulators and transport proteins can affect melanin formation in *P. aeruginosa*, *A. media*, and *R. solanacearum* (Hunter and Newman 2010; Wang et al. 2015; Ahmad et al. 2016). Additionally, the presence of glycerol was observed to inhibit melanin synthesis in *A. salmonicida* subsp.

pectinolytica, and attributed to a combination of metabolic and regulatory effects including a decrease in *hpd* transcription (Pavan et al. 2019).

Many factors, including nutrient availability, different kinds of stress, formation of resistance structures, and interaction with other organisms have been observed to affect melanin synthesis in bacteria. Pigment formation is controlled by transcriptional regulators both in bacteria that synthesize melanin through the action of specific enzymes or in those in which melanin synthesis is due to imbalances in aromatic amino acid degradation or other pathways. The growing evidence that indicates that melanin synthesis is subject to different levels of regulation in all these bacteria suggests that melanin production is highly relevant to their physiology.

5 Physiological Role of Bacterial Melanins

Melanins may have a wide variety of functions that confer adaptive advantages to enhance survival under many stress conditions. The role of melanin in bacterial fitness was verified in different lifestyles and ecological niches encompassing both free-living cells, biofilms, or associations with other microorganisms, plants, or animals, including both pathogenic and non-pathogenic interactions (Fig. 1).

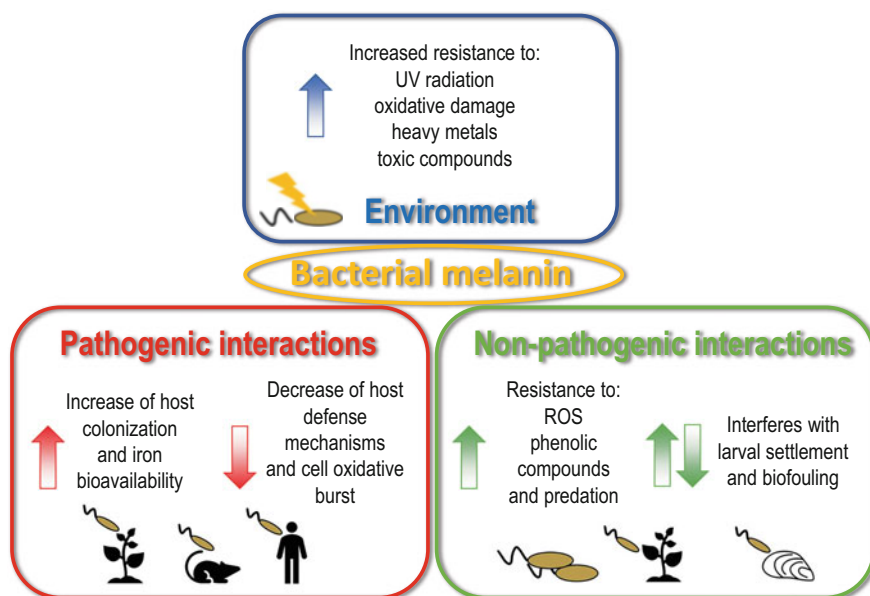


Fig. 1 The physiological role of melanins in bacteria. Melanin production increases bacterial fitness and provides resistance against several environmental stress factors. Melanin affects interactions among bacteria and both pathogenic and non-pathogenic interactions with animals and plants

5.1 Contribution of Melanin to Bacterial Fitness in Different Environments

Melanin production can enhance the capability of bacteria to respond to changing environmental conditions, increasing their survival in many environments (Fig. 1). *Shewanella* can use melanin as a terminal electron acceptor for anaerobic respiration and also as an electron shuttle during the respiration of Fe(III) minerals at low oxygen concentration helping this microorganism to live in anoxic or highly oxygenated environments (Turick et al. 2002, 2009).

Many melanin-producing bacteria have been discovered in extreme environments such as deserts and places with extreme hot or cold temperatures. *Streptomyces cyaneofuscatus* was isolated from the Sahara Desert (Harir et al. 2018), and *B. haynesii* from a hot spring in Chile showed melanin production under salinity stress (Marín-Sanhueza et al. 2022). The psychrotolerant melanin producer *B. weihenstephanensis* was isolated from cold environments in Poland (Drewnowska et al. 2015), and *Lysobacter oligotrophicus*, that was isolated in Antarctica, increased melanin production after UV exposure (Kimura et al. 2015). Nuclear waste, heavy metals, or oil spills can also generate extremely harsh environments where microorganisms have to cope with a variety of stress conditions. In *A. salmonicida* subsp. *pectinolytica*, a bacterium isolated from a heavily polluted river (Pavan et al. 2000), melanin production has been proposed to help this microorganism cope with the high concentrations of heavy metals, hydrocarbons, and other pollutants found in this environment (Pavan et al. 2015). Melanin-producing bacteria could thus be used for bioremediation applications as proposed for *A. chroococcum* which secretes melanin with high metal chelating activity (Rizvi et al. 2019).

In addition, one of the traditional roles assigned to melanin is the protection of cells from UV radiation (Fig. 1). Pigmented mutants of *Bacillus anthracis* (Han et al. 2015), and melanized spores of *S. griseus* are more resistant to UV irradiation than colorless mutants (Funa et al. 2005). Melanin has also been related to protection against oxidative stress, as melanogenic *P. aeruginosa* strains show higher tolerance to photodynamically induced oxidative stress (Orlandi et al. 2015).

5.2 Melanin in Pathogenic Interactions with Animals and Plants

Melanin production has been extensively associated with increased virulence in several bacterial pathogens (Nosanchuk and Casadevall 2003; Plonka and Grabacka 2006) (Fig. 1). This increase was attributed both to the reduction of the susceptibility of the pathogen to host defense mechanisms and to the alteration of the host immune response to infection (Nosanchuk and Casadevall 2006). Melanin production in

V. cholerae increases cholera toxin and pilus expression and enhances host colonization (Valeru et al. 2009).

In some melanin-producing epidemic strains of *Burkholderia cenocepacia* the pigment can diminish host cell oxidative burst due to its free radical scavenging potential, protecting this pathogen from oxidative stress (Keith et al. 2007). This was also observed for the plant pathogen *R. solanacearum*, in which protection against oxidative stress could help the bacteria cope with plant defense mechanisms (Ahmad et al. 2016) (Fig. 1). The ability of melanin to increase iron bioavailability through the reduction of ferric to ferrous form allows growth of *Legionella pneumophila* under iron-limited conditions such as those encountered in mammalian hosts and natural environments (Zheng et al. 2013). Melanin-producing *P. aeruginosa* emerge spontaneously during chronic infections in humans due to deletions in a genomic region containing *hmgA*. This generates mixed populations of pigmented and non-pigmented bacteria in an evolutionary process driven by continuous selective pressure due to intraspecific competition (Hocquet et al. 2016).

In the melanin producer *Bordetella parapertussis*, studies performed using a melanin-deficient mutant showed that melanin protects the bacteria from intracellular killing in macrophages and that the melanogenic strain was able to persist in the respiratory tract of mice more than the mutant strain (Hiramatsu et al. 2021). In line with this, it was observed that melanin from *Klebsiella pneumoniae* acts as a virulence factor suppressing the most important pro-inflammatory cytokines to counteract immune responses in mice (Saud and Alaubydi 2019).

Melanogenic bacteria having proteolytic, chitinolytic, and lipolytic activities were associated with tail fan necrosis in lobsters. It was proposed that the melanization of necrotized tail fans by lobsters was a sign of an effective immune response to eliminate pathogens (Perdomo-Morales et al. 2007). However, melanin-producing bacteria were isolated from the tail fans of the sick lobsters, suggesting that pigment formation in the characteristic melanized tissues associated with this disease could also be of bacterial origin (Zha et al. 2018). Melanin-producing bacteria can tolerate the presence of melanin from both bacterial or lobster origin. This fact may increase tail fan necrosis by protecting bacteria from lobster defenses, probably also enabling bacterial access to haemolymph and expanding infection (Zha et al. 2018). Melanosis is also recognized as one of the symptoms of fish diseases associated with some *A. salmonicida* melanin-producing strains (Janda and Abbott 2010).

5.3 Melanin in Non-pathogenic Interactions

Melanin is related to several interkingdom interactions involving non-pathogenic bacteria (Fig. 1). Tyrosinase activity, and consequently, melanin production is necessary during the first stages of nodulation during symbiosis of *Rhizobium etli*, a stage in which bacteria face reactive oxygen species (ROS) and phenolic compounds derived from plant defenses (Piñero et al. 2007). The melanin produced under metal exposure by the nitrogen-fixing *A. chroococcum* possesses a high metal

chelating activity, which makes this bacterium a good candidate to protect plants from toxicity in metal-stressed environments, also supplying N (Rizvi et al. 2019). Studies conducted on the melanin-producing endophytic *Bacillus subtilis* 4NP-BL isolated from the halophile plant *Salicornia brachiata* suggest that bacterial melanin could be involved in the protection of the host plant from environmental stresses and pathogens (Ghadge et al. 2020).

Induction of melanin production in *Pseudoalteromonas* sp. SM9913 that occurs at elevated temperatures or during biofilm formation might have a role in the adaptive responses of marine bacteria to environmental signals (Zeng et al. 2017a). In addition, melanin is related to interactions between bacterial biofilms and other organisms. Melanin secreted by biofilms of the marine bacterium *Pseudoalteromonas lipolytica* inhibits the larval settlement and metamorphosis of mussels, thus reducing the colonization of surfaces that leads to biofouling (Zeng et al. 2017b) (Fig. 1). *Shewanella* species establish symbioses with several metazoans (Lemaire et al. 2020), and in particular, in *S. colwelliana* melanin was reported to play a role in this process. A study mimicking the niche intertidal conditions performed using this bacterium showed higher biofilm formation and enhanced exopolysaccharides and melanin production that in turn increased the settlement of oyster larvae (Mitra et al. 2015). Contrasting results regarding biofouling activities suggest that melanin could act differently depending on the species involved or the environmental conditions, so further studies are necessary to elucidate the effect of melanin in complex communities in which bacteria interact with different organisms.

The photodamage protection conferred by bacterial melanin can be extended to other organisms living in close association. The dark pigmentation of sponges provided by melanogenic symbionts belonging to different bacterial genera such as *Vibrio*, *Bacillus*, *Providencia*, and *Shewanella*, also protects sponge cells from photodamage (Vijayan et al. 2017). The fact that several non-phylogenetically related bacteria sharing the same ecological niche produce melanins suggests that these pigments have an important role in this ecosystem (Fig. 1).

Melanin can also contribute to defenses against predation (Fig. 1). In *V. cholerae* biofilms, melanin production increases ROS production, protecting the bacteria from amoeba predation (Noorian et al. 2017).

When *Myxococcus xanthus* predaes on *S. meliloti*, copper accumulation is observed in the region of contact between these bacteria. This induces copper detoxification mechanisms in the predator, and melanin production in the prey. Mutants of *S. meliloti* unable to produce melanin are more sensitive to predation (Contreras-Moreno et al. 2020).

6 Concluding Remarks

The broad distribution of melanin synthesis among many groups of bacteria and the diverse metabolic pathways that can lead to their synthesis suggest that these compounds have important roles in several aspects of bacterial physiology.

Furthermore, some bacteria can synthesize melanins with different chemical compositions suggesting that the benefits of synthesizing these pigments outweigh the metabolic burden involved in maintaining multiple melanin synthesizing pathways.

The diverse roles already described for melanins involve protection from environmental stress, especially in extreme environments, and affect the relationships between bacteria and those of bacteria with animals and plants. Phylogenetic analysis of melanin synthesis in bacteria reveals that this trait seems to have risen or been acquired independently many times, probably as a characteristic associated with fitness and survival. The growing body of evidence that links melanin formation to a great number of physiological processes suggests that the role of melanin synthesis is diverse and relevant to microorganisms with many different lifestyles.

References

- Agodi A, Stefani S, Corsaro C et al (1996) Study of a melanic pigment of *Proteus mirabilis*. Res Microbiol 147:167–174. [https://doi.org/10.1016/0923-2508\(96\)80216-6](https://doi.org/10.1016/0923-2508(96)80216-6)
- Ahmad S, Lee SY, Kong HG et al (2016) Genetic determinants for pyomelanin production and its protective effect against oxidative stress in *Ralstonia solanacearum*. PLoS One 11:e0160845. <https://doi.org/10.1371/journal.pone.0160845>
- Al Khatib M, Harir M, Costa J et al (2018) Spectroscopic characterization of natural melanin from a *Streptomyces cyaneofuscatus* strain and comparison with melanin enzymatically synthesized by tyrosinase and laccase. Molecules 23:1916. <https://doi.org/10.3390/molecules23081916>
- Alexandre G, Zhulin IB (2000) Laccases are widespread in bacteria. Trends Biotechnol 18:41–42. [https://doi.org/10.1016/s0167-7799\(99\)01406-7](https://doi.org/10.1016/s0167-7799(99)01406-7)
- Arai T, Mikami Y (1972) Chromogenicity of *Streptomyces*. Appl Microbiol 23:402–406. <https://doi.org/10.1128/am.23.2.402-406.1972>
- Banerjee A, Supakar S, Banerjee R (2014) Melanin from the nitrogen fixing bacterium *Azotobacter chroococcum*: a spectroscopic characterization. PLoS One 9:e84574. <https://doi.org/10.1371/journal.pone.0084574>
- Bayram S, Dengiz C, Gerçek YC et al (2020) Bioproduction, structure elucidation and in vitro antiproliferative effect of eumelanin pigment from *Streptomyces parvus* BSB49. Arch Microbiol 202:2401–2409. <https://doi.org/10.1007/s00203-020-01956-2>
- Beijerinck MW (1900) Sur la production de quinone par le *Streptothrix chromogena*, et la biologie de ce microbe. In: Archives Néerlandaises des Sciences Exactes et Naturelles, Serie II, Tome III. Société hollandaise des sciences à Harlem, La Haye, pp 327–340
- Beijerinck MW (1911) Pigments as products of oxidation by bacterial action. In: Proceedings of the Royal Netherlands Academy of Arts and Sciences (KNAW) 13 II, 1910–1911, Amsterdam, pp 1066–1077
- Belozerskaya TA, Gessler NN, Aver'yanov AA (2017) Melanin pigments of fungi. In: Mérillon J-N, Ramawat KG (eds) Fungal metabolites (Reference series in phytochemistry), 1st edn. Springer, Switzerland, pp 263–291. https://doi.org/10.1007/978-3-319-25001-4_29
- Bizio B (1825) Ricerche chimiche sopra l'inchiostro della Seppia. Giornale di fisica, chimica, storia naturale, medicina, ed Arti Decade II VIII:88–108
- Borthakur D, Lamb JW, Johnston AW (1987) Identification of two classes of *Rhizobium phaseoli* genes required for melanin synthesis, one of which is required for nitrogen fixation and activates the transcription of the other. Mol Gen Genet 207:155–160. <https://doi.org/10.1007/bf00331503>

- Cao ZL, Tan TT, Jiang K et al (2018) Complete genome sequence of *Bacillus thuringiensis* L-7601, a wild strain with high production of melanin. *J Biotechnol* 275:40–43. <https://doi.org/10.1016/j.jbiotec.2018.03.020>
- Carletti G, Nervo G, Cattivelli L (2014) Flavonoids and melanins: a common strategy across two kingdoms. *Int J Biol Sci* 10:1159–1170. <https://doi.org/10.7150/ijbs.9672>
- Coelho-Souza T, Martins N, Maia F et al (2014) Pyomelanin production: a rare phenotype in *Acinetobacter baumannii*. *J Med Microbiol* 63:152–154. <https://doi.org/10.1099/jmm.0.064089-0>
- Contreras-Moreno FJ, Muñoz-Dorado J, García-Tomsig NI et al (2020) Copper and melanin play a role in *Myxococcus xanthus* predation on *Sinorhizobium meliloti*. *Front Microbiol* 11:94. <https://doi.org/10.3389/fmicb.2020.00094>
- Coyne VE, Al-Harhi L (1992) Induction of melanin biosynthesis in *Vibrio cholerae*. *Appl Environ Microbiol* 58:2861–2865. <https://doi.org/10.1128/aem.58.9.2861-2865.1992>
- Croxatto A, Chalker VJ, Lauritz J et al (2002) VanT, a homologue of *Vibrio harveyi* LuxR, regulates serine, metalloprotease, pigment, and biofilm production in *Vibrio anguillarum*. *J Bacteriol* 184:1617–1629. <https://doi.org/10.1128/jb.184.6.1617-1629.2002>
- Cubo MT, Buendia-Claveria AM, Beringer JE et al (1988) Melanin production by *Rhizobium* strains. *Appl Environ Microbiol* 54:1812–1817. <https://doi.org/10.1128/aem.54.7.1812-1817.1988>
- Denoya CD, Skinner DD, Morgenstern MR (1994) A *Streptomyces avermitilis* gene encoding a 4-hydroxyphenylpyruvic acid dioxygenase-like protein that directs the production of homogentisic acid and an ochronotic pigment in *Escherichia coli*. *J Bacteriol* 176:5312–5319. <https://doi.org/10.1128/jb.176.17.5312-5319.1994>
- Diamantidis G, Effosse A, Potier P et al (2000) Purification and characterization of the first bacterial laccase in the rhizospheric bacterium *Azospirillum lipoferum*. *Soil Biol Biochem* 32:919–927. [https://doi.org/10.1016/S0038-0717\(99\)00221-7](https://doi.org/10.1016/S0038-0717(99)00221-7)
- Drewnowska JM, Zambrzycka M, Kalska-Szostko B et al (2015) Melanin-like pigment synthesis by soil *Bacillus weihenstephanensis* isolates from northeastern Poland. *PLoS One* 10:e0125428. <https://doi.org/10.1371/journal.pone.0125428>
- El-Naggar NE, El-Ewasy SM (2017) Bioproduction, characterization, anticancer and antioxidant activities of extracellular melanin pigment produced by newly isolated microbial cell factories *Streptomyces glaucescens* NEAE-H. *Sci Rep* 7:42129. <https://doi.org/10.1038/srep42129>
- Eskandari S, Etemadifar Z (2021a) Melanin biopolymers from newly isolated *Pseudomonas koreensis* strain UIS 19 with potential for cosmetics application, and optimization on molasses waste medium. *J Appl Microbiol* 131:1331–1343. <https://doi.org/10.1111/jam.15046>
- Eskandari S, Etemadifar Z (2021b) Biocompatibility and radioprotection by newly characterized melanin pigment and its production from *Dietzia schimae* NM3 in optimized whey medium by response surface methodology. *Ann Microbiol* 71:1–13. <https://doi.org/10.1186/s13213-021-01628-6>
- Faccio G, Kruus K, Saloheimo M et al (2012) Bacterial tyrosinases and their applications. *Process Biochem* 47:1749–1760. <https://doi.org/10.1016/j.procbio.2012.08.018>
- Fernández-Cañón JM, Granadino B, Beltrán-Valero de Bernabé D et al (1996) The molecular basis of alkaptonuria. *Nat Genet* 14:19–24. <https://doi.org/10.1038/ng0996-19>
- Flydal MI, Chatfield CH, Zheng H et al (2012) Phenylalanine hydroxylase from *Legionella pneumophila* is a thermostable enzyme with a major functional role in pyomelanin synthesis. *PLoS One* 7:e46209. <https://doi.org/10.1371/journal.pone.0046209>
- Funai N, Ohnishi Y, Fujii I et al (1999) A new pathway for polyketide synthesis in microorganisms. *Nature* 400:897–899. <https://doi.org/10.1038/23748>
- Funai N, Funabashi M, Ohnishi Y et al (2005) Biosynthesis of hexahydroxyperylenequinone melanin via oxidative aryl coupling by cytochrome P-450 in *Streptomyces griseus*. *J Bacteriol* 187:8149–8155. <https://doi.org/10.1128/JB.187.23.8149-8155.2005>

- Gamal Shalaby AS, Ragab TIM, Helal MMI et al (2019) Optimization of *Bacillus licheniformis* MAL tyrosinase: in vitro anticancer activity for brown and black eumelanin. *Heliyon* 5:e01657. <https://doi.org/10.1016/j.heliyon.2019.e01657>
- Ganesh Kumar C, Sahu N, Narend Reddy G et al (2013) Production of melanin pigment from *Pseudomonas stutzeri* isolated from red seaweed *Hypnea musciformis*. *Lett Appl Microbiol* 57: 295–302. <https://doi.org/10.1111/lam.12111>
- Ghadge V, Kumar P, Singh S et al (2020) Natural melanin produced by the endophytic *Bacillus subtilis* 4NP-BL associated with the halophyte *Salicornia brachiata*. *J Agric Food Chem* 68: 6854–6863. <https://doi.org/10.1021/acs.jafc.0c01997>
- Givaudan A, Effosse A, Faure D et al (1993) Polyphenol oxidase in *Azospirillum lipoferum* isolated from rice rhizosphere: evidence for laccase activity in non-motile strains of *Azospirillum lipoferum*. *FEMS Microbiol Lett* 108:205–210. <https://doi.org/10.1111/j.1574-6968.1993.tb06100.x>
- Glagoleva AY, Shoeva OY, Khlestkina EK (2020) Melanin pigment in plants: current knowledge and future perspectives. *Front Plant Sci* 11:770. <https://doi.org/10.3389/fpls.2020.00770>
- Gonyar LA, Fankhauser SC, Goldberg JB (2015) Single amino acid substitution in homogentisate 1,2-dioxygenase is responsible for pigmentation in a subset of *Burkholderia cepacia* complex isolates. *Environ Microbiol Rep* 7:180–187. <https://doi.org/10.1111/1758-2229.12217>
- Goodwin PH, Sopher CR (1994) Brown pigmentation of *Xanthomonas campestris* pv. *phaseoli* associated with homogentisic acid. *Can J Microbiol* 40:28–34. <https://doi.org/10.1139/m94-005>
- Goudenège D, Labreuche Y, Krin E et al (2013) Comparative genomics of pathogenic lineages of *Vibrio nigripulchritudo* identifies virulence-associated traits. *ISME J* 7:1985–1996. <https://doi.org/10.1038/ismej.2013.90>
- Gowri PM, Srivastava S (1996) Encapsulation as a response of *Azospirillum brasilense* sp7 to zinc stress. *World J Microbiol Biotechnol* 12:319–322. <https://doi.org/10.1007/BF00340207>
- Guo J, Rao Z, Yang T et al (2014) High-level production of melanin by a novel isolate of *Streptomyces kathirae*. *FEMS Microbiol Lett* 357:85–91. <https://doi.org/10.1111/1574-6968.12497>
- Han H, Iakovenko L, Wilson AC (2015) Loss of homogentisate 1,2-dioxygenase activity in *Bacillus anthracis* results in accumulation of protective pigment. *PLoS One* 10:e0128967. <https://doi.org/10.1371/journal.pone.0128967>
- Harir M, Bellahcene M, Baratto MC et al (2018) Isolation and characterization of a novel tyrosinase produced by Sahara soil actinobacteria and immobilization on nylon nanofiber membranes. *J Biotechnol* 265:54–64. <https://doi.org/10.1016/j.jbiotec.2017.11.004>
- Hawkins FK, Johnston AW (1988) Transcription of a *Rhizobium leguminosarum* biovar *phaseoli* gene needed for melanin synthesis is activated by *nifA* of *Rhizobium* and *Klebsiella pneumoniae*. *Mol Microbiol* 2:331–337. <https://doi.org/10.1111/j.1365-2958.1988.tb00036.x>
- He P, Moran GR (2009) We two alone will sing: the two-substrate α -keto acid-dependent oxygenases. *Curr Opin Chem Biol* 13:443–450. <https://doi.org/10.1016/j.cbpa.2009.06.012>
- Held T, Kutzner HJ (1990) Transcription of the tyrosinase gene in *Streptomyces michiganensis* DSM 40015 is induced by copper and repressed by ammonium. *J Gen Microbiol* 136:2413–2419. <https://doi.org/10.1099/00221287-136-12-2413>
- Hernández-Romero D, Solano F, Sanchez-Amat A (2005) Polyphenol oxidase activity expression in *Ralstonia solanacearum*. *Appl Environ Microbiol* 71:6808–6815. <https://doi.org/10.1128/AEM.71.11.6808-6815.2005>
- Herrera MC, Krell T, Zhang X et al (2009) PhhR binds to target sequences at different distances with respect to RNA polymerase in order to activate transcription. *J Mol Biol* 394:576–586. <https://doi.org/10.1016/j.jmb.2009.09.045>
- Herter S, Schmidt M, Thompson ML et al (2011) A new phenol oxidase produced during melanogenesis and encystment stage in the nitrogen-fixing soil bacterium *Azotobacter chroococcum*. *Appl Microbiol Biotechnol* 90:1037–1049. <https://doi.org/10.1007/s00253-011-3093-x>

- Hiramatsu Y, Nishida T, Nugraha DK et al (2021) Melanin produced by *Bordetella parapertussis* confers a survival advantage to the bacterium during host infection. *mSphere* 6:e0081921. <https://doi.org/10.1128/mSphere.00819-21>
- Hocquet D, Petitjean M, Rohmer L et al (2016) Pyomelanin-producing *Pseudomonas aeruginosa* selected during chronic infections have a large chromosomal deletion which confers resistance to pyocins. *Environ Microbiol* 18:3482–3493. <https://doi.org/10.1111/1462-2920.13336>
- Hunter RC, Newman DK (2010) A putative ABC transporter, HatABCDE, is among molecular determinants of pyomelanin production in *Pseudomonas aeruginosa*. *J Bacteriol* 192:5962–5971. <https://doi.org/10.1128/JB.01021-10>
- Ikeda K, Masujima T, Suzuki K et al (1996) Cloning and sequence analysis of the highly expressed melanin-synthesizing gene operon from *Streptomyces castaneoglobisporus*. *Appl Microbiol Biotechnol* 45:80–85. <https://doi.org/10.1007/s002530050652>
- Ivanova EP, Gorshkova NM, Zhukova NV et al (2004) Characterization of *Pseudoalteromonas distincta*-like sea-water isolates and description of *Pseudoalteromonas aliena* sp. nov. *Int J Syst Evol Microbiol* 54:1431–1437. <https://doi.org/10.1099/ijs.0.03053-0>
- Janda JM, Abbott SL (2010) The genus *Aeromonas*: taxonomy, pathogenicity, and infection. *Clin Microbiol Rev* 23:35–73. <https://doi.org/10.1128/CMR.00039-09>
- Jiang L, Jeon D, Kim J et al (2021) Pyomelanin-producing *Brevundimonas vitisensis* sp. nov., isolated from grape (*Vitis vinifera* L.). *Front Microbiol* 12:733612. <https://doi.org/10.3389/fmicb.2021.733612>
- Kamarudheen N, Naushad T, Rao KVB (2019) Biosynthesis, characterization and antagonistic applications of extracellular melanin pigment from marine *Nocardiosis* sps. *Ind J Pharm Educ Res* 53:112–120. <https://doi.org/10.5530/ijper.53.2s.55>
- Keith KE, Killip L, He P et al (2007) *Burkholderia cenocepacia* C5424 produces a pigment with antioxidant properties using a homogentisate intermediate. *J Bacteriol* 189:9057–9065. <https://doi.org/10.1128/JB.00436-07>
- Kelley SK, Coyne VE, Sledjeski DD et al (1990) Identification of a tyrosinase from a periphytic marine bacterium. *FEMS Microbiol Lett* 67:275–279. [https://doi.org/10.1016/0378-1097\(90\)90008-E](https://doi.org/10.1016/0378-1097(90)90008-E)
- Kim H, Yeon YJ, Choi YR et al (2016) A cold-adapted tyrosinase with an abnormally high monophenolase/diphenolase activity ratio originating from the marine archaeon *Candidatus Nitrosopumilus koreensis*. *Biotechnol Lett* 38:1535–1542. <https://doi.org/10.1007/s10529-016-2125-0>
- Kimura T, Fukuda W, Sanada T et al (2015) Characterization of water-soluble dark-brown pigment from Antarctic bacterium, *Lysobacter oligotrophicus*. *J Biosci Bioeng* 120:58–61. <https://doi.org/10.1016/j.jbiosc.2014.11.020>
- Kiran GS, Dhasayan A, Lipton AN et al (2014) Melanin-templated rapid synthesis of silver nanostructures. *J Nanobiotechnol* 12:18. <https://doi.org/10.1186/1477-3155-12-18>
- Kotob SI, Coon SL, Quintero EJ et al (1995) Homogentisic acid is the primary precursor of melanin synthesis in *Vibrio cholerae*, a *Hyphomonas* strain, and *Shewanella colwelliana*. *Appl Environ Microbiol* 61:1620–1622. <https://doi.org/10.1128/aem.61.4.1620-1622.1995>
- Kurian NK, Bhat SG (2018a) Food, cosmetic and biological applications of characterized DOPA-melanin from *Vibrio alginolyticus* strain BTKKS3. *Appl Biol Chem* 61:163–171. <https://doi.org/10.1007/s13765-018-0343-y>
- Kurian NK, Bhat SG (2018b) Data on the characterization of non-cytotoxic pyomelanin produced by marine *Pseudomonas stutzeri* BTCZ10 with cosmetological importance. *Data Brief* 18: 1889–1894. <https://doi.org/10.1016/j.dib.2018.04.123>
- Laxmi M, Kurian NK, Smitha S et al (2016) Melanin and bacteriocin from marine bacteria inhibit biofilms of foodborne pathogens. *Indian J Biotechnol* 15:392–399
- Lee HS, Choi JY, Kwon SJ et al (2022) Melanin biopolymer synthesis using a new melanogenic strain of *Flavobacterium kingsejongi* and a recombinant strain of *Escherichia coli* expressing 4-hydroxyphenylpyruvate dioxygenase from *F. kingsejongi*. *Microb Cell Factories* 21:75. <https://doi.org/10.1186/s12934-022-01800-w>

- Lemaire ON, Méjean V, Iobbi-Nivol C (2020) The *Shewanella* genus: ubiquitous organisms sustaining and preserving aquatic ecosystems. *FEMS Microbiol Rev* 44:155–170. <https://doi.org/10.1093/femsre/fuz031>
- Lerch K, Ettinger L (1972) Purification and characterization of a tyrosinase from *Streptomyces glaucescens*. *Eur J Biochem* 31:427–437. <https://doi.org/10.1111/j.1432-1033.1972.tb02549.x>
- Leu WM, Chen LY, Liaw LL et al (1992) Secretion of the *Streptomyces* tyrosinase is mediated through its trans-activator protein, MelC1. *J Biol Chem* 267:20108–20113. [https://doi.org/10.1016/S0021-9258\(19\)88672-6](https://doi.org/10.1016/S0021-9258(19)88672-6)
- Liu N, Zhang T, Wang YJ et al (2004) A heat inducible tyrosinase with distinct properties from *Bacillus thuringiensis*. *Lett Appl Microbiol* 39:407–412. <https://doi.org/10.1111/j.1472-765X.2004.01599.x>
- López-Serrano D, Solano F, Sanchez-Amat A (2004) Identification of an operon involved in tyrosinase activity and melanin synthesis in *Marinomonas mediterranea*. *Gene* 342:179–187. <https://doi.org/10.1016/j.gene.2004.08.003>
- Lucas-Elío P, Solano F, Sanchez-Amat A (2002) Regulation of polyphenol oxidase activities and melanin synthesis in *Marinomonas mediterranea*: identification of *ppoS*, a gene encoding a sensor histidine kinase. *Microbiology* 148:2457–2466. <https://doi.org/10.1099/00221287-148-8-2457>
- Manivasagan P, Venkatesan J, Senthilkumar K et al (2013) Isolation and characterization of biologically active melanin from *Actinoalloteichus* sp. MA-32. *Int J Biol Macromol* 58:263–274. <https://doi.org/10.1016/j.ijbiomac.2013.04.041>
- Martínez LM, Martínez A, Gosset G (2019) Production of melanins with recombinant microorganisms. *Front Bioeng Biotechnol* 7:285. eCollection 2019. <https://doi.org/10.3389/fbioe.2019.00285>
- Marín-Sanhueza C, Echeverría-Vega A, Gómez A et al (2022) Stress dependent biofilm formation and bioactive melanin pigment production by a thermophilic *Bacillus* species from Chilean hot spring. *Polymers (Basel)* 14:680. <https://doi.org/10.3390/polym14040680>
- McMahon AM, Doyle EM, Brooks S et al (2007) Biochemical characterisation of the coexisting tyrosinase and laccase in the soil bacterium *Pseudomonas putida* F6. *Enzym Microb Technol* 40:1435–1441. <https://doi.org/10.1016/j.enzmictec.2006.10.020>
- Mekala LP, Mohammed M, Chinthalapati S et al (2019) Pyomelanin production: insights into the incomplete aerobic L-phenylalanine catabolism of a photosynthetic bacterium, *Rubrivivax benzoatilyticus* JA2. *Int J Biol Macromol* 126:755–764. <https://doi.org/10.1016/j.ijbiomac.2018.12.142>
- Mencher JR, Heim AH (1962) Melanin biosynthesis by *Streptomyces lavendulae*. *J Gen Microbiol* 28:665–670. <https://doi.org/10.1099/00221287-28-4-665>
- Méndez V, Agulló L, González M et al (2011) The homogentisate and homoprotocatechuate central pathways are involved in 3- and 4-hydroxyphenylacetate degradation by *Burkholderia xenovorans* LB400. *PLoS One* 6:e17583. <https://doi.org/10.1371/journal.pone.0017583>
- Mercado-Blanco J, García F, Fernández-López M et al (1993) Melanin production by *Rhizobium meliloti* GR4 is linked to nonsymbiotic plasmid pRmeGR4b: cloning, sequencing, and expression of the tyrosinase gene *mepA*. *J Bacteriol* 175:5403–5410. <https://doi.org/10.1128/jb.175.17.5403-5410.1993>
- Mitra S, Gachhui R, Mukherjee J (2015) Enhanced biofilm formation and melanin synthesis by the oyster settlement-promoting *Shewanella colwelliana* is related to hydrophobic surface and simulated intertidal environment. *Biofouling* 31:283–296. <https://doi.org/10.1080/08927014.2015.1038705>
- Nikodinovic-Runic J, Martin LB et al (2009) Characterization of melanin-overproducing transposon mutants of *Pseudomonas putida* F6. *FEMS Microbiol Lett* 298:174–183. <https://doi.org/10.1111/j.1574-6968.2009.01716.x>
- Noorian P, Hu J, Chen Z et al (2017) Pyomelanin produced by *Vibrio cholerae* confers resistance to predation by *Acanthamoeba castellanii*. *FEMS Microbiol Ecol* 93(12). <https://doi.org/10.1093/femsec/fix147>

- Nosanchuk JD, Casadevall A (2003) The contribution of melanin to microbial pathogenesis. *Cell Microbiol* 5:203–223. <https://doi.org/10.1046/j.1462-5814.2003.00268.x>
- Nosanchuk JD, Casadevall A (2006) Impact of melanin on microbial virulence and clinical resistance to antimicrobial compounds. *Antimicrob Agents Chemother* 50:3519–3528. <https://doi.org/10.1128/AAC.00545-06>
- Omura S, Ikeda H, Ishikawa J et al (2001) Genome sequence of an industrial microorganism *Streptomyces avermitilis*: deducing the ability of producing secondary metabolites. *Proc Natl Acad Sci U S A* 98:12215–12220. <https://doi.org/10.1073/pnas.211433198>
- Orlandi VT, Bolognese F, Chiodaroli L et al (2015) Pigments influence the tolerance of *Pseudomonas aeruginosa* PAO1 to photodynamically induced oxidative stress. *Microbiology* 161: 2298–2309. <https://doi.org/10.1099/mic.0.000193>
- Page WJ, Shivprasad S (1991) *Azotobacter salinestris* sp. nov., a sodium-dependent, microaerophilic, and aerotolerant nitrogen-fixing bacterium. *Int J Syst Evol Microbiol* 41: 369–376. <https://doi.org/10.1099/00207713-41-3-369>
- Palmer GC, Palmer KL, Jorth PA et al (2010) Characterization of the *Pseudomonas aeruginosa* transcriptional response to phenylalanine and tyrosine. *J Bacteriol* 192:2722–2728. <https://doi.org/10.1128/JB.00112-10>
- Pavan ME, Abbott SL, Zorzópulos J et al (2000) *Aeromonas salmonicida* subsp. *pectinolytica* subsp. nov., a new pectinase positive subspecies isolated from a heavily polluted river. *Int J Syst Evol Microbiol* 50:1119–1124. <https://doi.org/10.1099/00207713-50-3-1119>
- Pavan ME, Pavan EE, López NI et al (2015) Living in an extremely polluted environment: clues from the genome of melanin-producing *Aeromonas salmonicida* subsp. *pectinolytica* 34mel^T. *Appl Environ Microbiol* 81:5235–5248. <https://doi.org/10.1128/AEM.00903-15>
- Pavan ME, Solar Venero E, Egoburo DE et al (2019) Glycerol inhibition of melanin biosynthesis in the environmental *Aeromonas salmonicida* 34mel^T. *Appl Microbiol Biotechnol* 103:1865–1876. <https://doi.org/10.1007/s00253-018-9545-9>
- Pavan ME, López NI, Pettinari MJ (2020) Melanin biosynthesis in bacteria, regulation and production perspectives. *Appl Microbiol Biotechnol* 104:1357–1370. <https://doi.org/10.1007/s00253-019-10245-y>
- Perdomo-Morales R, Montero-Alejo V, Perera E et al (2007) Phenoloxidase activity in the hemolymph of the spiny lobster *Panulirus argus*. *Fish Shellfish Immunol* 23:1187–1195. <https://doi.org/10.1016/j.fsi.2007.04.001>
- Piñero S, Rivera J, Romero D et al (2007) Tyrosinase from *Rhizobium etli* is involved in nodulation efficiency and symbiosis-associated stress resistance. *J Mol Microbiol Biotechnol* 13:35–44. <https://doi.org/10.1159/000103595>
- Plonka PM, Grabacka M (2006) Melanin synthesis in microorganisms – biotechnological and medical aspects. *Acta Biochim Pol* 53:429–443
- Reddy GSN, Potrafka RM, Garcia-Pichel F (2007) *Modestobacter versicolor* sp. nov., an actinobacterium from biological soil crusts that produces melanins under oligotrophy, with emended descriptions of the genus *Modestobacter* and *Modestobacter multiseptatus* Mevs et al. 2000. *Int J Syst Evol Microbiol* 57:2014–2020. <https://doi.org/10.1099/ijs.0.64932-0>
- Reiss R, Ihssen J, Thöny-Meyer L (2011) *Bacillus pumilus* laccase: a heat stable enzyme with a wide substrate spectrum. *BMC Biotechnol* 11:9. <https://doi.org/10.1186/1472-6750-11-9>
- Rizvi A, Ahmed B, Zaidi A et al (2019) Bioreduction of toxicity influenced by bioactive molecules secreted under metal stress by *Azotobacter chroococcum*. *Ecotoxicology* 28:302–322. <https://doi.org/10.1007/s10646-019-02023-3>
- Rodríguez-Rojas A, Mena A, Martín S et al (2009) Inactivation of the *hmGA* gene of *Pseudomonas aeruginosa* leads to pyomelanin hyperproduction, stress resistance and increased persistence in chronic lung infection. *Microbiology* 155:1050–1057. <https://doi.org/10.1099/mic.0.024745-0>
- Ruan L, Yu Z, Fang B et al (2004) Melanin pigment formation and increased UV resistance in *Bacillus thuringiensis* following high temperature induction. *Syst Appl Microbiol* 27:286–289. <https://doi.org/10.1078/0723-2020-00265>

- Sajjan S, Kulkarni G, Yaligara V et al (2010) Purification and physiochemical characterization of melanin pigment from *Klebsiella* sp. GSK. J Microbiol Biotechnol 20:1513–1520. <https://doi.org/10.4014/jmb.1002.02006>
- Samson R, Shafik H, Benjama A et al (1998) Description of the bacterium causing blight of leek as *Pseudomonas syringae* pv. *porri* (pv. nov.). Phytopathology 88:844–850. <https://doi.org/10.1094/PHYTO.1998.88.8.844>
- Sanchez-Amat A, Ruzafa C, Solano F (1998) Comparative tyrosine degradation in *Vibrio cholerae* strains. The strain ATCC 14035 as a prokaryotic melanogenic model of homogenisate-releasing cell. Comp Biochem Physiol B Biochem Mol Biol 119:557–562. [https://doi.org/10.1016/S0305-0491\(98\)00028-5](https://doi.org/10.1016/S0305-0491(98)00028-5)
- Sanchez-Amat A, Solano F, Lucas-Elío P (2010) Finding new enzymes from bacterial physiology: a successful approach illustrated by the detection of novel oxidases in *Marinomonas mediterranea*. Mar Drugs 8:519–541. <https://doi.org/10.3390/md8030519>
- Saud HM, Alaubdy MA (2019) Effect of clinical *Klebsiella pneumoniae* extracted melanin on some immune aspects in mice. Iraqi J Agric Sci 50:352–358. <https://doi.org/10.36103/ijas.v50i1.301>
- Seelam SD, Agsar D, Shetty PR et al (2021) Characterization and photoprotective potentiality of lime dwelling *Pseudomonas* mediated melanin as sunscreen agent against UV-B radiations. J Photochem Photobiol B Biol 216:112126. <https://doi.org/10.1016/j.jphotobiol.2021.112126>
- Seo D, Choi KY (2020) Heterologous production of pyomelanin biopolymer using 4-hydroxyphenylpyruvate dioxygenase isolated from *Ralstonia pickettii* in *Escherichia coli*. Biochem Eng J 157:107548. <https://doi.org/10.1016/j.bej.2020.107548>
- Sharma KK, Kuhad RC (2009) An evidence of laccases in archaea. Indian J Microbiol 49:142–150. <https://doi.org/10.1007/s12088-009-0039-4>
- Sharma A, Jain KK, Jain A et al (2018) Bifunctional in vivo role of laccase exploited in multiple biotechnological applications. Appl Microbiol Biotechnol 102:10327–10343. <https://doi.org/10.1007/s00253-018-9404-8>
- Shivprasad S, Page WJ (1989) Catechol formation and melanization by Na⁺-dependent *Azotobacter chroococcum*: a protective mechanism for aeroadaptation? Appl Environ Microbiol 55:1811–1817. <https://doi.org/10.1128/aem.55.7.1811-1817.1989>
- Shuster V, Fishman A (2009) Isolation, cloning and characterization of a tyrosinase with improved activity in organic solvents from *Bacillus megaterium*. J Mol Microbiol Biotechnol 17:188–200. <https://doi.org/10.1159/000233506>
- Singh G, Bhalla A, Kaur P et al (2011) Laccase from prokaryotes: a new source for an old enzyme. Rev Environ Sci Biotechnol 10:309–326. <https://doi.org/10.1007/s11157-011-9257-4>
- Singh D, Kumar J, Kumar A (2018) Isolation of pyomelanin from bacteria and evidences showing its synthesis by 4-hydroxyphenylpyruvate dioxygenase enzyme encoded by *hpdD* gene. Int J Biol Macromol 119:864–873. <https://doi.org/10.1016/j.ijbiomac.2018.08.003>
- Solano F (2014) Melanins: skin pigments and much more – types, structural models, biological functions, and formation routes. New J Sci. Article ID 498276. <https://doi.org/10.1155/2014/498276>
- Solano F, Lucas-Elío P, Fernández E et al (2000) *Marinomonas mediterranea* MMB-1 transposon mutagenesis: isolation of a multipotent polyphenol oxidase mutant. J Bacteriol 182:3754–3760. <https://doi.org/10.1128/jb.182.13.3754-3760.2000>
- Surwase SN, Jadhav SB, Phugare SS et al (2013) Optimization of melanin production by *Brevundimonas* sp. SGJ using response surface methodology. Biotech 3:187–194. <https://doi.org/10.1007/s13205-012-0082-4>
- Takano H, Asano K, Beppu T et al (2007) Role of σ^H paralogs in intracellular melanin formation and spore development in *Streptomyces griseus*. Gene 393:43–52. <https://doi.org/10.1016/j.gene.2007.01.026>
- Tarangini K, Mishra S (2013) Production, characterization and analysis of melanin from isolated marine *Pseudomonas* sp. using vegetable waste. Res J Engineering Sci 2:40–46

- Tarangini K, Mishra S (2014) Production of melanin by soil microbial isolate on fruit waste extract: two step optimization of key parameters. *Biotechnol Rep* 4:139–146. <https://doi.org/10.1016/j.btre.2014.10.001>
- Toledo AV, Franco MEE, López SMY et al (2017) Melanins in fungi: types, localization and putative biological roles. *Physiol Mol Plant Pathol* 99:2–6. <https://doi.org/10.1016/j.pmp.2017.04.004>
- Trias J, Viñas M, Guinea J et al (1989) Brown pigmentation in *Serratia marcescens* cultures associated with tyrosine metabolism. *Can J Microbiol* 35:1037–1042. <https://doi.org/10.1139/m89-172>
- Turick CE, Tisa LS, Caccavo F Jr (2002) Melanin production and use as a soluble electron shuttle for Fe(III) oxide reduction and as a terminal electron acceptor by *Shewanella algae* BrY. *Appl Environ Microbiol* 68:2436–2444. <https://doi.org/10.1128/AEM.68.5.2436-2444.2002>
- Turick CE, Beliaev AS, Zakrajsek BA et al (2009) The role of 4-hydroxyphenylpyruvate dioxygenase in enhancement of solid phase electron transfer by *Shewanella oneidensis* MR-1. *FEMS Microbiol Ecol* 68:223–235. <https://doi.org/10.1111/j.1574-6941.2009.00670.x>
- Valeru SP, Rompikuntal PK, Ishikawa T et al (2009) Role of melanin pigment in expression of *Vibrio cholerae* virulence factors. *Infect Immun* 77:935–942. <https://doi.org/10.1128/IAI.00929-08>
- Vijayan V, Jasmin C, Anas A et al (2017) Sponge-associated bacteria produce non-cytotoxic melanin which protects animal cells from photo-toxicity. *Appl Biochem Biotechnol* 183:396–411. <https://doi.org/10.1007/s12010-017-2453-0>
- Wang G, Aazaz A, Peng Z et al (2000) Cloning and overexpression of a tyrosinase gene *mel* from *Pseudomonas maltophilia*. *FEMS Microbiol Lett* 185:23–27. <https://doi.org/10.1111/j.1574-6968.2000.tb09035.x>
- Wang R, Wang H, Zhou H et al (2011) Characters of homogentisate oxygenase gene mutation and high clonality of the natural pigment-producing *Vibrio cholerae* strains. *BMC Microbiol* 11: 109. <https://doi.org/10.1186/1471-2180-11-109>
- Wang H, Qiao Y, Chai B et al (2015) Identification and molecular characterization of the homogentisate pathway responsible for pyomelanin production, the major melanin constituents in *Aeromonas media* WS. *PLoS One* 10:e0120923. <https://doi.org/10.1371/journal.pone.0120923>
- Wu CC, Li H, Yin ZW et al (2022) Isolation, purification, and characterization of novel melanin from the submerged fermentation of *Rhizobium radiobacter*. *Process Biochem* 121:263–275. <https://doi.org/10.1016/j.procbio.2022.07.009>
- Yabuuchi E, Ohyama A (1972) Characterization of “pyomelanin”-producing strains of *Pseudomonas aeruginosa*. *Int J Syst Bacteriol* 22:53–64. <https://doi.org/10.1099/00207713-22-2-53>
- Yuan W, Burleigh SH, Dawson JO (2007) Melanin biosynthesis by *Frankia* strain CeI5. *Physiol Plant* 131:180–190. <https://doi.org/10.1111/j.1399-3054.2007.00948.x>
- Zaidi KU, Ali AS, Ali SA et al (2014) Microbial tyrosinases: promising enzymes for pharmaceutical, food bioprocessing, and environmental industry. *Biochem Res Int*. <https://doi.org/10.1155/2014/854687>
- Zeng Z, Cai X, Wang P et al (2017a) Biofilm formation and heat stress induce pyomelanin production in deep-sea *Pseudoalteromonas* sp. SM9913. *Front Microbiol* 8:1822. <https://doi.org/10.3389/fmicb.2017.01822>
- Zeng Z, Guo XP, Cai X et al (2017b) Pyomelanin from *Pseudoalteromonas lipolytica* reduces biofouling. *Microb Biotechnol* 10:1718–1731. <https://doi.org/10.1111/1751-7915.12773>

- Zha H, Jeffs A, Dong Y et al (2018) Potential virulence factors of bacteria associated with tail fan necrosis in the spiny lobster, *Jasus edwardsii*. J Fish Dis 41:817–828. <https://doi.org/10.1111/jfd.12791>
- Zhang J, Cai J, Deng Y et al (2007) Characterization of melanin produced by a wild-type strain of *Bacillus cereus*. Front Biol China 2:26–29. <https://doi.org/10.2323/jgam.50.183>
- Zheng H, Chatfield CH, Liles MR et al (2013) Secreted pyomelanin of *Legionella pneumophila* promotes bacterial iron uptake and growth under iron-limiting conditions. Infect Immun 81: 4182–4191. <https://doi.org/10.1128/IAI.00858-13>
- Zhu D, He X, Zhou X, Deng Z (2005) Expression of the *melC* operon in several *Streptomyces* strains is positively regulated by AdpA, an AraC family transcriptional regulator involved in morphological development in *Streptomyces coelicolor*. J Bacteriol 187:3180–3187. <https://doi.org/10.1128/JB.187.9.3180-3187.2005>

The Role of Melanin in Fungal Disease



Rosanna P. Baker, Arturo Casadevall, Emma Camacho,
Radames J. B. Cordero, Aryan Waghmode, Livia Liporagi-Lopes, Amy Liu,
Ellie Rose Mattoon, Nathan Mudrak, and Daniel F. Q. Smith

1 Fungal Melanin Biosynthesis

Members of the fungal kingdom make many types or classes of melanins. Most fungal species produce melanins of the allomelanin or eumelanin classes, canonically from the polymerization of 1,8-dihydroxynaphthalene (1,8-DHN) and derivatives of L-3,4-dihydroxyphenylalanine (L-DOPA) and other catecholamines, respectively (Eisenman and Casadevall 2012). Other fungal melanin subtypes have been reported, including pyomelanin production from homogentisate (HGA) by *Aspergillus fumigatus* (Schmaler-Ripcke et al. 2009) and GHB-melanin from the precursor glutaminyl-hydroxy-benzene (GHB) by *Agaricus biosporus* (Weijn et al. 2013). The production of a novel 5-deoxybostrycoidin-based melanin in *Fusarium* species (Frandsen et al. 2016), and an aspulvinone E-based melanin (Asp-melanin) by *Aspergillus terreus* (Geib et al. 2016) have been reported. However, further study of these novel compounds is necessary. Here, we describe the reported mechanisms of fungal biosynthesis for the three most prevalent melanin subtypes.

Aspergillus spp. as well as *W. dermatitidis* and *Sporothrix schenckii*, produce allomelanins, also known as DHN melanins (Gow et al. 2017). These melanins are black or brown, are typically attached to the inner side of fungal cell walls (Tran-Ly et al. 2020), and are produced from the polymerization of 1,8-dihydroxynaphthalene (DHN) (Britton 1983). As such, they do not contain nitrogen. DHN is produced from the polyketide pathway, which begins with either Acetyl-CoA or Malonyl-CoA.

R. P. Baker · A. Casadevall · E. Camacho · L. Liporagi-Lopes · D. F. Q. Smith ·

R. J. B. Cordero (✉)

Department of Molecular Microbiology and Immunology, Johns Hopkins Bloomberg School of Public Health, Baltimore, MD, USA

e-mail: rcorder4@jhu.edu

A. Waghmode · A. Liu · E. R. Mattoon · N. Mudrak

Johns Hopkins Krieger School of Arts and Sciences, Baltimore, MD, USA

These precursors undergo decarboxylative condensation via polyketide synthase to form 1,3,6,8-tetrahydroxynaphthalene (THN) (Singh et al. 2021). The reduction of THN by THN reductase to form scytalone is followed by two rounds of dehydration to ultimately produce the monomer DHN (Singh et al. 2021). Fungal mutants with mutations of the gene encoding polyketide synthase (pksP or alb1 for “Albino 1”) produce albino conidia in the absence of exogenous scytalone (Tanguay et al. 2006). In *Aspergillus fumigatus*, the genes for all six enzymes involved in DHN-melanin synthesis are encoded by a 19 kb gene cluster on the second chromosome (Tsai et al. 1999).

Other fungi, including *Cryptococcus neoformans*, *Candida auris*, and *Paracoccidioides brasiliensis*, produce nitrogen-containing eumelanin from catecholamine-based derivatives such as L-DOPA (Eisenman et al. 2007; Gómez et al. 2001). Eumelanin, a typically black-brown pigment, is formed by the polymerization of indoles. These indoles are canonically formed through a multi-step biosynthetic pathway, beginning with the oxidization of catecholamines into reactive quinones. These quinones can then cyclize via an intramolecular nucleophilic attack, after which their spontaneous oxidization and tautomerization form the necessary indoles (Eisenman and Casadevall 2012). While this pathway can occur spontaneously through autopolymerization, in most fungal species the first conversion to quinone is catalyzed by laccases (EC 1.10.3.2) or phenol oxidases (EC.1.14.18.1 and EC.1.10.3.1). Further, for fungal species that produce the phenol oxidase tyrosinase, the enzyme can catalyze both the oxidation of catecholamines to quinone as well as an additional precursor step converting L-tyrosine into the catecholamine L-DOPA, allowing for the production of eumelanin from an endogenous amino acid (Smith and Casadevall 2019).

In addition to the biosynthetic L-DOPA pathway originating from L-tyrosine, melanin can also be produced by the oxidation and subsequent polymerization of HGA, an intermediate in the degradation pathway of L-tyrosine. Mutation of the enzyme homogentisate dioxygenase that normally catalyzes the conversion of HGA to maleylacetoacetate in this pathway causes a rare human genetic disorder called alkaptonuria (La Du et al. 1958), characterized by a build-up of HGA and production of alkaptomelanin. Its microbial counterpart, pyomelanin, was first identified in the bacterium, *Pseudomonas aeruginosa* (Yabuuchi and Ohyama 1972), and has been discovered subsequently in several fungal species, such as *Aspergillus fumigatus*, *Sporothrix* spp., and *Histoplasma capsulatum* (Schmaler-Ripcke et al. 2009; Almeida-Paes et al. 2012, 2018). For fungal species that produce melanin by multiple pathways, pyomelanin is identified by its unique susceptibility to sulcotrione, a specific inhibitor of 4-hydroxyphenylpyruvic acid dioxygenase (HppD), the enzyme that converts 4-hydroxyphenylpyruvic acid to HGA (Lorquin et al. 2022). At least one instance of direct competition between pathways has been noted wherein pyomelanin synthesis by *Alternaria alternata* supplants the more canonical DHN-melanin pathway through down-regulation of CmrA, the key transcriptional activator of DHN-melanin synthesis genes (Fernandes et al. 2021). The upregulation of HppD that occurs upon the transition from the filamentous to parasitic yeast form of several fungal species including *H. capsulatum*,

Paracoccidioides brasiliensis, and *Talaromyces marneffeii* (Nunes et al. 2005; Boyce et al. 2015; Hwang et al. 2003) argues that pyomelanin may play a key role in fungal virulence.

2 Melanin Structure and Localization

The elucidation of melanin's exact chemical structure has been hampered due to the insoluble and heterogeneous character (e.g., variable starting monomers) of this biomaterial (Prota 1988). Any attempt at solubilization disrupts its structure and adds complexity to its structural analysis, the macroscale assembly of melanin is amorphous ("disordered") and thus not approachable with standard methods of structure determination such as X-ray crystallography. It involves supramolecular interactions within melanin and between melanin and other surrounding components. In the past three decades, the use of alternative and non-destructive spectroscopic methodologies (Casadevall et al. 2012; Chatterjee et al. 2012, 2014, 2015; Chrissian et al. 2020a–c; Baker et al. 2021; Camacho et al. 2017) along with high-resolution transmission electron microscopy (TEM) (Eisenman et al. 2005, 2009; Walker et al. 2010; Wolf et al. 2014; Franzen et al. 2008; Alviano et al. 1991; Almeida-Paes et al. 2017; Romero-Martinez et al. 2000; Freitas et al. 2019) and proteomics (Camacho et al. 2019; Almeida-Paes et al. 2020) have provided tremendous insights about the complex hierarchical assembly structure of fungal melanins.

In most fungal species, melanins are mainly deposited in layers within the cell wall displaying variations in their distribution (e.g., in inner or outer regions) (Eisenman et al. 2005; Walker et al. 2010; Franzen et al. 2008; Romero-Martinez et al. 2000; Nosanchuk and Casadevall 2003a; San-Blas et al. 1996; Bayry et al. 2014). However, given that melanin synthesis starts intracellularly, it is also detected in cytoplasmic deposits within membrane-enclosed compartments known as melanosomes as well as along the plasma membrane (Freitas et al. 2019; Camacho et al. 2019; San-Blas et al. 1996). The distribution and maintenance of melanin within the cell wall depend on covalent and non-covalent interactions with other cell wall components such as chitin, chitosan, glucan, and lipids.

The molecular organizational structure of melanins consists of locally-ordered oligomer sheets that form planar stacks with variable stacking distances due to differences in the chemical composition (Büngeler et al. 2017). In agreement with this model, studies using X-ray powder diffraction demonstrated that fungal melanins isolated from *C. neoformans*, *Wangiella dermatitidis*, *Aspergillus niger*, and *Coprinus comatus* conserved this basic stack sheet structure, with stacking distances between the melanin layers ranging from 3.46 to 4.39 Å, which may serve as a key parameter for further melanin categorization (Casadevall et al. 2012). While the supramolecular "disordered" structure is a consequence of the planar structures exhibiting diverse orientations to one another stabilized by hydrogen bonding, cation- π , and van der Waals interactions (Hong et al. 2018).

The most studied system of fungal melanin supramolecular architecture is that of *C. neoformans*, where complementary approaches have been used to elucidate its

cell wall building block unit (Camacho et al. 2019). That work investigated melanin hierarchical buildup from “melanin ghosts” (melanin carcasses from a hollow cell after acid exposure) and from structures released in the culture supernatant. Two main structures were identified: (1) Melanosomes; and (2) Melanin granules. The **melanosomes**, the structural unit of the cell-wall melanin that corresponds to ~30 nm in diameter smooth nanospheres. These are visualized by TEM within multivesicular bodies (MVBs) and vesicles in the cell cytoplasm or exposed in the cell wall after extended acid-hydrolysis of melanin ghosts. Similar melanosomes in the structure had been reported for other natural eumelanins (Xiao et al. 2018; Franzen et al. 2006). The **melanin granules** are aggregated melanosomes measuring from 40 to 200 nm in diameter, which result from the accumulation and crosslinking of melanosomes among each other and to surrounding non-pigmented components with different degrees of melanization. These are found intracellularly, within the cell wall, or in the extracellular media.

2.1 Cell-Wall Associated Melanin

Melanin granules can be arranged in layers within the cell wall (Chrissian et al. 2020a; Eisenman et al. 2005; Franzen et al. 2008; Romero-Martinez et al. 2000) or clustered on the cell wall surface (Walker et al. 2010; Romero-Martinez et al. 2000; Bayry et al. 2014). In *Cryptococcus* species and *Candida albicans* cell-wall chitin or its deacetylated form, chitosan, plays a key role in the melanin accumulation and distribution within the cell wall (Chrissian et al. 2020a; Camacho et al. 2017; Walker et al. 2010). Disruption of the chitin synthesis in *C. neoformans* (Tsirilakis et al. 2012) results in a leaky-melanin phenotype where melanin is not retained within the cell wall and is released to the extracellular medium. A similar leaky phenotype is also observed upon binding of cell wall dyes that interfere with melanin deposition (Perez-Dulzaides et al. 2018). Aliphatic groups identified as triglycerides (TGs) within fungal melanins are associated with their synthesis within vesicles (Eisenman et al. 2009; Zhong et al. 2008; Rodrigues et al. 2007) and cell-wall remodeling processes during budding (Nosanchuk and Casadevall 2003a). More recently, ss-NMR studies determined that melanized cells of *C. neoformans* were not only associated with TGs but also with sterol esters (SE) and polyisoprenoids. These lipids were also found in non-melanized cells but given that TGs and SEs are the typical cargo of lipid droplets, it may be possible that these organelles are involved in *C. neoformans* melanin synthesis (Chrissian et al. 2020c).

2.2 Secreted Melanin

During fungal growth and cell replication, melanized fungal cells have to remodel their cell wall during budding and morphological transitions such as making hyphae. To allow cellular budding, the local cell-wall remodeling might be driven by

secreted enzymes (peptidase, chitinases, and glucanases) (Geddes et al. 2015) that break melanin linkages to cell-wall components. In *C. neoformans*, using isopycnic gradient sedimentation, detached and secreted melanin granules in the culture supernatant were isolated and analyzed for proteins (Camacho et al. 2019). This study identified four proteins (Qsp1, Cig1, Blp1, and CNAG_05313) that may play important roles in the fungal melanogenesis and adaptation/survival of the fungus inside the host.

3 Role of Fungal Melanin in Human Disease

While mammalian endothermy, among other factors such as advanced immunity, protects against many fungal species, some species have evolved to be pathogenic in humans (Köhler, Hube, et al.). A concern particularly in those who are immunocompromised, the continued evolution of fungal virulence represents a growing threat to global health. While many fungal infections are superficial and mild, some may evolve into severe diseases, especially in the aforementioned immunocompromised hosts. For example, while *Candida albicans* is commonly a harmless colonizer of human mucous membranes, it can lead to fatal systemic candidemia in those with neutropenia. Meanwhile, infections with *Cryptococcus neoformans* or *C. gattii* can cause disseminated cryptococcosis in both healthy and immunocompromised adults, often leading to subacute meningoencephalitis (Köhler, Casadevall, et al.). To be pathogenic in humans, these fungi must evolve to be able to withstand the human febrile temperatures of 38–39 °C and resist the efforts of the immune system targeting fungal cells. Notably, melanin produced by the pathogens *Cryptococcus neoformans* and *Monilinia fructicola* has been shown to confer thermotolerance, representing a potential role for fungal melanin in this evasion of mammalian endothermy (Cordero and Casadevall), especially when exogenous melanization substrates are available in the extracellular environment, such as in infection of the substantia nigra. Further work is needed to better elucidate the contributions of melanin's conferral of thermotolerance to the development of fungal pathogenesis; however, other roles for melanin in fungal virulence are well described.

3.1 Cell-Host Interaction

Among the innate immune receptors, host pattern recognition receptors (PRRs) can be divided into two groups: secreted receptors and transmembrane signal-transducing receptors (Mortaz et al. 2017; Brubaker et al. 2015; Latgé 2020). Pathogen-associated molecular patterns (PAMPs) are highly conserved molecular structures found in some pathogenic microorganisms and are known to be critical in

initiating innate immune responses and inducing and directing subsequent adaptive immunity (Latgé 2020; Kurup and Tarleton 2013).

Most host cells express at least one type of cellular PRRs. PRRs can be divided into five different types: Toll-like receptors (TLRs), nucleotide oligomerization domain (NOD)-like receptors (NLRs), retinoic acid-inducible gene-I (RIG-I)-like receptors (RLRs), C-type lectin receptors (CLRs), and absent in melanoma-2 (AIM2)-like receptors (ALRs). Among them, TLRs and CLRs have been extensively studied in the context of fungal infection and also play central roles in antifungal immunity (Mortaz et al. 2017; Brubaker et al. 2015).

Several immunologically fungal ligands have been described as PRRs, including melanin 2,3. A C-type lectin receptor, called Melanin sensing C-type Lectin receptor (MelLec/CLEC1A), was shown to play an essential role in antifungal immunity through recognition of the naphthalene-diol unit of 1,8- dihydroxynaphthalene (DHN)-melanin. However, MelLec is not able to bind to DOPA-melanin, produced by other fungal pathogens, including *Cryptococcus* sp. (Smith and Casadevall 2019; Stappers et al. 2018). In humans, this receptor is expressed by endothelial cells and leukocytes, including monocytes, dendritic cells, and granulocytes, but not by lymphocytes (Sattler et al. 2012). In aspergillosis experimental infection, MelLec was required for early leukocyte recruitment in the lungs (Stappers et al. 2018). In summary, MelLec is a receptor recognizing an immunologically active component commonly found in fungi and plays an essential role in protective antifungal immunity in both mice and humans, showing the importance of fungal melanin as PAMPs and how it can be sensed and recognized by immune host cells, activating the development of the appropriate immune response (Stappers et al. 2018).

3.2 Mechanisms of Resistance to Human Host Immune Factors

3.2.1 Oxidative Stress

Two key features, namely a negative charge and a stable free radical population, are shared among the characteristics of melanins produced by fungi (Smith and Casadevall 2019). These properties confer upon fungal melanins the ability to reduce oxidizing free radicals, highly reactive molecular species with one or more unpaired electrons (Lobo et al. 2010). In the context of fungal infections, free radicals produced by host immune cells during oxidative bursts can be absorbed and neutralized by melanin in the fungal cell wall before they can enter the cell and elicit cytotoxic damage (Nosanchuk and Casadevall 2003b). For example, DOPA-derived eumelanin produced by *Cryptococcus neoformans* imparts a survival advantage to cells treated with oxidative reactants *in vitro* (Jacobson and Tinnell 1993; Wang and Casadevall 1994a) or during phagocytosis by macrophages (Wang et al. 1995). Enhanced survival of melanized cryptococcal cells inside macrophages is expected to contribute to virulence by promoting dissemination from the lungs to the brain

through a Trojan horse mechanism (Liu et al. 2012) and a recent study reporting a survival advantage for melanized compared to non-melanized *C. neoformans* cells in a mouse model of cryptococcal infection supports this hypothesis (Baker and Casadevall 2023). Other forms of melanin have been shown to protect fungal species from the types of free radicals released by host macrophages during phagocytosis, including DHN-melanin in *Sporothrix schenckii* and *Fonsecaea pedrosoi* (Romero-Martinez et al. 2000; Cunha et al. 2010) and both DHN and pyomelanin in *Aspergillus fumigatus* (Schmaler-Ripcke et al. 2009; Jahn et al. 1997). Thus, melanization is a widespread adaptation that permits prolonged survival of infective fungal cells within host phagolysosomes thereby increasing their propensity to cause disease.

3.2.2 Melanin Interference with Antifungal Drug Activity

Melanin also contributes to fungal virulence through the sequestration of antifungal drugs. Melanization of *C. neoformans* and *H. capsulatum* reduces the potency of the polyene amphotericin B and the echinocandin caspofungin (van Duin et al. 2002). These compounds have also been observed to change the elemental composition of fungal melanin after incubation *in vitro*, suggesting a mechanism of direct binding and sequestration (Nosanchuk and Casadevall 2006). Melanized *P. brasiliensis* cells have also demonstrated reduced susceptibility to amphotericin B, and, in contrast to that observed in *C. neoformans*, also manifested reduced susceptibility to azoles like fluconazole, ketoconazole, itraconazole, and sulfamethoxazole (Gómez et al. 2001). Notably, the direct sequestration of azole drugs by melanin has yet to be demonstrated. However, fungal melanins have been shown to bind to a variety of drug types beyond just the antifungals, with binding efficacies approaching other known absorbers like medicinal activated charcoal (Bridelli et al. 2006).

Further, treatment with the DHN-melanin synthesis inhibitor tricyclazole increased the potency of terbinafine in *Sporothrix brasiliensis* and *Sporothrix schenckii* species (Almeida-Paes et al. 2016). And, interestingly, antifungal drug treatment has also been shown to increase rates of DHN-melanin synthesis in *A. infectoria*, affecting the compound's deposition in the cell wall (Fernandes et al. 2015). Electron micrographs of melanized *C. neoformans* cells have demonstrated melanin deposition in the cell wall, providing support for extracellular drug capture by melanins (Eisenman et al. 2005). Melanization makes the cell wall less porous to amphotericin-containing liposomes suggesting another mechanism by which this pigment can reduce fungal susceptibility to this antifungal drug (Walker et al. 2018). Taken together, the role of melanin in antifungal drug resistance and uptake has been robustly established.

3.2.3 Immune Evasion

The extracellular localization of fungal melanin also contributes to its role in the evasion of host immunosurveillance. Melanin in *Aspergillus fumigatus* has been

shown to mask pathogen-associated molecular patterns (PAMPs) like mannans and β -glucan from the immune recognition, significantly attenuating the observed cytokine response (Liu et al. 2021). Likewise, melanin from *A. nidulans* was shown to have an anti-inflammatory effect, decreasing the production of nitric oxide and TNF- α in stimulated macrophages (Gonçalves et al. 2013). In *C. neoformans*, phagocytosis of melanized cells was observed to be lessened compared to those unable to form melanin (Mednick et al. 2005). In addition, Rosas et al. showed that the injection of *C. neoformans* melanin isolated particles could induce granuloma formation in mice; interestingly, the granulomas and the latent infection commonly associated with them are observed in pathogens capable of melanization (Nosanchuk and Casadevall 2006; Rosas et al. 2002). In addition to the protection conferred by its immunomodulatory and ROS scavenging roles, melanin has also been shown to be protective against enzymatic degradation and secreted antimicrobial peptides like defensins, likely due to its negative charge and promiscuous binding affinity (Rosas and Casadevall 2001). Broadly, melanin knockout has been shown to decrease fungal virulence (McClelland et al. 2006), underscoring its importance in fungal pathogenesis and human disease.

4 Interactions Between Fungal Melanins and Insect Hosts

Insect hosts provide an interesting context for melanized fungi. Insects, like most arthropods, produce their own melanin as an important part of their immune response to microbes, including fungi (González-Santoyo and Córdoba-Aguilar 2012). Insect immune melanization is produced by the oxidation of catecholamines in the hemolymph by activated phenoloxidases, resulting in the formation of DOPA melanins. The melanization reaction is believed to kill the microbes through the oxidative and toxic intermediates produced by the melanization reaction (Zhao et al. 2011). The interactions between fungal melanins and insect melanins have not been extensively studied, but current evidence in the literature indicates that fungal melanins are not advantageous for fungal survival and limit infection within insects. In contrast to mammalian and plant fungal pathogens, many entomopathogenic fungi—or fungi that infect insects—do not produce melanin pigment, including *Metarhizium anisopliae* and *Beauveria bassiana* (Lu et al. 2021; Fang et al. 2010). Since insect melanins are used for immunity and wound healing, fungal melanins may act as damage-associated molecular patterns (DAMPs), which in turn would activate more immune and wound-healing responses as seen in *in vitro* studies investigating melanization of insect hemolymph (Smith et al. 2022).

During infections of *Galleria mellonella* wax moth larvae, pigmentation mutants of *Aspergillus fumigatus* are more virulent than their wild-type melanized counterparts (Jackson et al. 2009). Conversely, melanin-deficient *A. fumigatus* mutants (*alb1 Δ*) were less virulent during oral and topical infection of *Drosophila melanogaster* fruit flies deficient in *Toll*, an immune gene responsible for recognizing microbes (Lionakis et al. 2005). While these findings appear contradictory, if the

fungal melanin activates an effective immune response via *Toll* signaling, then the *Toll*-deficient *D. melanogaster* mutants would not reveal an enhanced virulence phenotype of albino fungal mutants. Non-melanin-producing mutants of *Fonseca monophora* are more virulent than the melanized counterparts in *G. mellonella* larvae (Liu et al. 2019). Lastly, cultures from wildtype non-melanized *Cryptococcus neoformans* are also more virulent than the wildtype melanized cultures in *G. mellonella* (Eisenman et al. 2014). The melanized cells induced larger inflammatory nodules, indicating that melanin can activate inflammation and immune reactions in the larvae (Eisenman et al. 2014). These nodules are often sites of the insect's immune melanization reaction and are key in controlling infection (Dubovskiy et al. 2016). Additional evidence shows that the melanin-producing enzyme laccase from *C. neoformans* can activate the insect's melanization response (Smith et al. 2022), although the laccase-null *lac1Δ* mutant is hypovirulent in *G. mellonella* infections, possibly due to other non-fungal melanin related roles (Lu et al. 2021; Mylonakis et al. 2005). On the other hand, a strain of the entomopathogenic fungus *M. anisopliae* that was genetically modified to produce melanin resulted in mutants that had enhanced virulence and enhanced stress tolerance overall in a wide variety of insect pests (Tseng et al. 2011, 2014).

In studies investigating the correlation between virulence factors, fungal properties, and survival of insect hosts, the role of fungal melanin is less clear. Survival of *D. melanogaster* positively correlated to the degree of melanization of *Cryptococcus spp.* isolates, indicating that degree of fungal melanization is maladaptive in the case of infections of insect hosts (Thompson et al. 2014), while fungal melanization from *Cryptococcus gattii* isolates was correlated with increased virulence in *G. mellonella* (Firacative et al. 2014). These studies only provide correlations between virulence and melanization, which may be influenced by many other virulence factors and conditions, including capsule size and fungal growth rate. Additional experiments studying the nuanced and mechanistic interactions between fungal melanin and the insect immune response need to be done.

5 Role of Fungal Melanin in Plant Infections

The melanin in melanized fungi can also play a surprisingly crucial role beyond human and insect hosts. Black fungal pathogens have a significant impact on agriculture globally. One example is the species *Colletotrichum*. This species predominantly causes anthracnose disease, red rot, crown rot, and brown blotch (Cannon et al. 2012). The fungi are so expansive that it affects: papaya, citrus, strawberry, tomato, corn, alfalfa, pepper, legumes, radish, coffee, and sorghum plants to name a few (Dean et al. 2012). The melanin in melanized fungi can also play a surprisingly crucial role beyond human and insect hosts. More specifically, melanized fungi use melanin to create and maintain high turgor pressures in the appressorium while inserting themselves into the plant hosts, absorbing essential

minerals which function as a reservoir for the fungi, and preventing loss of glucose (Nosanchuk and Casadevall 2003b; Butler et al. 2001).

The melanin produced by fungal plant pathogens plays a significant role in the colonization of the plant host. To colonize a plant host, fungi produce appressoria, or tiny hyphal cell formations containing glycerol, which help create enough turgor pressure to penetrate the epidermal cells of plants. Specifically, melanized appressoria are comparatively advantageous to non-melanized appressoria in terms of generating and maintaining sufficient turgor pressure to invade the plant (de Jong et al. 1997). Melanized fungi more effectively prevent diffusion of glycerol which retains a higher turgor pressure necessary for the degradation of the cuticle (de Jong et al. 1997). A notable example of this phenomenon is the fungus *Magnaporthe grisea* which utilizes melanin to invade rice plants and result in rice blast disease (Howard and Valent 1996). When the same *M. grisea* is treated with a tricyclazole, a reagent that prevents the synthesis of melanin, or an albino mutant of *M. grisea* is used, the appressoria are unable to generate sufficient turgor pressure (Howard and Valent 1996).

The role of melanin in melanized fungi is not limited to just host-invasion processes; it can also play a defensive role. Melanin can aid the survival of melanized fungi even while in a dormant state (Butler et al. 2001). Fungi which produce melanized sclerotia, a bundle of hyphae, are far more resistant to chemical attacks (Butler et al. 2001); this is incredibly important for resistance against fungicides as well. For fungi that do not produce sclerotia, melanin still plays a role in protecting the fungi (Butler et al. 2001). This is evident, for example, in mutant versions of fungi *G. Graminis* which are more susceptible to ultraviolet radiation, lytic enzymes, and some antimicrobial agents (Frederick et al. 1999).

Melanotic fungi pose clear offensive and defensive advantages over their non-melanized counterparts. More specifically, melanized fungi are more effectively able to invade plants, maintain nutrients, and protect themselves against an array of chemical, radioactive, and other physical threats.

6 Fungal Melanin as a Target for Antimicrobial Therapies

Fungal melanin is of particular consideration in the development of antimicrobial therapies due to its roles both in fungal virulence and antimicrobial resistance. Melanized fungi can exhibit decreased susceptibility and enhanced resistance to antifungal medications. For example, while amphotericin B (AmB) is often effective against non-melanized *C. neoformans* in vitro (Wang and Casadevall 1994b), it likely acts by causing an increase in ROS (Sangalli-Leite et al. 2011). Due to melanin's antioxidant properties, *C. neoformans* grown with L-Dopa exhibited significantly enhanced survival against AmB at concentrations up to 0.3 µg/ml (Wang and Casadevall 1994b). In vivo melanization of *C. neoformans* may hinder amphotericin B's fungicidal action in clinical settings (Nosanchuk and Casadevall 2006).

Past research has suggested that inhibition of melanization can be an effective infection control strategy. When Alviano et al. collected sera from patients with chromoblastomycosis, purified melanin-binding antibodies were shown to opsonize melanotic *Fonsecaea pedrosoi* conidia in vitro. In addition, treating mice with monoclonal antibodies (mAbs) to melanin significantly improved survival against *C. neoformans* infection (Rosas et al. 2001). In addition, mice administered mAbs experienced significantly less *Cryptococcal* growth both in the lungs and the brain (Rosas et al. 2001).

Glyphosate, a glycine analog, and a component of the herbicide Roundup interfere with the shikimate pathway, which is used by many organisms for the synthesis of aromatic amino acids. Because melanin is synthesized from phenolic compounds, glyphosate can also interfere with melanin synthesis in fungal pathogens such as *C. neoformans*. Nosanchuk et al. demonstrated that mice infected with *C. neoformans* and administered glyphosate displayed prolonged survival and decreased *C. neoformans* melanization (Nosanchuk et al. 2001). On the other hand, in organisms that rely on melanin production for the immune defense such as insects (See Sect. 4), glyphosate increases host susceptibility to microbial infection (Smith et al. 2021). In total, the body of existing research points to a need for further studies into the use of inhibiting melanin synthesis and/or activity for antimicrobial purposes.

7 Concluding Remarks

Melanin is a multifunctional polymer that has varied roles in fungal pathogenesis ranging from interfering with the immune system in animals to promoting turgor pressure for plant-invasive fungi to protecting fungal cells from antifungal drugs. Melanin functions in virulence stand apart from the other mechanisms by which this pigment promotes fungal survival in the environment (Cordero and Casadevall 2017) such as conferring protection against amoeba predators (Steenbergen et al. 2001), ultraviolet light (Wang and Casadevall 1994c) and cellular mechanical strength (Mattoon et al. 2023) and promoting the capture of electromagnetic energy for growth (Dadachova et al. 2007) and thermal regulation (Cordero et al. 2018). Interference with melanization is a potential therapeutic strategy that is currently unexploited in drug development. Despite all we know about this enigmatic polymer there are major unresolved problems in the biology of melanin ranging from uncertainty in its structure to the mechanisms by which it is assembled in the cell wall and rearranged during budding and cellular morphological transitions. The study of melanization and its effects on virulence are exciting and productive frontiers in fungal pathogenesis.

References

- Almeida-Paes R, Frases S, GDS A, de Oliveira MME, Gerfen GJ, Nosanchuk JD et al (2012) Biosynthesis and functions of a melanoid pigment produced by species of the sporothrix complex in the presence of L-tyrosine. *Appl Environ Microbiol* 78(24):8623–8630
- Almeida-Paes R, Figueiredo-Carvalho MHG, Brito-Santos F, Almeida-Silva F, Oliveira MME, Zancopé-Oliveira RM (2016) Melanins protect *Sporothrix brasiliensis* and *Sporothrix schenckii* from the antifungal effects of terbinafine. *PLoS One* 11(3):e0152796
- Almeida-Paes R, Borba-Santos LP, Rozental S, Marco S, Zancopé-Oliveira RM, da Cunha MML (2017) Melanin biosynthesis in pathogenic species of *Sporothrix*. *Fungal Biol Rev* 31(1):50–59
- Almeida-Paes R, Almeida-Silva F, Pinto GCM, MDA A, MDM M, Pizzini CV et al (2018) L-tyrosine induces the production of a pyomelanin-like pigment by the parasitic yeast-form of *Histoplasma capsulatum*. *Med Mycol* 56(4):506–509
- Almeida-Paes R, Almeida MA, Baeza LC, Marmello LAM, Trugilho MRDO, Nosanchuk JD et al (2020) Beyond melanin: proteomics reveals virulence-related proteins in *paracoccidioidesbrasiliensis* and *paracoccidioideslutzii* yeast cells grown in the presence of L-dihydroxyphenylalanine. *J Fungi (Basel)* 6(4)
- Alviano CS, Farbiarz SR, De Souza W, Angluster J, Travassos LR (1991) Characterization of *Fonsecaea pedrosoi* melanin. *J Gen Microbiol* 137(4):837–844
- Baker RP, Chrissian C, Stark RE, Casadevall A (2021) *Cryptococcus neoformans* melanization incorporates multiple catecholamines to produce polytypic melanin. *J Biol Chem*:101519
- Baker RP, Casadevall A (2023) Reciprocal modulation of ammonia and melanin production has implications for cryptococcal virulence. *Nat Commun* 14(1):849
- Bayry J, Beaussart A, Dufrêne YF, Sharma M, Bansal K, Knemeyer O et al (2014) Surface structure characterization of *Aspergillus fumigatus* conidia mutated in the melanin synthesis pathway and their human cellular immune response. *Infect Immun* 82(8):3141–3153
- Boyce KJ, McLauchlan A, Schreider L, Andrianopoulos A (2015) Intracellular growth is dependent on tyrosine catabolism in the dimorphic fungal pathogen *Penicillium marneffei*. *PLoS Pathog* 11(3):e1004790
- Bridelli MG, Ciati A, Crippa PR (2006) Binding of chemicals to melanins re-examined: adsorption of some drugs to the surface of melanin particles. *Biophys Chem* 119(2):137–145
- Britton G (1983) The biochemistry of natural pigments. Cambridge University Press, Cambridge
- Brubaker SW, Bonham KS, Zanon I, Kagan JC (2015) Innate immune pattern recognition: a cell biological perspective. *Annu Rev Immunol* (33):257–290
- Büngeler A, Hämisch B, Strube OI (2017) The supramolecular buildup of eumelanin: structures, mechanisms, controllability. *Int J Mol Sci* 18(9)
- Butler MJ, Day AW, Henson JM, Money NP (2001) Pathogenic properties of fungal melanins. *Mycologia* 93(1):1
- Camacho E, Chrissian C, Cordero RJB, Liporagi-Lopes L, Stark RE, Casadevall A (2017) N-acetylglucosamine affects *Cryptococcus neoformans* cell-wall composition and melanin architecture. *Microbiology (Reading, Engl)* 163(11):1540–1556
- Camacho E, Vij R, Chrissian C, Prados-Rosales R, Gil D, O'Meally RN et al (2019) The structural unit of melanin in the cell wall of the fungal pathogen *Cryptococcus neoformans*. *J Biol Chem* 294(27):10471–10489
- Cannon PF, Damm U, Johnston PR, Weir BS (2012) *Colletotrichum* – current status and future directions. *Stud Mycol* 73(1):181–213
- Casadevall A, Nakouzi A, Crippa PR, Eisner M (2012) Fungal melanins differ in planar stacking distances. *PLoS One* 7(2):e30299
- Chatterjee S, Prados-Rosales R, Frases S, Itin B, Casadevall A, Stark RE (2012) Using solid-state NMR to monitor the molecular consequences of *Cryptococcus neoformans* melanization with different catecholamine precursors. *Biochemistry* 51(31):6080–6088

- Chatterjee S, Prados-Rosales R, Tan S, Itin B, Casadevall A, Stark RE (2014) Demonstration of a common indole-based aromatic core in natural and synthetic eumelanins by solid-state NMR. *Org Biomol Chem* 12(34):6730–6736
- Chatterjee S, Prados-Rosales R, Itin B, Casadevall A, Stark RE (2015) Solid-state NMR reveals the carbon-based molecular architecture of *Cryptococcus neoformans* fungal eumelanins in the cell wall. *J Biol Chem* 290(22):13779–13790
- Chrissian C, Camacho E, Fu MS, Prados-Rosales R, Chatterjee S, Cordero RJB et al (2020a) Melanin deposition in two *Cryptococcus* species depends on cell-wall composition and flexibility. *J Biol Chem* 295(7):1815–1828
- Chrissian C, Lin CP-C, Camacho E, Casadevall A, Neiman AM, Stark RE (2020b) Unconventional constituents and shared molecular architecture of the melanized cell wall of *C. neoformans* and spore wall of *S. cerevisiae*. *J Fungi (Basel)* 6(4)
- Chrissian C, Camacho E, Kelly JE, Wang H, Casadevall A, Stark RE (2020c) Solid-state NMR spectroscopy identifies three classes of lipids in *C. neoformans* melanized cell walls and whole fungal cells. *BioRxiv*
- Cordero RJB, Casadevall A (2017) Functions of fungal melanin beyond virulence. *Fungal Biol Rev* 31(2):99–112
- Cordero RJB, Robert V, Cardinali G, Arinze ES, Thon SM, Casadevall A (2018) Impact of yeast pigmentation on heat capture and latitudinal distribution. *Curr Biol* 28(16):2657–2664.e3
- Cunha MML, Franzen AJ, Seabra SH, Herbst MH, Vugman NV, Borba LP et al (2010) Melanin in *Fonsecaea pedrosoi*: a trap for oxidative radicals. *BMC Microbiol* (10):80
- Dadachova E, Bryan RA, Huang X, Moadel T, Schweitzer AD, Aisen P, Nosanchuk JD, Casadevall A (2007) Ionizing radiation changes the electronic properties of melanin and enhances the growth of melanized fungi. *PLoS One* 2(5):e4573
- de Jong JC, McCormack BJ, Smirnoff N, Talbot NJ (1997) Glycerol generates turgor in rice blast. *Nature* 389(6648):244–244
- Dean R, Van Kan JAL, Pretorius ZA, Hammond-Kosack KE, Di Pietro A, Spanu PD et al (2012) The top 10 fungal pathogens in molecular plant pathology. *Mol Plant Pathol* 13(4):414–430
- Dubovskiy IM, Kryukova NA, Glupov VV, Ratcliffe NA (2016) Encapsulation and nodulation in insects. *Invertebr Surviv J*
- Eisenman HC, Casadevall A (2012) Synthesis and assembly of fungal melanin. *Appl Microbiol Biotechnol* 93(3):931–940
- Eisenman HC, Nosanchuk JD, Webber JBW, Emerson RJ, Camesano TA, Casadevall A (2005) Microstructure of cell wall-associated melanin in the human pathogenic fungus *Cryptococcus neoformans*. *Biochemistry* 44(10):3683–3693
- Eisenman HC, Mues M, Weber SE, Frases S, Chaskes S, Gerfen G et al (2007) *Cryptococcus neoformans* laccase catalyses melanin synthesis from both D- and L-DOPA. *Microbiology (Reading, Engl)* 153(Pt 12):3954–3962
- Eisenman HC, Frases S, Nicola AM, Rodrigues ML, Casadevall A (2009) Vesicle-associated melanization in *Cryptococcus neoformans*. *Microbiology (Reading, Engl)* 155(Pt 12):3860–3867
- Eisenman HC, Duong R, Chan H, Tsue R, McClelland EE (2014) Reduced virulence of melanized *Cryptococcus neoformans* in *Galleria mellonella*. *Virulence* 5(5):611–618
- Fang W, Fernandes EKK, Roberts DW, Bidochka MJ, St Leger RJ (2010) A laccase exclusively expressed by *Metarhizium anisopliae* during isotropic growth is involved in pigmentation, tolerance to abiotic stresses and virulence. *Fungal Genet Biol* 47(7):602–607
- Fernandes C, Prados-Rosales R, Silva B, Nakouzi-Naranjo A, Zuzarte M, Chatterjee S et al (2015) Activation of melanin synthesis in *Alternaria infectoria* by antifungal drugs. *Antimicrob Agents Chemother* 60(3):1646–1655
- Fernandes C, Mota M, Barros L, Dias MI, Ferreira ICFR, Piedade AP et al (2021) Pyomelanin synthesis in *Alternaria alternata* inhibits DHN-melanin synthesis and decreases cell wall chitin content and thickness. *Front Microbiol* 12:691433

- Firacative C, Duan S, Meyer W (2014) *Galleria mellonella* model identifies highly virulent strains among all major molecular types of *Cryptococcus gattii*. *PLoS One* 9(8):e105076
- Frandsen RJN, Rasmussen SA, Knudsen PB, Uhlig S, Petersen D, Lysøe E et al (2016) Black perithecial pigmentation in *Fusarium* species is due to the accumulation of 5-deoxybostrycoidin-based melanin. *Sci Rep* 6(1):26206
- Franzen AJ, Cunha MML, Batista EJO, Seabra SH, De Souza W, Rozental S (2006) Effects of tricyclazole (5-methyl-1,2,4-triazol[3,4] benzothiazole), a specific DHN-melanin inhibitor, on the morphology of *Fonsecaea pedrosoi* conidia and sclerotic cells. *Microsc Res Tech* 69(9): 729–737
- Franzen AJ, Cunha MML, Miranda K, Hentschel J, Plattner H, da Silva MB et al (2008) Ultra-structural characterization of melanosomes of the human pathogenic fungus *Fonsecaea pedrosoi*. *J Struct Biol* 162(1):75–84
- Frederick BA, Caesar-Tonthat TC, Wheeler MH, Sheehan KB, Edens WA, Henson JM (1999) Isolation and characterisation of *Gaeumannomyces graminis* var. *graminis* melanin mutants. *Mycol Res* 103(1):99–110
- Freitas DF, Vieira-Da-Motta O, Mathias LDS, Franco RWDA, Gomes RDS, Vieira RAM et al (2019) Synthesis and role of melanin for tolerating in vitro rumen digestion in *Duddingtonia flagrans*, a nematode-trapping fungus. *Mycology* 10(4):229–242
- Geddes JMH, Croll D, Caza M, Stoykov N, Foster LJ, Kronstad JW (2015) Secretome profiling of *Cryptococcus neoformans* reveals regulation of a subset of virulence-associated proteins and potential biomarkers by protein kinase A. *BMC Microbiol* (15):206
- Geib E, Gressler M, Viedernikova I, Hillmann F, Jacobsen ID, Nietzsche S et al (2016) A non-canonical melanin biosynthesis pathway protects *Aspergillus terreus* conidia from environmental stress. *Cell Chem Biol* 23(5):587–597
- Gómez BL, Nosanchuk JD, Díez S, Youngchim S, Aisen P, Cano LE et al (2001) Detection of melanin-like pigments in the dimorphic fungal pathogen *Paracoccidioides brasiliensis* in vitro and during infection. *Infect Immun* 69(9):5760–5767
- González-Santoyo I, Córdoba-Aguilar A (2012) Phenoloxidase: a key component of the insect immune system. *Entomol Exp Appl* 142(1):1–16
- Gow NAR, Latgé J-P, Munro CA (2017) The fungal cell wall: structure, biosynthesis, and function. *Microbiol Spectr* 5(3)
- Hong S, Wang Y, Park SY, Lee H (2018) Progressive fuzzy cation- π assembly of biological catecholamines. *Sci Adv* 4(9):eaat7457
- Howard RJ, Valent B (1996) Breaking and entering: host penetration by the fungal rice blast pathogen *Magnaporthe grisea*. *Annu Rev Microbiol* 50:491–512
- Hwang L, Hocking-Murray D, Bahrami AK, Andersson M, Rine J, Sil A (2003) Identifying phase-specific genes in the fungal pathogen *Histoplasma capsulatum* using a genomic shotgun microarray. *Mol Biol Cell* 14(6):2314–2326
- Jackson JC, Higgins LA, Lin X (2009) Conidiation color mutants of *Aspergillus fumigatus* are highly pathogenic to the heterologous insect host *Galleria mellonella*. *PLoS One* 4(1):e4224
- Jacobson ES, Tinnell SB (1993) Antioxidant function of fungal melanin. *J Bacteriol* 175(21): 7102–7104
- Jahn B, Koch A, Schmidt A, Wanner G, Gehringer H, Bhakdi S et al (1997) Isolation and characterization of a pigmentless-conidium mutant of *Aspergillus fumigatus* with altered conidial surface and reduced virulence. *Infect Immun* 65(12):5110–5117
- Kurup SP, Tarleton RL (2013) Perpetual expression of PAMPs necessary for optimal immune control and clearance of a persistent pathogen. *Nat Commun* (4):2616
- La Du BN, Zannoni VG, Laster L, Seegmiller JE (1958) The nature of the defect in tyrosine metabolism in alcaptonuria. *J Biol Chem* 230(1):251–260
- Latgé J-P (ed) (2020) The fungal cell wall: an armour and a weapon for human fungal pathogens. Springer, Cham

- Lionakis MS, Lewis RE, May GS, Wiederhold NP, Albert ND, Halder G et al (2005) Toll-deficient *Drosophila* flies as a fast, high-throughput model for the study of antifungal drug efficacy against invasive aspergillosis and *Aspergillus* virulence. *J Infect Dis* 191(7):1188–1195
- Liu T-B, Perlin DS, Xue C (2012) Molecular mechanisms of cryptococcal meningitis. *Virulence* 3(2):173–181
- Liu Y, Huang X, Liu H, Xi L, Cooper CR (2019) Increased virulence of albino mutant of *Fonsecaea monophora* in *Galleria mellonella*. *Med Mycol* 57(8):1018–1023
- Liu S, Youngchim S, Zamith-Miranda D, Nosanchuk JD (2021) Fungal melanin and the mammalian immune system. *J Fungi (Basel)* 7(4)
- Lobo V, Patil A, Phatak A, Chandra N (2010) Free radicals, antioxidants and functional foods: impact on human health. *Pharmacogn Rev* 4(8):118–126
- Lorquin F, Piccerelle P, Orneto C, Robin M, Lorquin J (2022) New insights and advances on pyromelanin production: from microbial synthesis to applications. *J Ind Microbiol Biotechnol*
- Lu Z, Deng J, Wang H, Zhao X, Luo Z, Yu C et al (2021) Multifunctional role of a fungal pathogen-secreted laccase 2 in evasion of insect immune defense. *Environ Microbiol* 23(2):1256–1274
- Mattoon ER, Cordero RJB, Casadevall A (2023) Melanization reduces *Cryptococcus neoformans* susceptibility to mechanical stress. *mSphere* 8(1):e0059122
- McClelland EE, Bernhardt P, Casadevall A (2006) Estimating the relative contributions of virulence factors for pathogenic microbes. *Infect Immun* 74(3):1500–1504
- Mednick AJ, Nosanchuk JD, Casadevall A (2005) Melanization of *Cryptococcus neoformans* affects lung inflammatory responses during cryptococcal infection. *Infect Immun* 73(4):2012–2019
- Mortaz E, Adcock IM, Tabarsi P, Darazam IA, Movassaghi M, Garssen J et al (2017) Pattern recognition receptors in immunodeficiency disorders. *Eur J Pharmacol*
- Mylonakis E, Moreno R, El Khoury JB, Idnurm A, Heitman J, Calderwood SB et al (2005) *Galleria mellonella* as a model system to study *Cryptococcus neoformans* pathogenesis. *Infect Immun* 73(7):3842–3850
- Nosanchuk JD, Casadevall A (2003a) Budding of melanized *Cryptococcus neoformans* in the presence or absence of L-dopa. *Microbiology (Reading, Engl)* 149(7)
- Nosanchuk JD, Casadevall A (2003b) The contribution of melanin to microbial pathogenesis. *Cell Microbiol* 5(4):203–223
- Nosanchuk JD, Casadevall A (2006) Impact of melanin on microbial virulence and clinical resistance to antimicrobial compounds. *Antimicrob Agents Chemother* 50(11):3519–3528
- Nosanchuk JD, Ovalle R, Casadevall A (2001) Glyphosate inhibits melanization of *Cryptococcus neoformans* and prolongs survival of mice after systemic infection. *J Infect Dis* 183(7):1093–1099
- Nunes LR, Costa de Oliveira R, Leite DB, da Silva VS, dos Reis ME, da Silva Ferreira ME et al (2005) Transcriptome analysis of *Paracoccidioides brasiliensis* cells undergoing mycelium-to-yeast transition. *Eukaryot Cell* 4(12):2115–2128
- Perez-Dulzaides R, Camacho E, Cordero RJB, Casadevall A (2018) Cell-wall dyes interfere with *Cryptococcus neoformans* melanin deposition. *Microbiology* 164(8):1012–1022
- Prota G (1988) Progress in the chemistry of melanins and related metabolites. *Med Res Rev* 8(4):525–556
- RDCR G, Kitagawa RR, MSG R, Carlos IZ, Pombeiro-Sponchiado SR (2013) Inhibition of nitric oxide and tumour necrosis factor- α production in peritoneal macrophages by *Aspergillus nidulans* melanin. *Biol Pharm Bull* 36(12):1915–1920
- Rodrigues ML, Nimrichter L, Oliveira DL, Frases S, Miranda K, Zaragoza O et al (2007) Vesicular polysaccharide export in *Cryptococcus neoformans* is a eukaryotic solution to the problem of fungal trans-cell wall transport. *Eukaryot Cell* 6(1):48–59
- Romero-Martinez R, Wheeler M, Guerrero-Plata A, Rico G, Torres-Guerrero H (2000) Biosynthesis and functions of melanin in *Sporothrix schenckii*. *Infect Immun* 68(6):3696–3703
- Rosas AL, Casadevall A (2001) Melanization decreases the susceptibility of *Cryptococcus neoformans* to enzymatic degradation. *Mycopathologia* 151(2):53–56

- Rosas AL, Nosanchuk JD, Casadevall A (2001) Passive immunization with melanin-binding monoclonal antibodies prolongs survival of mice with lethal *Cryptococcus neoformans* infection. *Infect Immun* 69(5):3410–3412
- Rosas AL, MacGill RS, Nosanchuk JD, Kozel TR, Casadevall A (2002) Activation of the alternative complement pathway by fungal melanins. *Clin Diagn Lab Immunol* 9(1):144–148
- San-Blas G, Guanipa O, Moreno B, Pekerar S, San-Blas F (1996) *Cladosporium carrionii* and *Hormoconis resinae* (C. resinae): cell wall and melanin studies. *Curr Microbiol* 32(1):11–16
- Sangalli-Leite F, Scorzoni L, Mesa-Arango AC, Casas C, Herrero E, Gianinni MJSM et al (2011) Amphotericin B mediates killing in *Cryptococcus neoformans* through the induction of a strong oxidative burst. *Microbes Infect* 13(5):457–467
- Sattler S, Reiche D, Sturtzel C, Karas I, Richter S, Kalb ML et al (2012) The human C-type lectin-like receptor CLEC-1 is upregulated by TGF- β and primarily localized in the endoplasmic membrane compartment. *Scand J Immunol* 75(3):282–292
- Schmalzer-Ripcke J, Sugareva V, Gebhardt P, Winkler R, Kniemeyer O, Heinekamp T et al (2009) Production of pyomelanin, a second type of melanin, via the tyrosine degradation pathway in *Aspergillus fumigatus*. *Appl Environ Microbiol* 75(2):493–503
- Singh S, Nimse SB, Mathew DE, Dhimmar A, Sahastrabudhe H, Gajjar A et al (2021) Microbial melanin: recent advances in biosynthesis, extraction, characterization, and applications. *Biotechnol Adv* 53:107773
- Smith DFQ, Casadevall A (2019) The role of melanin in fungal pathogenesis for animal hosts. *Curr Top Microbiol Immunol* 422:1–30
- Smith DFQ, Camacho E, Thakur R, Barron AJ, Dong Y, Dimopoulos G et al (2021) Glyphosate inhibits melanization and increases susceptibility to infection in insects. *PLoS Biol* 19(5): e3001182
- Smith DFQ, Dragotakes Q, Kulkarni M, Hardwick JM, Casadevall A (2022) *Galleria mellonella* immune melanization is fungicidal during infection. *Commun Biol* 5(1):1364
- Stappers MHT, Clark AE, Aimaniananda V, Bidula S, Reid DM, Asamaphan P et al (2018) Recognition of DHN-melanin by a C-type lectin receptor is required for immunity to *Aspergillus*. *Nature* 555(7696):382–386
- Steenbergen JN, Shuman HA, Casadevall A (2001) *Cryptococcus neoformans* interactions with amoebae suggest an explanation for its virulence and intracellular pathogenic strategy in macrophages. *Proc Natl Acad Sci U S A* 98(26):15245–15250
- Tanguay P, Loppnau P, Morin C, Bernier L, Breuil C (2006) A spontaneous albino mutant of *Ceratocystis resinifera* results from a point mutation in the polyketide synthase gene, PKS1. *Can J Microbiol* 52(6):501–507
- Thompson GR, Albert N, Hodge G, Wilson MD, Sykes JE, Bays DJ et al (2014) Phenotypic differences of *Cryptococcus* molecular types and their implications for virulence in a *Drosophila* model of infection. *Infect Immun* 82(7):3058–3065
- Tran-Ly AN, Reyes C, Schwarze FWMR, Ribera J (2020) Microbial production of melanin and its various applications. *World J Microbiol Biotechnol* 36(11):170
- Tsai HF, Wheeler MH, Chang YC, Kwon-Chung KJ (1999) A developmentally regulated gene cluster involved in conidial pigment biosynthesis in *Aspergillus fumigatus*. *J Bacteriol* 181(20): 6469–6477
- Tseng MN, Chung PC, Tzean SS (2011) Enhancing the stress tolerance and virulence of an entomopathogen by metabolic engineering of dihydroxynaphthalene melanin biosynthesis genes. *Appl Environ Microbiol* 77(13):4508–4519
- Tseng M-N, Chung C-L, Tzean S-S (2014) Mechanisms relevant to the enhanced virulence of a dihydroxynaphthalene-melanin metabolically engineered entomopathogen. *PLoS One* 9(3): e90473
- Tsirilakis K, Kim C, Vicencio AG, Andrade C, Casadevall A, Goldman DL (2012) Methylxanthine inhibit fungal chitinases and exhibit antifungal activity. *Mycopathologia* 173(2–3):83–91

- van Duin D, Casadevall A, Nosanchuk JD (2002) Melanization of *Cryptococcus neoformans* and *Histoplasma capsulatum* reduces their susceptibilities to amphotericin B and caspofungin. *Antimicrob Agents Chemother* 46(11):3394–3400
- Walker CA, Gómez BL, Mora-Montes HM, Mackenzie KS, Munro CA, Brown AJP et al (2010) Melanin externalization in *Candida albicans* depends on cell wall chitin structures. *Eukaryot Cell* 9(9):1329–1342
- Walker L, Sood P, Lenardon MD, Milne G, Olson J, Jensen G et al (2018) The viscoelastic properties of the fungal cell wall allow traffic of ambisome as intact liposome vesicles. *MBio* 9(1)
- Wang Y, Casadevall A (1994a) Susceptibility of melanized and nonmelanized *Cryptococcus neoformans* to nitrogen- and oxygen-derived oxidants. *Infect Immun* 62(7):3004–3007
- Wang Y, Casadevall A (1994b) Growth of *Cryptococcus neoformans* in presence of L-dopa decreases its susceptibility to amphotericin B. *Antimicrob Agents Chemother* 38(11):2648–2650
- Wang Y, Casadevall A (1994c) Decreased susceptibility of melanized *Cryptococcus neoformans* to UV light. *Appl Environ Microbiol* 60(10):3864–3866
- Wang Y, Aisen P, Casadevall A (1995) *Cryptococcus neoformans* melanin and virulence: mechanism of action. *Infect Immun* 63(8):3131–3136
- Weijn A, Bastiaan-Net S, Wichers HJ, Mes JJ (2013) Melanin biosynthesis pathway in *Agaricus bisporus* mushrooms. *Fungal Genet Biol* 55:42–53
- Wolf JM, Espadas-Moreno J, Luque-Garcia JL, Casadevall A (2014) Interaction of *Cryptococcus neoformans* extracellular vesicles with the cell wall. *Eukaryot Cell* 13(12):1484–1493
- Xiao M, Chen W, Li W, Zhao J, Hong Y-L, Nishiyama Y et al (2018) Elucidation of the hierarchical structure of natural eumelanins. *J R Soc Interface* 15(140)
- Yabuuchi E, Ohya A (1972) Characterization of “pyomelanin”-producing strains of *Pseudomonas aeruginosa*. *Int J Syst Bacteriol* 22(2):53–64
- Zhao P, Lu Z, Strand MR, Jiang H (2011) Antiviral, anti-parasitic, and cytotoxic effects of 5,6-dihydroxyindole (DHI), a reactive compound generated by phenoloxidase during insect immune response. *Insect Biochem Mol Biol* 41(9):645–652
- Zhong J, Frases S, Wang H, Casadevall A, Stark RE (2008) Following fungal melanin biosynthesis with solid-state NMR: biopolymer molecular structures and possible connections to cell-wall polysaccharides. *Biochemistry* 47(16):4701–4710

Melanosome Origins, Diversity and Functional Relevance Across Animals



Liliana D'Alba

1 Melanosome Origins and Development

Melanins characterize a defense system as well as a resistance mechanism to stress in all organisms. Dopaquinone, a highly reactive o-quinone plays an essential role in melanogenesis, the production of both eumelanin and pheomelanin (Ito and Wakamatsu 2008). While some of the reactions involved in melanogenesis are favorable to the organisms, most of the reactions of o-quinones, for example, those including binding to macromolecules like proteins and DNA, are strongly detrimental, including increases in cytotoxicity and carcinogenesis (Ito et al. 2020). Therefore, melanin production commonly occurs in the confined space of membrane-bound organelles called melanosomes, or it is externalized, forming physical barriers or encrustations on targeted surfaces. For example, bacteria produce diffuse melanin in extracellular spaces (Polacheck and Kwon-Chung 1988); fungi produce melanin granules at the surface of the cell wall (Butler and Day 1998) and deposit these granules in the area close to pathogens or intruding bodies. Invertebrate animals also deposit diffuse melanin pigments on their scales (e.g. Papilionid butterflies; Shawkey et al. 2009), exoskeleton (*Aedes aegypti*; Christensen and Forton 1986) and mantle in hydrobiid snails (Kabat and Hershler 1993). Vertebrates compartmentalize the process of melanin synthesis into melanosomes but these have not been found in insects or most other invertebrates. So, where is melanin produced and how is it localized in invertebrates?

The bulk of melanin production in invertebrates is due to the activity of pro-phenoloxidasases (PPOs) systems that can be combined with a cellular response involved mostly in immunity, and to a lesser degree, in pigment production. In a few invertebrates including cephalopods (Schraermeyer 1994), some bivalves (e.g. Han

L. D'Alba (✉)

Naturalis Biodiversity Center, Leiden, the Netherlands

e-mail: liliana.dalbaaltamirano@naturalis.nl

et al. 2022) and some cnidarian (e.g. *Gornonia ventalina*; Mydlarz et al. 2008), melanogenesis is confined in cells where the pigment is concentrated in membrane-bound melanosome like granules. Of particular interest in the context of the origins of the melanosome are ascidians, because they are the sister taxa of vertebrates (Delsuc et al. 2006). They present an immune system based on circulating immunocytes (phagocytes, cytotoxic granular cells) that produce an amyloid-protein scaffolding to package melanin into granules to fill their cytoplasm (Franchi and Ballarin 2017; Franchi et al. 2019). Subsequently, these melanin-filled cells degranulate and localize melanin where encapsulation is needed. It is important to highlight that across Animalia, the production of melanin seems to be consistently supported and intrinsically linked to the formation of amyloid fibrils (Grimaldi et al. 2012; Franchi et al. 2019).

Insects have been heavily researched in the context of melanogenesis because they have evolved alternative ways to avoid the deleterious effects of toxic by-products from melanogenesis, by strictly limiting melanin distribution and targeting deposition only where it is needed. How the localization of melanization is controlled in those tissues is not fully known but several important discoveries, which deserve further mention, have been made in recent years.

Invertebrates rely exclusively on innate immunity to combat infections (Janeway and Medzhitov 2002; Ratcliffe and Whitten 2004). Thus, their immune defense is mainly based on cytotoxic effector responses, including phagocytosis, antimicrobial peptides and the synthesis of extracellular matrix and reactive intermediates of oxygen (ROI) and nitrogen (RNI), (Beutler 2004). More specifically, the production of melanin in insects contributes to the formation of cytotoxic molecules that interact with ROI and RNI to provide an efficient immune response (Nappi and Christensen 2005). Consequently, the typical demonstration of defensive responses against pathogens in insects is melanization.

Production and localization of melanin in insects involves the recruitment of phenoloxidases (POs) to initiate the biogenesis of melanin. Hemocytes, the blood cells of insects, are essential for melanogenesis and act as the main source and carriers of PPOs. The hemocytes containing PPOs break to deposit them at specific locations, for example, around wounds in the cuticle or infected areas. POs in the hemolymph enzymatically convert tyrosine into DOPAquinone (via hydroxylation followed by oxidation). DOPAquinone autocatalyse to form DOPochrome and finally, an isomerase converts it into DHI, which polymerizes to form eumelanin (Whitten and Coates 2017).

Perhaps through a highly conserved mechanism (Grimaldi et al. 2012), both systems of melanin containment in vertebrates and invertebrates involve the production of amyloid proteins (protein fibrils configured into cross- β sheet quaternary structures), which act as scaffolds to direct and enhance the rate of melanin accumulation (Fig. 1). In vertebrates, PMEL17, a pre-melanosomal protein specific to pigment cells, forms amyloid fibrils in the luminal space of melanosomes. In insects, amyloid proteins were first discovered in 2012 (Falabella et al. 2012), forming bundles of fibrils surrounding the nuclei of hemocytes. Other studies since then have shown that, indeed, amyloids in insects provide an anchoring mechanism for

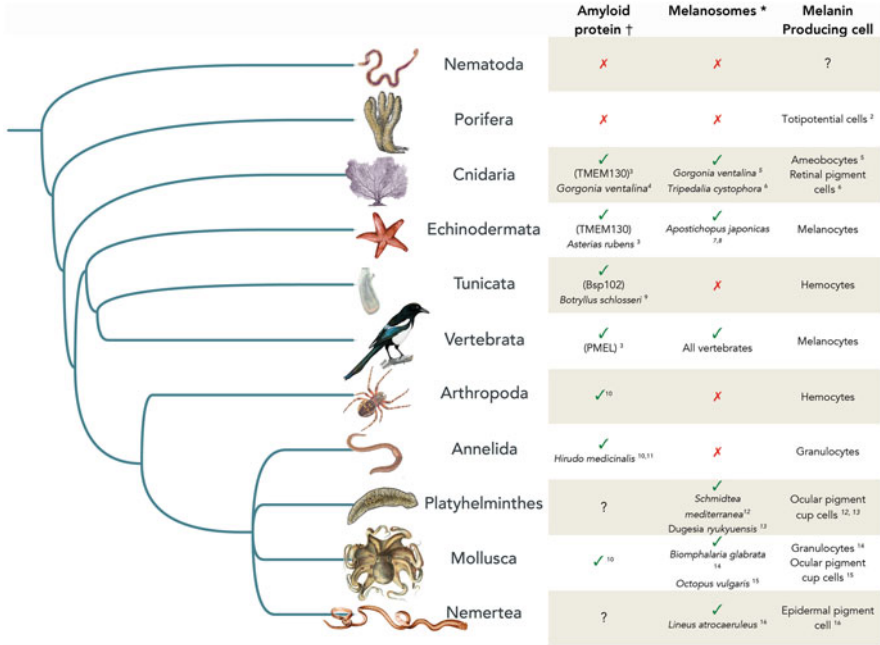


Fig. 1 Simplified phylogenetic tree of Animalia showing, for each major phyla, the correspondence between the production of amyloid proteins (when associated with melanin production) and the occurrence of melanosomes (reported in the literature as membrane-bound granules). References cited are summarized: (1) Freitas et al. (2019); (2) Araujo et al. (2012); (3) Chrystal et al. (2021); (4) Petes et al. (2003); (5) Mydlarz et al. (2008); (6) Kozmik et al. (2008); (7) Zhao et al. (2012); (8) Xing et al. (2017); (9) Ballarin et al. (2018); (10) Grimaldi et al. (2012); (11) Girardello et al. (2015); (12) Lambrus et al. (2015); (13) Hase et al. (2006); (14) Matricón-Gondran and Letocart (1999); (15) Rogers et al. (2019); (16) Moretto et al. (1988); (17) Pascale et al. (2014)

melanin and allow attachment of hemocytes to encapsulate pathogens (Pascale et al. 2014; Di Lelio et al. 2014).

In vertebrate skin, melanin is synthesized in specialized cells called melanophores (or melanocytes in humans; Ratcliffe and Gagen 1977), specifically inside melanosomes, which are present in skin, eyes and internal tissues. Melanophores are the most common type of chromatophores, responsible for the black, brown and brownish red coloration of integuments and their derivatives. Melanosomes are derived from early endosomal membranes and have become specialized to synthesize and store melanin. As a generality, melanin is composed of 30–50 nm nanoparticles, in which melanin monomers are cross-linked together and form stacking structures by Π - Π interactions (noncovalent interactions between the Π -bonds of aromatic rings). Melanosomes within melanophores often vary in size, shape and composition depending on the types of melanin they contain. Eumelanosomes (containing predominantly eumelanin, but see below) tend to be ellipsoidal and larger compared to pheomelanosomes, which are generally spherical but also more irregularly shaped

(Liu et al. 2005). It was hypothesized that the irregular shape of pheomelanosomes is due to the absence of amyloid protein scaffolds (PMEL17; Moyer 1966; Jimbow et al. 1983), which anchor the deposition of melanin in eumelanosomes. However, a few recent discoveries call the notion of a total absence of amyloid proteins in pheomelanosomes into question. First, it has been shown that PMEL17 protein is readily available in membranes and cytosol of epithelial cells, even in unpigmented cells, and that the high reactivity of the thiol group of cysteine residues in the PMEL17 molecule promotes bonding with melanin precursors (Ito et al. 2020). Second, across Animalia, from cnidarians, annelids, mollusks and insects, amyloid protein fibrils template and accelerate the production of melanins (Fig. 1), bind to reactive melanin precursors to prevent their harmful diffusion into the cytoplasm of hemocytes and are crucial in driving melanin close to intruders and pathogens in a process that seems to be evolutionarily conserved (Grimaldi et al. 2012). Third, using solid-state NMR spectroscopy, Thureau et al. (2012) showed that, as in eumelanosomes, a proteinaceous matrix is also present as a substrate for melanin polymerization within pheomelanosomes (from red human hair) but this matrix is irregular and defined by the configuration of the intraluminal globular vesicles of the premelanosome (see below; Fig. 2).

1.1 Non-integumentary Melanosomes

Besides their important roles in the integument, melanosomes also occur in animal eyes. Melanins and ommochromes protect the photoreceptor cells of the eye from prooxidant molecules both by neutralizing free radical products and by screening or filtering unwanted light. All vertebrates studied so far use eumelanin as their screening pigment, which is always contained in melanosomes (Ostrovsky et al. 2018) of diverse morphologies (Liu et al. 2005) and organized into distinct layers within the retinal pigment epithelium, basal to the rod and cone photoreceptors. In invertebrates, however, there seem to be mixed reports about the presence of granules containing melanin. Most invertebrates are assumed to use ommochromes, and to some extent, pterins and carotenoids to shield their photoreceptors and filter light (Vopalensky and Kozmik 2009). Notoriously, melanosomes are found in the inverse cup eye cells of platyhelminthes (*Schmidtea mediterranea*; Lambrus et al. 2015, *Dugesia ryukyurnsis*; Hase et al. 2006), photoreceptor cells in cnidarians (*Tripedalia cystophora*; Kozmik et al. 2008), retinal pigment epithelium, iridial and scleral cells in cephalopods (Rogers et al. 2019), shell eyes of polyplacophora (*Acanthopleura granulata*; Speiser et al. 2014) and the compound eyes of some arthropods, including fossil specimens (e.g. crane-fly; *Diptera*; Lindgren et al. 2019). In contrast to the large variation of melanosome shape in vertebrate eyes, invertebrate ocular melanosomes seem restricted to small ovoid morphologies (Clements et al. 2016). Importantly, the precise chemistry of invertebrate melanin granules remains poorly studied.

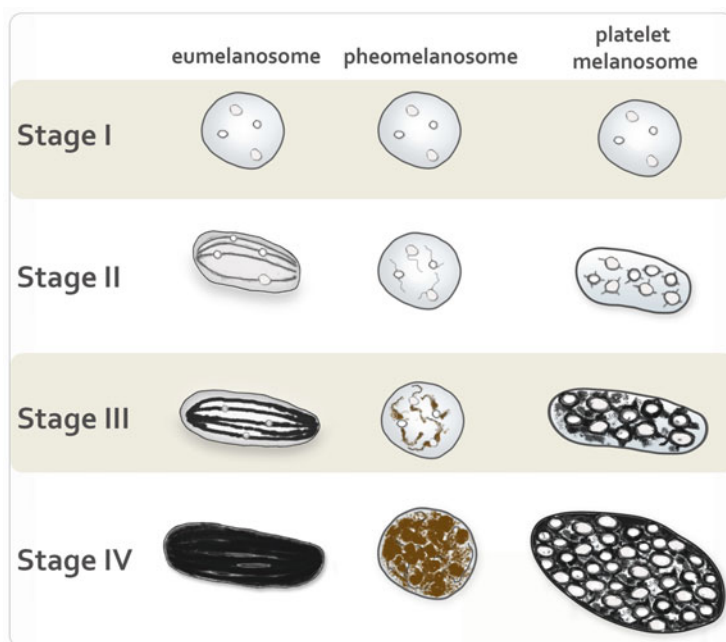


Fig. 2 Stages of development of eumelanosomes, pheomelanosomes and bird melanosome platelets. All melanosome types are thought to originate from multivesicular endosomes, which contain numerous ILVs. Stage I and II precede the production and deposition of melanin and are characterized by the formation of protein scaffolds, which guide the deposition of melanin. In pheomelanosomes and platelets the protein scaffold does not seem to form regular sheets as in eumelanosomes. In bird platelets the protein fibrils are hypothesized to form around the ILVs. Stage III is evidenced by the production of melanin. Mature melanosomes increase in size and adopt different shapes towards Stage IV. Complete melanization happens in Stage IV and in most cases also the occlusion of the ILVs

Melanosomes are also present in internal organs of vertebrates, including the heart, lungs liver, kidneys and spleen. These melanosomes contain mixed concentrations of eu- and pheomelanin and show large variations in shape and size, but this morphological diversity is not associated with their chemical composition (Rossi et al. 2019). The function of melanin within internal organs is hypothesized to include the detoxification, antioxidation and immune defense of cells in these tissues (Rossi et al. 2019). The concentrations of free radicals (e.g. O_2^-) inside cells are constantly maintained at low levels by the antioxidant action of catalytic enzymes that require metals like Cu, Zn and Mn to function (Geremia et al. 1989). Across vertebrates, there seems to be a negative correlation between melanin content in the liver and the activity of these enzymes, particularly that of superoxide dismutase (SOD), suggesting that melanin might be the main scavenger of singlet oxygen (1O_2) in the melanized organs.

1.2 *Melanosome Biogenesis*

Melanosomes containing exclusively eumelanin or pheomelanin are rare, exceptions being the melanosomes of the RPE (Peles et al. 2010). It even has been argued that pure pheomelanin does not occur in nature (Simon and Peles 2010). In most cases, melanosomes contain co-polymers and mixed amounts of the two melanin types (Ito and Wakamatsu 2003; Liu et al. 2005) in a configuration that follows a “casing model” (pheomelanin core encased by eumelanin; Agrup et al. 1981). Nevertheless, in an initial stage, all melanosomes contain tyrosinase, the enzyme that converts L-tyrosine to L-dopaquinone (DQ). After this first step, two different processes can occur. In eumelanogenesis, dopachrome, a result of the oxidization of cyclodopa, accumulates preferentially and is converted to DHI and DHICA and subsequently oxidates to form eumelanin. Only if a sufficient concentration of L-cysteine (Cys) is present within melanosomes, a redox exchange with DQ occurs to eventually produce pheomelanin (Ito et al. 2020). Only in eumelanosomes, two membrane-bound enzymes, tyrosinase-related protein-1 and -2 (TRP-1 and TRP-2), form a multi-enzyme complex and help stabilize tyrosinase (Kobayashi et al. 1998). The production of eumelanin or pheomelanin is then modulated by the opposing action of alpha-melanocyte stimulating hormone (MSH) and agouti protein. A shift between eumelanin and pheomelanin production can occur rapidly through changes in the pH inside melanosomes, where eumelanin is produced around neutral pHs but the production of pheomelanin proceeds faster and even suppresses eumelanogenesis at acidic pHs (Wakamatsu et al. 2017).

Based on observations of mammalian melanocytes, melanosomes are formed through a series of well-defined stages starting with the fusion between an endosome and intraluminal vesicles (ILVs) from the transcisternae of the Golgi apparatus to form a multivesicular body (MVB) (Hurbain et al. 2008) (Fig. 2). The first stage of melanosomes (I) begins with an MVB that lacks pigment and is characterized by incipient proteinaceous fibrils present in the organelle's lumen. In melanosomes containing predominantly eumelanin, fibrils are completely formed in stage II and the melanosome adopts an ellipsoidal shape. The protein PMEL17 (also known as gp100) is exclusively synthesized by melanocytes and represents the main structural constituent of fibrils (Raposo and Marks 2007). PMEL17 expression is strongly downregulated in cells synthesizing pheomelanin by agouti signaling (Furumura et al. 1998; Kobayashi et al. 1994) but a proteinaceous matrix is still found to be associated with the synthesis of melanin in pheomelanosomes (Thureau et al. 2012) (Fig. 2). PMEL17 has been used as a tracker of transferred melanin into keratinocytes (Singh et al. 2008).

In stages III and IV electron-dense melanin is synthesized and progressively deposited on the fibrils until the internal structure of the melanosome is completely obscured at the end of stage IV. Human pheomelanosomes seem to always be spherical throughout development and contain only granular melanin and amorphous proteinaceous material that does not form sheets (Jimbow et al. 1983). In derived melanosomes in birds (e.g. the hollow platelets in hummingbird feathers),

the ILVs seem to be retained and even increase in number throughout melanosome maturation, and do not become occluded by melanin deposition, giving the melanosome their distinctive porous appearance (D'Alba et al. 2021). Noticeably, a clear fibrillar proteinaceous structure was not observed in the early stages. Instead, melanin seems to be heavily deposited around the vesicles until all the intraluminal space of the melanosomes becomes filled, suggesting that, if present, the scaffolding protein could be seeded around the ILVs. The platelet melanosomes in hummingbird feathers dramatically increase in size, first elongating but then widening until they adopt their characteristic disc shape (D'Alba et al. 2021) (Fig. 2). The precise biogenetic path resulting in the formation of melanosomes is still a topic of active research and much information is needed particularly about pheomelanosomes and non-mammalian systems.

From epidermal melanocytes, stage IV melanosomes are then transported to keratinocytes through four different hypothesized processes (reviewed in D'Alba and Shawkey 2019). The vast majority of research in the field of melanin transfer has been done in mammals with a few exceptions on amphibians (Aspengren et al. 2006) and birds (Durrer and Villiger 1967). The most supported model of melanin transfer to keratinocytes in mammal skin is the exocytosis model, where melanin units, free of their melanosomal membranes are released into the extracellular space between cells and then internalized by keratinocytes through phagocytosis (Wu and Hammer 2014). Alternatively, the vesicle transfer model (Wu et al. 2012) has been supported by studies of melanogenesis in developing feathers (Durrer and Villiger 1967; Shawkey et al. 2015).

2 Melanosome Diversity Across Animal Taxa

2.1 *Evolution of Melanosome Shape*

In general, vertebrate melanosomes tend to have a globular or ovoid shape, about 600 nm in diameter, and seem to be very conserved across vertebrates (Li et al. 2014). It is only in mammals and birds where a much larger diversity of melanosome morphologies has been consistently observed (Li et al. 2014; Eliason and Clarke 2018). In these two groups, melanosomes that mostly contain eumelanin are oblong, with a length of about a micrometer, while melanosomes containing mostly pheomelanin are spheroidal and about 500 nm in diameter (Fig. 3).

However, the precise mechanism behind the correlation between melanin chemistry and melanosome morphology still needs to be clarified. For example, very little is known about the distribution of pheomelanin across other metazoans and whether melanosome morphology conveys information about eumelanin/phomelanin content. Phaeomelanin has so far been chemically identified in insects (Galván et al. 2015; García et al. 2016), chiton molluscs (Speiser et al. 2014), frogs (Wolnicka-Glubisz et al. 2012), lizards (Megía-Palma et al. 2018) and tortoises (Roulin et al. 2013); none of which display large morphological diversity in melanin packaging.

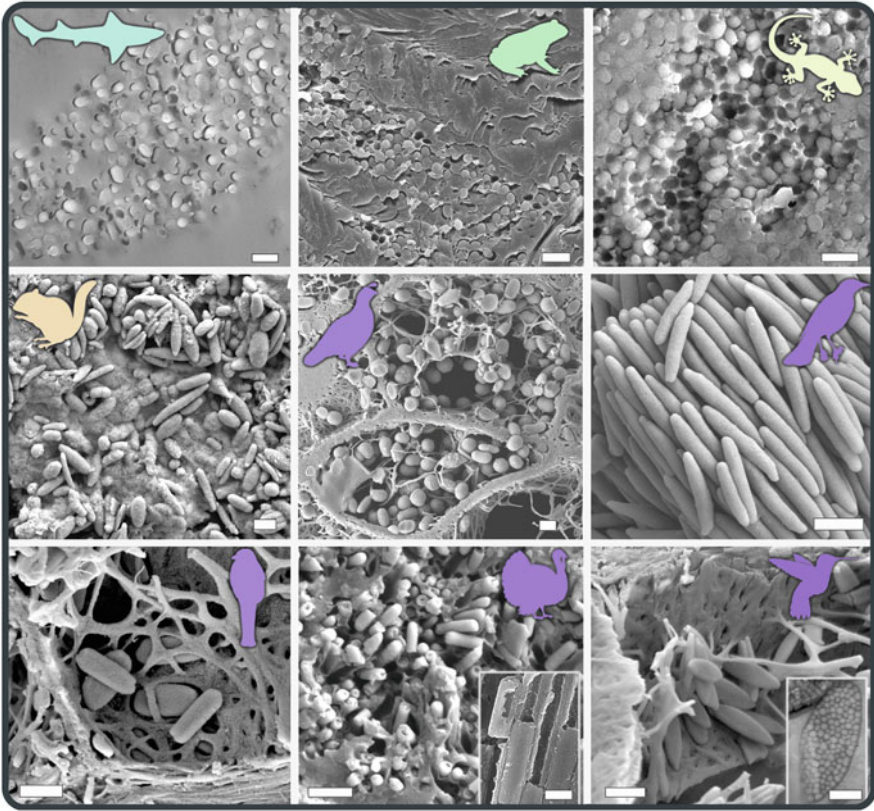


Fig. 3 Diversity of melanosome shapes in vertebrates. Melanosomes are globular and lack morphological diversity in fish, amphibians and reptiles. In mammals and birds (purple silhouettes) melanosomes display a greater diversity that ranges from spherical, to rod-like. The most derived melanosomes are found in birds, where cylinders, platelets and disc-shape melanosomes, solid and hollow, can be observed. (a) Fish: *Squalus acanthias*; (b) frog: *Bufo bufo*; (c) reptile: *Gekko gecko*; (d) mammal: *Tamias striatus*; (e) *Callipepla californica*; (f): *Agelaius phoeniceus*; (g) *Priotelus temnurus*; (h) *Meleagris gallopavo*; (i) *Melanotrochillus fuscus*. Scale bars: 1 μm , insets in (h) and (i): 500 nm

The presence of pheomelanin outside vertebrates also suggests a more extensive and earlier origin than previously anticipated.

A unique set of melanosome shapes that includes spheres, hollow cylinders, platelets and porous platelets has been discovered exclusively in bird feathers, with no equivalents anywhere else in metazoans (Fig. 3); these derived melanosomes are closely related to color production mechanisms in feathers. How melanosomes develop these geometries is as yet unclear. Some evidence suggests that melanosomes become hollow after their deposition in the developing feather cells (e.g. in *Meleagris gallopavo* Shawkey et al. 2015). The cores of melanosomes within the melanocyte seem to degenerate gradually and become hollow while in transit to the

developing barbule cell, perhaps after the pheomelanin core is lost during transport (Shawkey et al. 2015). This hypothesized process would agree with the eumelanin casing model of melanosomes (Agrup et al. 1981). However, the reason for the stability of melanosome cores in most (solid) melanosomes but not in a few types of feathers is unclear, and only using advanced techniques to verify the internal chemistry of developing hollow melanosomes would allow us to move towards clarification. Alternatively, holes within melanosomes could stem from the intraluminal vesicles already present in premelanosomes (see above), which could increase in size or fuse together during development as was suggested for hollow platelet melanosomes (D'Alba et al. 2021).

Recently, the presence of diverse melanosome geometries was reported in a tapejarid pterosaur (Cincotta et al. 2022). Melanosome shape was specific to the tissue in which melanosomes were embedded and interestingly elongate and ovoid melanosomes were present in the filamentous and branched feathers (integumentary appendages) while spheroidal melanosomes were found in the skin. The discovery of cylindrical melanosomes in pterosaurs and their similarity with melanosome morphology in birds and other theropod dinosaurs could indicate that either, the genes controlling melanosome formation and their phenotypes are ancestral to avemetatarsalians (i.e. clade that includes all dinosaurs and pterosaurs) or that they evolved separately (Cincotta et al. 2022). Parsimony suggests the former scenario is more likely.

So, what drove the evolution of animal melanosomes? Given that melanogenesis is a crucial component of immunity in invertebrates (Grimaldi et al. 2012) and in vertebrates melanin and immunity are tightly bound through the melanocortin pathway (Ducrest et al. 2008), it is reasonable to hypothesize that simple melanosomes could be present in organisms since the origin of the immune system. Later in animal evolution, the need for specialized pigmentation could have resulted in novel melanosome morphologies in two vertebrate lineages, bird and mammals. However, our estimation of the time of melanosome origins is limited to their availability in the fossil record. At present, the oldest known fossil-bearing melanosomes is the bilaterian *Tullimonstrum*, which only dates back to the Carboniferous (307 Ma; Clements et al. 2016). Older specimens may reveal an earlier origin of melanosomes.

3 Functional Relevance of Melanosome Diversity

3.1 General Properties of Melanin and Melanosomes

A general function of melanin across organisms is the protection against diverse forms of stress imposed on cells and tissues. Melanin interacts with environmental radiation and pollution causing structural changes to its molecules, which are not fully understood yet but that determine the ability to protect biological tissues. Melanins absorb light in the UV, visible and near-infrared regions (to at least 1300 nm; Wolbarsht et al. 1981; Medenhall et al. 2015) of the electromagnetic

spectrum and protect their embedding tissues by scattering or dissipating light by converting it into heat (Wolbarsht et al. 1981; Zonios et al. 2008; Bustamante et al. 1993; Hennessy et al. 2005). Melanin, behaving as a semiconductor (Prota 1988) is capable of transferring almost 90% of UV radiation to heat within a nanosecond (Mostert et al. 2012). Thus, exposure to UV radiation promotes melanogenesis in vertebrate integument, leading to the production of more melanin to protect the skin from UV damage.

Ionizing radiation, however, induces a transformation of melanin to an excited state. Excited melanin molecules transfer energy to molecular oxygen (3O_2) forming singlet oxygen (1O_2). UVB and UVA also produce an array of radical species including hydroxyl and hydrogen radicals, which can induce DNA damage. Ionized pheomelanin generates reactive oxygen species making it a potentially damaging molecule (Chiarelli-Neto et al. 2011).

Another very important chemical property of natural melanin is its ability to extract metals from the environment and chelate them to coordination sites within its polymeric structure. Melanin is negatively charged and readily binds to diverse metal ions through the formation of ionic and charge transfer complexes; specifically, metal ions bind to the o-semiquinone radical centers within melanin polymers (Felix et al. 1978). Thus, melanin's affinity for metals leads to the accumulation of several metal ions in melanized tissues including the internal organs of many vertebrates (Rossi et al. 2019). Melanosomes sequester bio-relevant metals (Na, Ca, Cu, Fe, Zn) as well as more toxic ones (Hg, Pb, Cr, Mn). Sepia melanin granules contain Mg, Ca, Na and K (Liu et al. 2014) and can store up to 8% Fe^{3+} by weight (Simon et al. 2006). Melanosomes have been reported to play an important role in calcium homeostasis in vertebrate cells (Bush and Simon 2007; Hoogduijn et al. 2003) and have been proposed as a mechanism of metal detoxification in fish (Cooper and Midling 2007), birds (Chatelain et al. 2014) reptiles (Martin et al. 2022) and mammals (Nicolaus 2005).

Nevertheless, the mechanism of this protective role is still poorly understood. For instance, it is not known how the metal ion transport and storage inside the melanosome take place. It has been shown that the metal ions first need to bind to the melanosome surface but they are not stored there (Simon et al. 2008). Similarly, how does the integrity of a melanosome change upon metal chelation? Or, are some metals more prone to degrading the polycatechol structure than others? Techniques that retrieve *in situ* magnetic and spectroscopic information are currently showing promising opportunities to track changes in melanosome structure, metal coordination and oxidation state under radical stress.

The cross-linked network of melanin inside melanosomes and proteins, as well as their binding to metals, is also behind the enhancement of the mechanical strength of numerous types of tissues. In birds, melanin strengthens feathers (Bonser 1995; Burt 1986) and increases resistance to bacterial degradation (Goldstein et al. 2004). Melanized tissue help resists mechanical damage in insect exoskeleton, and *Glycera* marine worms use melanin to strengthen their jaws (Moses et al. 2006).

Melanosome properties have been interpreted almost exclusively in terms of the properties of the melanin pigment they contain. Nevertheless, melanosomes contain

many types of proteins, enzymes and lipids which most certainly influence their behavior, the interactions between these organelles and other molecules, and ultimately their function. For example, proteomic analyses of melanosomes have revealed that nearly 1500 proteins are involved in the formation of different types of melanosomes (Chi et al. 2006). Similarly, an analysis of different types of ocular melanosomes showed that the content and composition of lipids vary greatly with melanosome type (Simon et al. 2006). Accordingly, the surface properties of melanosomes will vary with their composition and given that it is on the surface where melanin interacts with molecules inside cells, the presence of proteins and lipids is likely an important determinant of melanosomes' ability to chelate metals or absorb or reflect radiation.

These studies show that melanosomes show great complexity of molecular composition and that a complete understanding of the structure and biological functions of melanosomes can only be achieved by considering this mixed chemistry into account.

3.2 Optical Properties and Color Production by Melanosomes

Melanosomes are responsible for important variations in animal coloration, which play many essential roles in camouflage and communication. Due to its dense, cross-linked polymeric structure melanin possesses two unique optical properties, high refractive index (RI) and broadband absorption (Chen et al. 2014) which form the basis for the production of structural coloration, photoprotection, and thermal absorption in many biological systems. However, direct measurements of RI assume translucence of the material being measured, therefore, researchers have primarily used indirect methods to measure RI of melanin. The RI of melanin from damselfly wings and bird feathers was first estimated using polarizing interference microscopy and optical modeling (Stavenga et al. 2012, 2015). In those studies, the RI was calculated to be ~ 1.7 – 1.8 . More recently, Xiao et al. (2015) measured the RI of aqueous synthetic melanin and corroborated these values. Nevertheless, optical modeling assuming an RI of 2.0 has produced an excellent agreement between theoretical and empirical reflectance spectra (e.g. Eliason and Shawkey 2012; Xiao et al. 2014), therefore more direct measurements of diverse natural melanins are further needed.

Melanosomes can attenuate the incident light through absorption and scattering. Specific melanosome morphologies likely determine the extent to which they absorb or reflect light. Researchers have been able to determine the optical properties of single melanosomes using both indirect (pulsed laser disruption; Jacques et al. 1996) and direct methods (photoemission electron microscopy; Peles et al. 2010; Peles and Simon 2011). These studies have provided valuable insight into the photoabsorption behavior of melanosomes. For example, we now know that melanosomes from different types of tissues (e.g. skin, choroid, RPE, internal organs) and embryonic origin show different absorption coefficients, most likely explained by differences in

their melanin content (Jacques et al. 1996), chemical composition and/or structural configuration (Peles et al. 2010).

Eumelanin is built from varying amounts of two building monomers, 5,6-dihydroxyindole (DHI) and 5,6-dihydroxyindole-2-carboxylic acid (DHICA) while pheomelanin is derived from isomers of cysteinyl dopa. Correspondingly, the photoabsorption coefficient of melanosomes increases with larger DHICA content relative to DHI (Peles and Simon 2011) and decreases with larger ratios of pheomelanin to eumelanin (Peles and Simon 2010). Melanosomes are mostly comprised of melanins but they also contain ions, proteins, and lipids. From these components, some amino acids significantly absorb in the UV portion and therefore they could contribute to the absorption properties of melanosomes, nevertheless, this still awaits further examination.

One limitation of the aforementioned studies is that the optical properties have been measured mostly within the UV range (240–400 nm) and in some visible wavelengths (500–600 nm). The main focus so far has been to reveal functional differences in photoprotection provided by melanosomes in the context of melanoma and skin cancer. Thus, we still do not know much about the variation in optical properties of different types of melanosomes from the perspective of color production or thermoregulation.

Even though melanin is a dark pigment and it is responsible for colors ranging from black to greys and browns, some of the brightest colors in nature are produced by nanoscale arrangements of melanosomes (Maia et al. 2013; Eliason et al. 2013). Further, melanosomes vary greatly in shape and size, and this diversity is particularly large in birds (see above; Fig. 3) where we also see some of the best examples of brilliant iridescence. This is due to its strong absorption and high RI that can sharply contrast with those of other materials with lower RI such as feather keratins (~ 1.56) and air (1.0). Consequently, when melanosomes are spatially organized with keratins or air (as in hollow melanosomes), they can produce bright iridescent colors. Without spatial organization, these melanosomes produce typical dark melanin-based colors. However, the precise mechanism of color production by melanosomes is still not fully understood. Some studies have shown that melanin enhances the color saturation and or purity by absorbing incoherently scattered light (Shawkey and Hill 2006; Xiao et al. 2017). Experimental work on synthetic melanin particles demonstrated that coloration can be adjusted either by varying the spacing between the melanosomes (Xiao et al. 2017) or the degree of layering and separation between melanin and keratin.

In recent years a basic separation of the types of iridescent colors produced by melanosomes has been proposed. “Thick films” have a single layer of melanin granules below a single superficial keratin layer (Brink and van der Berg 2004; Doucet 2006); here, the layer of melanosomes apparently serves primarily to define the thickness of the superficial keratin layer (Brink and van der Berg 2004). An example of this type of coloration is found in the coppery-purple iridescence of the dark plumage of the hadeda ibis, *Bosthrychia hagedash* (Brink and van der Berg 2004), which is produced primarily by coherent scattering from a thick ($\sim 0.8 \mu\text{m}$) and uniform keratin cortex. Conversely, “Thin films” are formed by multiple layers

of melanin granules and keratin (Durrer 1986; Prum 2006). In some cases, a single continuous layer of melanosomes under a thin keratin cortex is enough to produce intense reflectance peaks and iridescent effects (e.g. European and Cape starlings; Freyer et al. 2021). In other cases, brilliantly-colored iridescent feathers are produced by coherent light scattering from multiple (~ 20), alternating layers of keratin and air-filled, disk-shaped melanin granules (e.g. hummingbirds; Family Trochilidae, Greenewalt et al. 1960; Eliason et al. 2020).

Melanosomes may also be arranged two-dimensionally, for example, in the hexagonal close-packed configuration that confers diverse iridescent colors to dabbling duck wing patches (Eliason and Shawkey 2012). The authors in that study showed that small changes in melanosome diameter and spacing can cause strong shifts in hue, but these parameters and thus the resulting colors are limited relative to what could be theoretically possible, in other words, structural colors in birds have not occupied the full extent of the potential avian colorspace. This could perhaps be due to energetic constraints during development, like nutritional or environmental stress. Optical nanostructures like the ones formed by melanosomes enable the production of colors otherwise hard to produce, for example, green and blue colors that require rare pigments (Durrer 1986). Accordingly, the functions facilitated by these colors such as camouflage may have enabled the colonization of new niches or the production of novel signals for sexual selection (Maia et al. 2013).

Hollow melanosomes introduce an additional low refractive index material (air) into organized nanostructures and thereby produce even brighter colors (Eliason et al. 2013). These types of melanosomes have independently evolved numerous times in some lineages with bright colors (e.g. turkeys, hummingbirds, African starlings) and have recently been shown to accelerate both the rate of color evolution and speciation in lineages that have them (Maia et al. 2013; Beltrán et al. 2021). The ability of melanosome arrays to selectively interact with wavelengths of light with high precision, and to be “tuned” to specific wavelengths through slight changes in dimensionality makes them ideal models for bioinspired optical devices (Parker and Townley 2007).

In some animals like cephalopods and reptiles, melanosomes are also involved in producing highly dynamic and fast-changing colorations. Controlling melanosome density and distribution in their integument can switch from dull or obscure colors to vibrant and intense hues (Sköld et al. 2013). In other organisms, specific arrangements of melanosomes can lead to enhanced antireflection. For example, deep-sea fishes have evolved an efficient antireflective skin, which they use to improve camouflage and being undetected in dark deep waters. These fish show a simple arrangement of close-packed, small melanosomes with a size and shape optimized to produce the lowest reflectance. These packed melanosomes scatter light and increase the optical path length and absorption by melanin (Davis et al. 2020).

3.3 Thermal Properties of Melanized Tissue

Melanin-based coloration can determine the thermal properties of the vertebrate integument. Coloration strongly depends on the concentration of pigments deposited in animal tissues and pigments selectively absorb particular wavelengths of visible light. Variation in reflectance and absorption of light affect the heating of the skin surface (Wolf and Walsberg 2000; Rogalla et al. 2021). When a body surface is heated by the sun under cold conditions, the temperature gradient between the surface and the interior is reduced, resulting in a decrease in heat loss to the environment (Lustick et al. 1970; Lustick 1969; Heppner 1970; Cowles 1967). However, when ambient temperatures are high and skin surface temperature exceeds body temperature due to solar heating, animals gain excessive heat.

Structurally iridescent feathers are less reflective than pigmentary-colored feathers and heat up more under exposure to solar radiation (Rogalla et al. 2021). Iridescent feathers contain large concentrations of melanosomes, often higher than black feathers, and these melanosomes are aligned forming multiple layers inside feather barbules. The organized arrangement and large concentration of melanosomes in iridescent feathers (Maia et al. 2013) may lower the reflectance in the NIR compared to non-iridescent feathers, (Shawkey et al. 2017). As a result, these arrangements could enhance photothermal absorption and result in higher surface temperatures. Both, experimental and theoretical studies on the thermal effects of melanosome properties in feathers have shown that in addition to melanin concentration, melanosome shape can have substantial effects on photothermal absorption within tissues. Optical simulations have estimated that melanosomes with greater aspect ratios (i.e. flat and long platelets) could have higher photothermal absorption compared to oblong or spherical melanosomes, regardless of the arrangement in which they exist (organized or random arrangements of melanosomes). Therefore, tissues containing these platelet melanosomes are expected to heat up more than those containing rods or spherical melanosomes (Rogalla et al. 2021). Similarly, experiments using synthetic particles have demonstrated that hollow melanosomes exhibit enhanced absorption as hollow structures allow the transmission of light inside the air gaps (Wang and Guo 2017). This enhanced absorption suggests a potential enhanced photothermal efficiency of tissues with hollow melanosomes but future investigations using natural melanosomes will be needed in order to test this hypothesis.

4 Novel Techniques in the Study of Melanosomes

Identifying patterns in melanin composition of differently-colored tissues has been the goal of much research in recent decades and could give great insights into the relationship between melanin chemistry and color, as well as inform about the links between melanosome chemistry and the material's biomechanical properties.

Unfortunately, our knowledge of the chemistry of melanosomes remains limited and is primarily based on samples from human hair and squid ink sacs.

Different techniques can reveal different aspects of melanin chemistry, and a coordinated multi-pronged approach most likely will succeed where individual techniques have not. Some of the techniques so far used include nuclear magnetic resonance (NMR; solution and solid-state), Raman (molecule level) and MALDI (polymer level) spectroscopy, and ToF-SIMS to identify the fingerprint of the melanin at different levels of biological scale. X-ray photoelectron spectroscopy (XPS) analyzes the surface composition of melanosomes and provides high-resolution elemental data of the top ~100 nm of a sample, which would be perfect to determine the composition of the membrane that envelops melanosomes.

Pheomelanin has still not been well defined, either regarding its spectral or other physical characteristics. Among the techniques that have been applied to the structural and functional characterization of pheomelanin are gas chromatography-mass spectrometry (GC-MS) and ultrafast absorption spectroscopy. In the last decade, solid-state NMR spectroscopy has shown great potential to determine the structure of many biomaterials, but it has only been started to be used for the characterization of melanins, (Tian et al. 2003; Chatterjee et al. 2014; Thureau et al. 2012). 1D and 2D solid-state NMR techniques have been utilized to investigate the structure and dynamics of eumelanin and pheomelanin extracted from human black and red hair (Thureau et al. 2012) this procedure does not alter the pigment structure, thus, it has the advantage of retaining the morphology of intact melanosomes.

The surface features of individual melanosomes can be analyzed using atomic force microscopy (AFM), which, with an appropriately functionalized tip, can be applied to force probe surfaces to single-molecule resolution. Recent research using AFM has provided novel insights into the structure near the surface of melanosomes, for example, that melanosomes, regardless of their shape, have a substantially rough surface (Simon et al. 2008).

Very recently, synchrotron infrared nano-spectroscopy (SINS), a combination of atomic force microscopy (AFM) and infrared (IR) spectroscopy, emerged as a powerful tool for nanoscale chemical characterization of materials as it takes advantage of the low-noise, broadband, high spectral irradiance, and coherence of synchrotron infrared radiation for infrared measurements with nanometer spatial resolution. This powerful combination provides a qualitatively new form of broadband spatio-spectral analysis of nanoscale, mesoscale, and surface phenomena that were previously difficult to study with IR techniques and makes it ideal to analyze the chemistry of individual melanosomes. Stanic et al. (2018) used SINS for *in situ* nanoscale characterization of black and white sheep hair. The authors revealed a strong orientation of keratin fibrils along the hair fiber axis. More interestingly, a comparison of the white and black types of hair allowed them to isolate the IR fingerprint hair melanosomes, enabling them to achieve the unprecedented assignment of the vibrational modes of pheomelanin and eumelanin.

Melanosomes constitute a key component of animal pigmentary and defense systems but for a long time have resisted complete characterization due, to a great extent, to melanin's inherent physicochemical properties. However, only a better

understanding of melanosome properties and the relevance of their diverse forms across animals will lead to a full knowledge of their functions.

References

- Agrup G, Hansson C, Rorsman H, Rosengren E (1981) The effect of cysteine on oxidation of tyrosine dopa, and cysteinyl dopas. *Arch Dermatol Res* 272(1):103–115
- Araujo M, Xavier JR, Nunes CD, Vaz PD, Humanes M (2012) Marine sponge melanin: a new source of an old biopolymer. *Struct Chem* 23:115–122
- Aspengren S, Hedberg D, Wallin M (2006) Studies of pigment transfer between *Xenopus laevis* melanophores and fibroblasts in vitro and in vivo. *Pigment Cell Res* 19:136–145. <https://doi.org/10.1111/j.1600-0749.2005.00290.x>
- Ballarin L, Franchi N, Peronato A, Grimaldi A, Girardello R, de Eguileor M (2018) Amyloid and immune responses in the colonial ascidian *Botryllus schlosseri*. *Invertebr Surviv J*:124–124
- Beltrán DF, Shultz AJ, Parra JL (2021) Speciation rates are positively correlated with the rate of plumage color evolution in hummingbirds. *Evolution* 75(7):1665–1680
- Beutler B (2004) Innate immunity: an overview. *Mol Immunol* 40(12):845–859
- Bonser RHC (1995) Melanin and the abrasion resistance of feathers. *Condor* 97:590–591
- Brink DJ, van der Berg NG (2004) Structural color from the feathers of the bird *Bostrychia hagedash*. *J Phys D Appl Phys* 37:813–818
- Burt EH Jr (1986) An analysis of physical, physiological, and optical aspects of avian coloration with emphasis on wood-warblers. *Ornithol Monogr* 38:1–128
- Bush WD, Simon JD (2007) Quantification of Ca²⁺ binding to melanin supports the hypothesis that melanosomes serve a functional role in regulating calcium homeostasis. *Pigment Cell Res* 20(2):134–139
- Bustamante J, Bredeston L, Malanga G, Mordoh J (1993) Role of melanin as a scavenger of active oxygen species. *Pigment Cell Res* 6:348–353
- Butler M, Day A (1998) Fungal melanins: a review. *Can J Microbiol* 44:1115–1136. <https://doi.org/10.1139/w98-119>
- Chatelain M, Gasparini J, Jacquin L, Frantz A (2014) The adaptive function of melanin-based plumage coloration to trace metals. *Biol Lett* 10(3):20140164
- Chatterjee S, Prados-Rosales R, Tan S, Itin B, Casadevall A, Stark RE (2014) Demonstration of a common indole-based aromatic core in natural and synthetic eumelanins by solid-state NMR. *Org Biomol Chem* 12(34):6730–6736
- Chen CT, Chuang C, Cao J, Ball V, Ruch D, Buehler MJ (2014) Excitonic effects from geometric order and disorder explain broadband optical absorption in eumelanin. *Nat Commun* 5:3859. <https://doi.org/10.1038/ncomms4859>
- Chi A, Valencia JC, Hu ZZ, Watabe H, Yamaguchi H, Mangini NJ et al (2006) Proteomic and bioinformatic characterization of the biogenesis and function of melanosomes. *J Proteome Res* 5(11):3135–3144
- Chiarelli-Neto O, Pavani C, Ferreira AS, Uchoa AF, Severino D, Baptista MS (2011) Generation and suppression of singlet oxygen in hair by photosensitization of melanin. *Free Radic Biol Med* 51:1195–1202. <https://doi.org/10.1016/j.freeradbiomed.2011.06.013>
- Christensen BM, Forton KF (1986) Hemocyte-mediated melanization of microfilariae in *Aedes aegypti*. *J Parasitol* 72:220–225. <https://doi.org/10.2307/3281595>
- Chrystal PW, Footz T, Hodges ED, Jensen JA, Walter MA, Allison WT (2021) Functional domains and evolutionary history of the PMEL and GPNMB family proteins. *Molecules* 26(12):3529
- Cincotta A, Nicolai M, Campos HBN, McNamara M, D'Alba L, Shawkey MD, Kischlat EE, Yans J, Carleer R, Escuillie F, Godefroit P (2022) Pterosaur melanosomes support signalling functions for early feathers. *Nature* 604(7907):684–688

- Clements T, Dolocan A, Martin P et al (2016) The eyes of *Tullimonstrum* reveal a vertebrate affinity. *Nature* 532:500–503. <https://doi.org/10.1038/nature17647>
- Cooper M, Midling KØ (2007) Blood vessel melanosis: a physiological detoxification mechanism in Atlantic cod (*Gadus morhua*). *Aquac Int* 15(1):43–54
- Cowles RB (1967) Black pigmentation: adaptation for concealment or heat conservation? *Science* 158(3806):1340–1341
- D’Alba L, Shawkey MD (2019) Melanosomes: biogenesis, properties, and evolution of an ancient organelle. *Physiol Rev* 99(1):1–19
- D’Alba L, Meadows M, Maia R, Yeo JS, Manceau M, Shawkey MD (2021) Morphogenesis of iridescent feathers in Anna’s hummingbird calypte anna. *Integr Comp Biol* 61(4):1502–1510
- Davis AL, Thomas KN, Goetz FE, Robison BH, Johnsen S, Osborn KJ (2020) Ultra-black camouflage in deep-sea fishes. *Curr Biol* 30(17):3470–3476
- Delsuc F, Brinkmann H, Chourrout D, Philippe H (2006) Tunicates and not cephalochordates are the closest living relatives of vertebrates. *Nature* 439(7079):965–968
- Di Lelio I, Varricchio P, Di Prisco G, Marinelli A, Lasco V, Caccia S et al (2014) Functional analysis of an immune gene of *Spodoptera littoralis* by RNAi. *J Insect Physiol* 64:90–97
- Doucet SM (2006) Iridescent plumage in satin bowerbirds: structure, mechanisms and nanostructural predictors of individual variation in colour. *J Exp Biol* 209:380–390
- Ducrest AL, Keller L, Roulin A (2008) Pleiotropy in the melanocortin system, coloration and behavioural syndromes. *Trends Ecol Evol* 23(9):502–510
- Durrer H (1986) The skin of birds: colouration. In: Bereiter-Hahn J, Matolsky AG, Richards KS (eds) *Biology of the integument 2, vertebrates*, vol 2. Springer, Berlin, pp 239–247
- Durrer H, Villiger W (1967) Bildung der Schillerstruktur beim Glanzstar. Elektronenmikroskopische Untersuchungen der Entstehung gasgefüllter Melaninkörner. *Z Zellforsch Mikrosk Anat* 81:445–456. <https://doi.org/10.1007/BF00342767>
- Eliason CM, Clarke JA (2018) Metabolic physiology explains macroevolutionary trends in the melanic colour system across amniotes. *Proc R Soc B* 285(1893):20182014
- Eliason CM, Shawkey MD (2012) A photonic heterostructure produces diverse iridescent colours in duck wing patches. *J Royal Soc Interface* 9:2279–2289
- Eliason CM, Bitton PP, Shawkey MD (2013) How hollow melanosomes affect iridescent colour production in birds. *Proc R Soc B Biol Sci* 280(1767):20131505
- Eliason CM, Maia R, Parra JL, Shawkey MD (2020) Signal evolution and morphological complexity in hummingbirds (Aves: Trochilidae). *Evolution* 74(2):447–458
- Falabella P, Riviello L, Pascale M, Di Lelio I, Tettamanti G, Grimaldi A et al (2012) Functional amyloids in insect immune response. *Insect Biochem Mol Biol* 42(3):203–211
- Felix CC, Hyde JS, Sama T, Sealy RC (1978) Interactions of melanin with metal ions. Electron spin resonance evidence for chelate complexes of metal ions with free radicals. *J Am Chem Soc* 100(12):3922–3926
- Franchi N, Ballarin L (2017) Immunity in protochordates: the tunicate perspective. *Front Immunol* 8:674
- Franchi N, Ballarin L, Peronato A, Cima F, Grimaldi A, Girardello R, de Eguileor M (2019) Functional amyloidogenesis in immunocytes from the colonial ascidian *Botryllus schlosseri*: evolutionary perspective. *Dev Comp Immunol* 90:108–120
- Freitas DF, Vieira-Da-Motta O, Mathias LDS, Franco RWDA, Gomes RDS, Vieira RAM et al (2019) Synthesis and role of melanin for tolerating in vitro rumen digestion in *Duddingtonia flagrans*, a nematode-trapping fungus. *Mycology* 10(4):229–242
- Freyer P, Wilts BD, Stavenga DG (2021) Cortex thickness is key for the colors of iridescent starling feather barbules with a single, organized melanosome layer. *Front Ecol Evol* 9:746254
- Furumura M, Sakai C, Potterf SB, Vieira WD, Barsh GS, Hearing VJ (1998) Characterization of genes modulated during pheomelanogenesis using differential display. *Proc Natl Acad Sci U S A* 95:7374–7378. <https://doi.org/10.1073/pnas.95.13.7374>
- Galván I, Jorge A, Edelaar P, Wakamatsu K (2015) Insects synthesize pheomelanin. *Pigment Cell Melanoma Res* 28(5):599–602

- García AJ, Polidori C, Nieves-Aldrey JL (2016) Pheomelanin in the secondary sexual characters of male parasitoid wasps (Hymenoptera: Pteromalidae). *Arthropod Struct Dev* 45(4):311–319
- Geremia E, Corsaro C, Baratta D, Santoro C, Scalia M, Sichel G (1989) Antioxidant enzymatic systems in pigment tissue of amphibia. *Pigment Cell Res* 2(3):208–212
- Girardello R, Tasselli S, Baranzini N, Valvassori R, de Eguileor M, Grimaldi A (2015) Effects of carbon nanotube environmental dispersion on an aquatic invertebrate, *Hirudo medicinalis*. *PLoS One* 10(12):e0144361
- Goldstein G, Flory KR, Browne BA, Majid S, Ichida JM, Burt EH Jr (2004) Bacterial degradation of black and white feathers. *Auk* 121:656–659
- Greenewalt CH, Brandt W, Friel DD (1960) Iridescent colors of hummingbird feathers. *J Opt Soc* 50:1005
- Grimaldi A, Girardello R, Malagoli D, Falabella P, Tettamanti G, Valvassori R, Ottaviani E, De Eguileor M (2012) Amyloid/melanin distinctive mark in invertebrate immunity. *Invertebr Surviv J* 9(2):153–162
- Han Y, Xie C, Fan N, Song H, Wang X, Zheng Y, Zhang M, Liu Y, Huang B, Wei L, Wang X (2022) Identification of melanin in the mantle of the Pacific oyster *Crassostrea gigas*. *Front Mar Sci* 31:9
- Hase S, Wakamatsu K, Fujimoto K, Inaba A, Kobayashi K, Matsumoto M et al (2006) Characterization of the pigment produced by the planarian, *Dugesia ryukyuensis*. *Pigment Cell Res* 19(3):248–249
- Hennessy A, Oh C, Diffey B, Wakamatsu K, Ito S, Rees J (2005) Eumelanin and pheomelanin concentrations in human epidermis before and after UVB irradiation. *Pigment Cell Res* 18:220–223
- Heppner F (1970) The metabolic significance of differential absorption of radiant energy by black and white birds. *Condor* 72(1):50–59
- Hoogduijn MJ, Smit NP, Van Der Laarse A, Van Nieuwpoort AF, Wood JM, Thody AJ (2003) Melanin has a role in Ca²⁺ homeostasis in human melanocytes. *Pigment Cell Res* 16(2):127–132
- Hurbain I, Geerts WJ, Boudier T, Marco S, Verkleij AJ, Marks MS, Raposo G (2008) Electron tomography of early melanosomes: implications for melanogenesis and the generation of fibrillar amyloid sheets. *Proc Natl Acad Sci* 105(50):19726–19731
- Ito S, Wakamatsu K (2003) Quantitative analysis of eumelanin and pheomelanin in humans, mice, and other animals: a comparative review. *Pigment Cell Res* 16(5):523–531
- Ito S, Wakamatsu K (2008) Chemistry of mixed melanogenesis – pivotal roles of dopaquinone. *Photochem Photobiol* 84(3):582–592
- Ito S, Sugumaran M, Wakamatsu K (2020) Chemical reactivities of ortho-quinones produced in living organisms: fate of quinonoid products formed by tyrosinase and phenoloxidase action on phenols and catechols. *Int J Mol Sci* 21(17):6080
- Jacques SL, Glickman RD, Schwartz JA (1996) Internal absorption coefficient and threshold for pulsed laser disruption of melanosomes isolated from retinal pigment epithelium. In: *Laser-tissue interaction VII*, vol 2681. SPIE, pp 468–477
- Janeway CA Jr, Medzhitov R (2002) Innate immune recognition. *Annu Rev Immunol* 20(1):197–216
- Jimbow K, Ishida O, Ito S, Hori Y, Witkop CJ Jr, King RA (1983) Combined chemical and electron microscopic studies of pheomelanosomes in human red hair. *J Invest Dermatol* 81:506–511. <https://doi.org/10.1111/1523-1747.ep12522838>
- Kabat AR, Hershler R (1993) The prosobranch snail family Hydrobiidae (Gastropoda: Rissooidea): review of classification and supraspecific taxa
- Kobayashi T, Urabe K, Winder A, Jiménez-Cervantes C, Imokawa G, Brewington T, Solano F, García-Borrón JC, Hearing VJ (1994) Tyrosinase related protein 1 (TRP1) functions as a DHICA oxidase in melanin biosynthesis. *EMBO J* 13:5818–5825
- Kobayashi T, Imokawa G, Bennett DC, Hearing VJ (1998) Tyrosinase stabilization by Tyrp1 (the brown locus protein). *J Biol Chem* 273:31801–31805. <https://doi.org/10.1074/jbc.27348.31801>

- Kozmik Z, Ruzickova J, Jonasova K, Matsumoto Y, Vopalensky P, Kozmikova I, Vlcek C (2008) Assembly of the cnidarian camera-type eye from vertebrate-like components. *Proc Natl Acad Sci* 105(26):8989–8993
- Lambrus BG, Cochet-Escartin O, Gao J, Newmark PA, Collins EMS, Collins JJ III (2015) Tryptophan hydroxylase is required for eye melanogenesis in the planarian *Schmidtea mediterranea*. *PLoS One* 10(5):e0127074
- Li Q, Clarke JA, Gao KQ, Zhou CF, Meng Q, Li D, D'Alba L, Shawkey MD (2014) Melanosome evolution indicates a key physiological shift within feathered dinosaurs. *Nature* 507(7492):350–353
- Lindgren J, Nilsson DE, Sjövall P, Jarenmark M, Ito S, Wakamatsu K, Kear BP, Schultz BP, Sylvestersen RL, Madsen H, LaFountain JR (2019) Fossil insect eyes shed light on trilobite optics and the arthropod pigment screen. *Nature* 573(7772):122–125
- Liu Y, Hong L, Wakamatsu K, Ito S, Adhyaru B, Cheng C-Y, Bowers CR, Simon JD (2005) Comparison of structural and chemical properties of black and red human hair melanosomes. *Photochem Photobiol* 81:135–144. <https://doi.org/10.1562/2004-08-03-RA-259.1>
- Liu S, Shawkey MD, Parkinson D, Ahmed M (2014) Elucidation of the chemical composition of avian melanin. *R Soc Chem Adv* 4:40396–40399
- Lustick S (1969) Bird energetics: effects of artificial radiation. *Science* 163(3865):387–390
- Lustick S, Talbot S, Fox EL (1970) Absorption of radiant energy in Redwinged Blackbirds (*Agelaius phoeniceus*). *Condor* 72(4):471–473
- Maia R, Rubenstein DR, Shawkey MD (2013) Key ornamental innovations facilitate diversification in an avian radiation. *Proc Natl Acad Sci* 110(26):10687–10692
- Martin J, Recio P, Rodriguez-Ruiz G, Barja I, Gutierrez E, Garcia LV (2022) Relationships between soil pollution by heavy metals and melanin-dependent coloration of a fossorial amphibia reptile. *Integr Zool* 17(4):596–607
- Matricón-Gondran M, Letocart M (1999) Internal defenses of the snail *Biomphalaria glabrata*: III. Observations on tubular helical filaments induced in the hemolymph by foreign material. *J Invertebr Pathol* 74(3):248–254
- Medenhall MJ, Nunez AS, Martin RK (2015) Human skin detection in the visible and near infrared. *Appl Opt* 54:10559–10570
- Megía-Palma R, Jorge A, Reguera S (2018) Raman spectroscopy reveals the presence of both eumelanin and pheomelanin in the skin of lacertids. *J Herpetol* 52(1):67–73
- Moretto HJ, Sánchez M, Vernet G (1988) The colour pattern of *Lineus atrocaeruleus* (Nemertea). *Hydrobiologia* 156(1):183–189
- Moses DN, Harrelld JH, Stucky GD, Waite JH (2006) Melanin and glyceric acids in jawless vertebrates. *J Biol Chem* 281:34826–34832
- Mostert AB, Powell BJ, Pratt FL, Hanson GR, Sarna T, Gentle IR, Meredith P (2012) Role of semiconductivity and ion transport in the electrical conduction of melanin. *Proc Natl Acad Sci U S A* 109:8943–8947
- Moyer FH (1966) Genetic variations in the fine structure and ontogeny of mouse melanin granules. *Am Zool* 6:43–66
- Mydlarz LD, Holthouse SF, Peters EC, Harvell CD (2008) Cellular responses in sea fan corals: granular amoebocytes react to pathogen and climate stressors. *PLoS One* 3(3):e1811. <https://doi.org/10.1371/journal.pone.0001811>
- Nappi AJ, Christensen BM (2005) Melanogenesis and associated cytotoxic reactions: applications to insect innate immunity. *Insect Biochem Mol Biol* 35(5):443–459
- Nicolaus BJR (2005) A critical review of the function of neuromelanin and an attempt to provide a unified theory. *Med Hypotheses* 65:791–796
- Ostrovsky MA, Zak PP, Dontsov AE (2018) Vertebrate eye melanosomes and invertebrate eye ommochromes as screening cell organelles. *Biol Bull* 45(6):570–579
- Parker AR, Townley HE (2007) Biomimetics of photonic nanostructures. *Nat Nanotechnol* 2(6):347–353

- Pascale M, Laurino S, Vogel H, Grimaldi A, Monné M, Riviello L et al (2014) The Lepidopteran endoribonuclease e-U domain protein P102 displays dramatically reduced enzymatic activity and forms functional amyloids. *Dev Comp Immunol* 47(1):129–139
- Peles DN, Simon JD (2010) Direct measurement of the ultraviolet absorption coefficient of single retinal melanosomes. *Photochem Photobiol* 86(2):279–281
- Peles DN, Simon JD (2011) UV-absorption spectra of melanosomes containing varying 5, 6-dihydroxyindole and 5, 6-dihydroxyindole-2-carboxylic acid content. *J Phys Chem B* 115(43):12624–12631
- Peles DN, Lin E, Wakamatsu K, Ito S, Simon JD (2010) Ultraviolet absorption coefficients of melanosomes containing eumelanin as related to the relative content of DHI and DHICA. *J Phys Chem Lett* 1(15):2391–2395
- Petes LE, Harvell CD, Peters EC, Webb MAH, Mullen KM (2003) Pathogens compromise reproduction and induce melanization in Caribbean sea fans. *Mar Ecol Prog Ser* 264:167–171
- Polacheck I, Kwon-Chung KJ (1988) Melanogenesis in *Cryptococcus neoformans*. *J Gen Microbiol* 134:1037–1041
- Prota G (1988) Progress in the chemistry of melanins and related metabolites. *Med Res Rev* 8:525–556
- Prum R (2006) Anatomy, physics, and evolution of structural colors. In: Hill GE, KJ MG (eds) *Bird coloration: mechanisms and measurements*, vol 1. Harvard University Press, Cambridge, pp 295–353
- Raposo G, Marks MS (2007) Melanosomes—dark organelles enlighten endosomal membrane transport. *Nat Rev Mol Cell Biol* 8:786–797. <https://doi.org/10.1038/nrm2258>
- Ratcliffe NA, Gagen SJ (1977) Studies on the in vivo cellular reactions of insects: an ultrastructural analysis of nodule formation in *Galleria mellonella*. *Tissue Cell* 9:73–85. [https://doi.org/10.1016/0040-8166\(77\)90050-7](https://doi.org/10.1016/0040-8166(77)90050-7)
- Ratcliffe NA, Whitten MMA (2004) Vector immunity in microbe-vector interactions. In: Gillespie SH, Osbourn A, Smith GL (eds) *Vector-borne diseases*. SGM symposium, pp 199–262
- Rogalla S, Patil A, Dhinojwala A, Shawkey MD, D'Alba L (2021) Enhanced photothermal absorption in iridescent feathers. *J R Soc Interface* 18(181):20210252
- Rogers CS, Astrop TI, Webb SM, Ito S, Wakamatsu K, McNamara ME (2019) Synchrotron X-ray absorption spectroscopy of melanosomes in vertebrates and cephalopods: implications for the affinity of Tullimonstrum. *Proc R Soc B* 286(1913):20191649
- Rossi V, McNamara ME, Webb SM, Ito S, Wakamatsu K (2019) Tissue-specific geometry and chemistry of modern and fossilized melanosomes reveal internal anatomy of extinct vertebrates. *Proc Natl Acad Sci* 116(36):17880–17889
- Roulin A, Maffi A, Wakamatsu K (2013) Reptiles produce pheomelanin: evidence in the eastern Hermann's tortoise (*Eurotestudo boettgeri*). *J Herpetol* 47(2):258–261
- Schraermeyer U (1994) Fine structure of melanogenesis in the ink sac of *Sepia officinalis*. *Pigment Cell Res* 7(1):52–60
- Shawkey MD, Hill GE (2006) Significance of a basal melanin layer to production of non-iridescent structural plumage color: evidence from an amelanotic Steller's jay (*Cyanocitta stelleri*). *J Exp Biol* 209(7):1245–1250
- Shawkey MD, Morehouse NI, Vukusic P (2009) A protean palette: colour materials and mixing in birds and butterflies. *J R Soc Interface* 6(Suppl 2):S221–S231. <https://doi.org/10.1098/rsif.2008.0459.focus>
- Shawkey MD, D'Alba L, Xiao M, Schutte M, Buchholz R (2015) Ontogeny of an iridescent nanostructure composed of hollow melanosomes. *J Morphol* 276:378–384. <https://doi.org/10.1002/jmor.20347>
- Shawkey MD, Igc B, Rogalla S, Goldenberg J, Clusella-Trullas S, D'Alba L (2017) Beyond colour: consistent variation in near infrared and solar reflectivity in sunbirds (Nectariniidae). *Sci Nat* 104:1–5
- Simon JD, Peles DN (2010) The red and the black. *Acc Chem Res* 43(11):1452–1460

- Simon JD, Goldsmith MR, Hong L, Kempf VR, McGuckin LE, Ye T, Zuber G (2006) Spectroscopy and photoreactivity of trichochromes: molecular components of pheomelanins. *Photochem Photobiol* 82(1):318–323
- Simon JD, Hong L, Peles DN (2008) Insights into melanosomes and melanin from some interesting spatial and temporal properties. *J Phys Chem B* 112(42):13201–13217
- Singh SK, Nizard C, Kurfurst R, Bonte F, Schnebert S, Tobin DJ (2008) The silver locus product (Silv/gp100/Pmel17) as a new tool for the analysis of melanosome transfer in human melanocyte-keratinocyte co-culture. *Exp Dermatol* 17:418–426. <https://doi.org/10.1111/j.1600-0625.2008.00702.x>
- Sköld HN, Aspengren S, Wallin M (2013) Rapid color change in fish and amphibians – function, regulation, and emerging applications. *Pigment Cell Melanoma Res* 26(1):29–38. <https://doi.org/10.1111/pcmr.12040>
- Speiser DI, DeMartini DG, Oakley TH (2014) The shell-eyes of the chiton *Acanthopleura granulata* (Mollusca, Polyplacophora) use pheomelanin as a screening pigment. *J Nat Hist* 48:2899–2911
- Stanic V, Maia FCB, de Oliveira Freitas R, Montoro FE, Evans-Lutterodt K (2018) The chemical fingerprint of hair melanosomes by infrared nano-spectroscopy. *Nanoscale* 10(29):14245–14253
- Stavenga DG, Leertouwer HL, Hariyama T, Raedt HAD, Wilts BD (2012) Sexual dichromatism of the damselfly *Calopteryx japonica* caused by a melanin-chitin multilayer in the male wing veins. *PLoS One* 7
- Stavenga DG, Leertouwer HL, Osorio DC, Wilts BD (2015) High refractive index of melanin in shiny occipital feathers of a bird of paradise. *Light: Sci Appl* 4:e243
- Thureau P, Ziarelli F, Thévand A, Martin RW, Farmer PJ, Viel S, Mollica G (2012) Probing the motional behavior of eumelanin and pheomelanin with solid-state NMR spectroscopy: new insights into the pigment properties. *Chem Eur J* 18(34):10689–10700
- Tian S, Garcia-Rivera J, Yan B, Casadevall A, Stark RE (2003) Unlocking the molecular structure of fungal melanin using ¹³C biosynthetic labeling and solid-state NMR. *Biochemistry* 42(27):8105–8109
- Vopalensky P, Kozmik Z (2009) Eye evolution: common use and independent recruitment of genetic components. *Philos Trans R Soc B* 364:2819–2832
- Wakamatsu K, Nagao A, Watanabe M, Nakao K, Ito S (2017) Pheomelanogenesis is promoted at a weakly acidic pH. *Pigment Cell Melanoma Res* 30:372–377. <https://doi.org/10.1111/pcmr.12587>
- Wang Z, Guo Z (2017) Biomimetic superwetttable materials with structural colours. *Chem Commun* 53(97):12990–13011
- Whitten MM, Coates CJ (2017) Re-evaluation of insect melanogenesis research: views from the dark side. *Pigment Cell Melanoma Res* 30(4):386–401
- Wolbarsht ML, Walsh AW, George G (1981) Melanin, a unique biological absorber. *Appl Opt* 20(13):2184–2186
- Wolf BO, Walsberg GE (2000) The role of the plumage in heat transfer processes of birds. *Am Zool* 40(4):575–584
- Wolnicka-Glubisz A, Pecio A, Podkowa D, Kolodziejczyk LM, Plonka PM (2012) Pheomelanin in the skin of *Hymenochirus boettgeri* (Amphibia: Anura: Pipidae). *Exp Dermatol* 21(7):537–540
- Wu X, Hammer JA (2014) Melanosome transfer: it is best to give and receive. *Curr Opin Cell Biol* 29:1–7. <https://doi.org/10.1016/j.ceb.2014.02.003>
- Wu XS, Martina JA, Hammer JA III (2012) Melanoregulin is stably targeted to the melanosome membrane by palmitoylation. *Biochem Biophys Res Commun* 426(2):209–214
- Xiao M, Dhinojwala A, Shawkey M (2014) Nanostructural basis of rainbow-like iridescence in common bronzing Phaps chalcoptera feathers. *Opt Express* 22:14625
- Xiao M, Li Y, Allen MC, Deheyn DD, Yue X, Zhao J, Gianneschi NC, Shawkey MD, Dhinojwala A (2015) Bio-inspired structural colors produced via self-assembly of synthetic melanin nanoparticles. *ACS Nano* 9:5454–5460

- Xiao M, Hu Z, Wang Z, Li Y, Tormo AD, Le Thomas N, Wang B, Gianneschi NC, Shawkey MD, Dhinojwala A (2017) Bioinspired bright noniridescent photonic melanin supraballs. *Sci Adv* 3(9):e1701151
- Xing L, Sun L, Liu S, Li X, Miao T, Zhang L, Yang H (2017) Comparison of pigment composition and melanin content among white, light-green, dark-green, and purple morphs of sea cucumber, *Apostichopus japonicus*. *Acta Oceanol Sin* 36:45–51
- Zhao H, Yang H, Zhao H, Liu S, Wang T (2012) Differences in MITF gene expression and histology between albino and normal sea cucumbers (*Apostichopus japonicus* Selenka). *Chin J Oceanol Limnol* 30(1):80
- Zonios G, Dimou A, Bassukas I, Galaris D, Tsolakidis A, Kaxiras E (2008) Melanin absorption spectroscopy: new method for noninvasive skin investigation and melanoma detection. *J Biomed Opt* 13(1):014017

Biotechnological Production of Melanins with Recombinant Microorganisms



Luz María Martínez, Alejandro Miguel Cisneros-Martínez,
Georgina Hernández-Chávez, Alfredo Martínez, and Guillermo Gosset

1 Introduction

Melanins are a family of polymeric pigments that are abundantly present in nature (d'Ischia et al. 2015). These polymers are the end products of the enzymatic oxidation of phenolic or indolic substrates. Additionally, it is thought that some of the oldest pigments found in nature are melanins, since this type of compound has been found in dinosaur and bird fossils (Zhang et al. 2010). Furthermore, intact melanin was also found in Jurassic-era squid ink sacs (Glass et al. 2012). Therefore, melanin has been proposed as a biomarker in the study of evolution (Wogelius et al. 2011). The four main types of melanin are eumelanin, pheomelanin, allomelanins, and pyomelanin. Eumelanin is produced by the oxidation of the amino acid L-tyrosine and/or L-dihydroxyphenylalanine (L-DOPA), resulting in a brown or black polymer. Alternatively, pheomelanin is formed when L-tyrosine and/or L-DOPA are oxidized in the presence of L-cysteine, resulting in a red-yellow pigment. Moreover, the oxidation of 4-hydroxyphenylacetic acid, catechols, dihydroxynaphthalene (DHN), -glutaminy-4-hydroxybenzene, protocatechualdehyde, or tetrahydroxynaphthalene results in the formation of allomelanins. Finally, a particular kind of melanin called pyomelanin is produced when homogentisic acid is oxidized (HGA) (Fig. 1) (Lindgren et al. 2015).

Due to their chemical makeup, melanins exhibit unique physicochemical features, allowing them to function as cation exchangers, amorphous semiconductors,

L. M. Martínez · G. Hernández-Chávez · A. Martínez · G. Gosset (✉)

Departamento de Ingeniería Celular y Biotecnología, Instituto de Biotecnología, Universidad Nacional Autónoma de México, Cuernavaca, Morelos, Mexico
e-mail: gosset@ibt.unam.mx

A. M. Cisneros-Martínez

Departamento de Ecología Evolutiva, Instituto de Ecología, Universidad Nacional Autónoma de México, Ciudad de México, Mexico

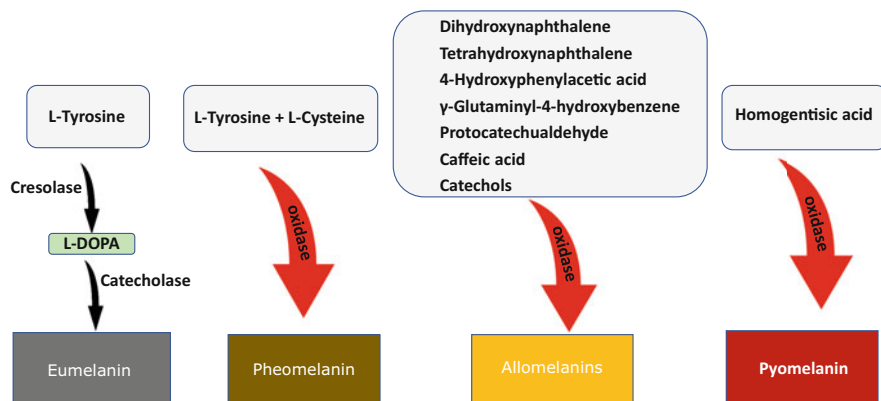


Fig. 1 Biochemical reactions that lead to the synthesis of eumelanin, pheomelanin, allomelanins and pyomelanin

X-ray, γ -ray, and ultraviolet light absorbers (della-Cioppa et al. 1990; Krol and Liebler 1998; Rózanowska et al. 1999; Sarna et al. 1976; Ambrico et al. 2014). Additionally, it has been demonstrated that melanins contain antioxidant and antiviral properties (Nofsinger et al. 2002; Montefiori and Zhou 1991). Therefore, the ability to obtain these polymers in large quantities and at an affordable cost is necessary for the creation of a variety of valuable products and applications. Melanins can be chemically produced or isolated from animal and plant tissues. Nevertheless, these procedures can be rather expensive and are occasionally not sustainable (Saini and Melo 2015). An innovative and viable alternative to obtaining melanins is based on the development of biotechnological processes that use melanogenic microorganisms. Two advantages of this approach are its scalability and good yields for melanin production. Furthermore, this strategy can be strengthened by using genetic engineering techniques to boost the inherent melanogenic potential of some organisms or by creating new melanin-producing strains. In this context, the expression of genes encoding the enzymes involved in the oxidation of melanin precursors is the most typical genetic modification used to improve or generate a production strain (Martínez et al. 2019).

2 Enzymes Involved in Melanin Formation: Classification and Evolution

The initial process leading to the production of melanins is the enzyme-dependent oxidation of phenolic or indolic chemicals. Tyrosinases are the most common type of enzyme associated with melanogenesis. Tyrosinases are copper enzymes that catalyze both the ortho-hydroxylation of monophenols (cresolase activity) and the oxidation of catechols (catecholase activity), generating ortho-quinone products

(Garcia-Molina et al. 2007) (Fig. 1). More specifically, the enzyme tyrosinase catalyzes the hydroxylation of L-tyrosine to L-DOPA using molecular oxygen and then oxidizes this compound to dopachrome, which in turn nonenzymatically polymerizes to yield melanin (Ito 2003).

Copper proteins are classified into three categories according to their spectroscopic and structural properties. These are (1) mononuclear type-1 or blue copper proteins, which are mostly involved in electron transfer; (2) type-2 or non-blue copper proteins, typically found in enzymes that activate molecular oxygen and; (3) type-3 or binuclear copper proteins, which are part of the Di-copper superfamily or clan (CL0205) which includes phenoloxidases (i. e. tyrosinases and catechol oxidases) and hemocyanins (Jaenicke and Decker 2004; Aguilera et al. 2013; Kaintz et al. 2014). Phenoloxidases are enzymes involved in the oxidation of phenolic compounds. On the one hand, catechol oxidases have diphenolase activity, while on the other hand, tyrosinases are bifunctional enzymes with monophenolase and diphenolase activities (Aguilera et al. 2013; Kaintz et al. 2014). Hemocyanins are oxygen carriers found in arthropods and mollusks, although some may also have weak phenoloxidase activity (van Holde et al. 2001).

Type-3 copper proteins bind oxygen through two copper atoms (CuA and CuB) whose oxidation state changes from Cu^+ (reduced) to Cu^{2+} (oxidized) upon oxygen binding. Each Cu atom is coordinated by three histidine residues provided by two pairs of α helices, forming a four α helix bundle motif (Jaenicke and Decker 2004). The CuA binding site is typically characterized by an H1(n)-H2(8)-H3 motif and the CuB binding site by an H1(3)-H2(n)-H3 motif, where n is a variable number of residues between histidines (Aguilera et al. 2013). Sequence differences in the copper binding sites and domain architecture have been used as criteria for the classification of these proteins into three subclasses: (1) α -subclass with N-terminal signal peptide, suggesting secretion or vesicle localization (includes tyrosinases in the three domains of life, plant catechol oxidases and molluscan and urochordate hemocyanins); (2) β -subclass without a signal peptide and, therefore, presumably localized in the cytosol (includes arthropod tyrosinases and hemocyanins) and; (3) γ -subclass with a signal peptide, which is a cysteine-rich region upstream of the binuclear copper center and a transmembrane domain downstream of the binuclear copper center (includes various metazoan tyrosinases such as human ones) (Aguilera et al. 2013). Among these, the β -subclass appears as the most evolutionary divergent group, presenting a motif variation in the CuA binding site as H1(2)-H2(n)-H3 (Aguilera et al. 2013) (Fig. 2).

The presence of type-3 copper proteins in the three domains of life suggests an early origin probably dating back to the times of the last universal common ancestor to all cellular life (LUCA) (Jaenicke and Decker 2004; Aguilera et al. 2013) (Fig. 2), where a common ancestral protein with a mononuclear copper center (probably CuB binding site) duplicated resulting in a protein with a binuclear copper center (CuB + CuA binding sites) from which all type-3 copper proteins evolved. This ancestral protein may have protected primitive organisms from increasing levels of oxygen, which began to accumulate 3.5 billion years ago as a byproduct of photosynthesis (van Holde et al. 2001; Jaenicke and Decker 2004).

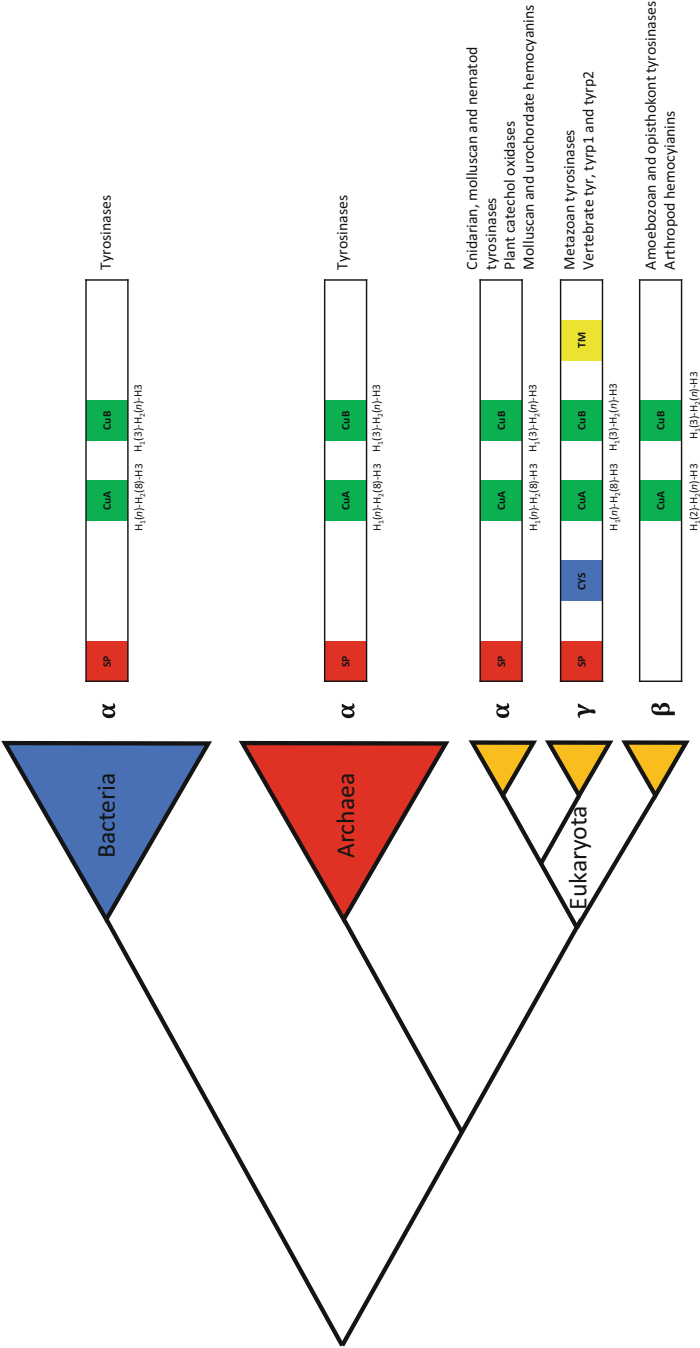


Fig. 2 Schematic representation of the taxonomic distribution of type-3 copper proteins. Domain architectures and sequence motifs characteristic of each subclass are represented to the right, as well as the type of enzymes present in each of them. SP signal peptide, CYS cysteine-rich region, CuA copper binding site A, CuB copper binding site B, TM transmembrane domain. The Eukaryota branch represents the branching order of α , β , and γ type-3 copper proteins. See the text for further detail on the taxonomic distribution and evolutionary processes related to type-3 copper proteins

Phylogenetic analyses have shown that type-3 copper proteins have a complex evolutionary history including multiple lineage-specific gene expansions and losses. Given the wide distribution of α -subclass proteins, it has been hypothesized that the first type-3 copper proteins belonged to this group. β and γ -subclasses appear to have originated from gene duplication within the Eukaryota domain. Among these, the most ancient one is the β -subclass, which seems to have originated before the divergence of amoebozoan and opisthokont lineages (present in amoebae, fungi, and some animals) where they lost the signal peptide and their sequences began to diverge at the CuA binding site. More recently, γ -subclass appears to have originated within the metazoan lineage (only found in animals), where they acquired the cysteine-rich region and the transmembrane domain (Aguilera et al. 2013) (Fig. 2).

Metazoan tyrosinases are mainly members of the γ -subclass (where α and β -subclass tyrosinases were lost); although α -subclass tyrosinases are maintained in Cnidaria, Nematoda and Mollusca; whereas β -subclass tyrosinases are found in Porifera, Urochordata, and Arthropoda. Regarding hemocyanins, α -subclass hemocyanins were probably duplicated before the divergence of bilaterians but were lost in most lineages except for urochordates and molluscs, whereas β -subclass hemocyanins were duplicated more recently within the Arthropoda lineage (van Holde et al. 2001; Aguilera et al. 2013). Although metazoans are the only kingdom that possesses proteins from the α , β , and γ -subclasses, gene loss has occurred to such an extent that *Ciona intestinalis* is the only organism possessing the three types in its genome (α -subclass hemocyanin and, β and γ -subclass tyrosinases) (Aguilera et al. 2013).

In vertebrates, in addition to tyrosinase, two tyrosinase-related proteins are also involved in different steps of melanin biosynthesis: tyrosinase-related protein-1 (tyrp1) and tyrosinase-related protein-2 (tyrp2) also known as DOPAchrome tautomerase (dct). These two enzymes influence the quantity and quality of melanins produced and are involved in the stabilization of the tyrosinase structure (Esposito et al. 2012). Phylogenetic analyses suggest a duplication event before the divergence of urochordates and vertebrates resulting in tyrosinases and a tyrosinase-related protein, and a second duplication event before the divergence of teleost fishes gave rise to the two tyrosinase-related proteins tyrp1 and tyrp2. Interestingly, it may be possible that these enzymes do not coordinate Cu atoms at the metal binding sites, as tyrp2 is known to coordinate two zinc atoms instead (Esposito et al. 2012).

To the best of our knowledge, the evolution of bacterial and archaeal tyrosinases has not been extensively explored. Thus, for the time being, a tentative scheme proposes at least three unambiguous types of bacterial tyrosinases based on their domain architecture. For example, the first type includes the well-studied tyrosinases from *Streptomyces* sp. which are produced as a heterodimer where tyrosinase (*melC2* gene product) is bound to a caddy protein (*melC1* gene product) involved in heterodimer secretion and delivery of copper atoms to the active site of tyrosinase. A second type is not associated with a caddy protein for copper incorporation and includes tyrosinases such as that of *Bacillus megaterium*. Finally, a third type includes tyrosinases produced as zymogens that, similarly to plant and fungal tyrosinases catechol oxidases, require proteolytic removal of a C-terminal domain

for activation (Fairhead and Thöny-Meyer 2012; Pretzler and Rompel 2018). Interestingly, a preliminary analysis performed in our group suggests that tyrosinases from plant-associated bacteria (e. g. those from *Rhizobium etli* or *Ralstonia solanacearum*) are more closely related to plant catechol oxidases, which implies horizontal gene transfers that would further increase the complexity of the already intricate evolutionary history of this protein family. Additionally, a cold-adapted tyrosinase from the archaeon *Candidatus Nitrosopumilus koreensis* is distinct from other known bacterial tyrosinases (Kim et al. 2016).

Despite efforts to classify type-3 copper proteins based on their domain architecture, conserved sequence motifs, and tertiary structure elements, it is still unclear what changes have driven the functional differentiation of these proteins throughout evolution. However, besides the six conserved histidines, mutagenesis studies have shed some light on some amino acids of great catalytic importance that could explain the functional differentiation between catechol oxidases and tyrosinases. These include a variable gatekeeper residue which may support or inhibit substrate entry; a waterkeeper residue (Glu for tyrosinase activity) required to maintain a stable water network around the active center; variable residues (Asn and Asp for tyrosinase activity) one position ahead of the first and second histidines in CuB copper binding site, which are involved in increased basicity of adjacent histidines required for substrate deprotonation; a thioether bond (absent in tyrosinases) between a cysteine residue and the second histidine in the CuA copper binding site, which upon breaking allows the histidine to move more freely within the active site where it can also intervene in substrate deprotonation and; a seventh histidine one position before the third histidine in the CuB copper binding site and disulfide bonds that may stabilize the enzyme's catalytic activity (Kampatsikas and Rompel 2021).

Lacasses are another group of enzymes involved in melanogenesis. These enzymes which have been found in bacteria, fungi, and plants, are not related to tyrosinases but are also copper-dependent oxidoreductases (Valderrama et al. 2003). For example, the enzyme 4-hydroxyphenylacetic acid (4-HPA) hydroxylase is involved in the catabolism of 4-HPA in bacteria. This enzyme is a two-component flavin adenine dinucleotide (FAD)-dependent monooxygenase (Gibello et al. 1995). This group of enzymes displays a broad substrate range, they can hydroxylate various monohydric and dihydric phenols (Prieto et al. 1993).

3 Production of Melanins with Genetically Engineered Microorganisms

3.1 Eumelanin Production

The ability to obtain these pigments from plentiful and affordable sources is a prerequisite for the current and future uses of melanin. By using relatively simple procedures, these products can be recovered from natural sources such as the tissues

of animals or plants. However, the mixture of various melanin types and related compounds found in these sources frequently makes purifying processes difficult and could result in a product with varied compositions. Furthermore, these polymers can be produced chemically or enzymatically by oxidizing phenolic or indolic substrates (Saini and Melo 2015). These processes can produce melanins that are highly pure, but they come at a high price (d'Ischia et al. 2015). Alternatively, culturing melanin-producing microorganisms or microbes that have been genetically modified to produce melanin is another method for obtaining these polymers. This last method allows for the production of melanins at a high yield and relatively low cost.

The experimental procedures collectively referred to as “genetic engineering” allow altering the genetic make-up of bacteria to increase or give them the capacity to generate chemicals. An increasing number of microbes may be genetically engineered for producing melanin, and the identification of individual genes and melanin-producing pathways has been possible through the application of DNA sequencing technologies in conjunction with biochemical investigations. This knowledge and technologies are the basis for creating recombinant microbes with improved melanin production and the capacity to transfer this capability to non-melanogenic bacteria.

The latest developments in the design of recombinant microbial strains and the production techniques used for the synthesis of melanins are reviewed and analyzed in the following sections. The bacterium *Escherichia coli* was the first documented recombinant melanogenic microbe. Genes from the actinomycete *Streptomyces antibioticus* were altered to be expressed in *E. coli*. The two genes in question, *mel* and ORF438 at the *mel* locus in *S. antibioticus* are necessary for the synthesis of melanin. In agar plates and liquid cultures, the recombinant *E. coli* strain was capable of producing eumelanin from L-tyrosine. Furthermore, it has been demonstrated that the *S. antibioticus* tyrosinase enzyme could use synthetic, non-natural amino acids such N-acetyl-L-tyrosine and L-tyrosine ethyl ester, as substrates, to produce synthetic melanins (Della-Cioppa et al. 1990). In a different report, a recombinant *E. coli* strain derived from JM109 was created using the *mel* locus from *S. antibioticus*. In this case, the phage T5 promoter and two *lac* operators were used to control the expression of the *mel* gene. The resulting recombinant strain was cultivated in LB medium, producing 0.4 g/L of eumelanin (Table 1). Eumelanin was removed from the culture medium by precipitation at a pH of 3.0, followed by dissolution at a pH of 8.0 in distilled water. Afterward, liquid chromatography on Sephadex LH-20 was performed. To investigate how the presence of this polymer affected the antibacterial activity of several antibiotics, pure eumelanin was used. It was found that eumelanin dose-dependently decreased the antibacterial effect of ampicillin, kanamycin, polymyxin B, and tetracycline against *E. coli* (Lin et al. 2005). In addition to the potential therapeutic significance of such data, the observed results could be used to select for greater melanin-producing recombinant strains based on antibiotic resistance.

Another early study demonstrated that the *Bacillus thuringiensis* strain 4D11 was able to produce melanin when cultivated with L-tyrosine at 42 °C (Ruan et al. 2004).

Table 1 Engineered microbial strains used in the production of melanin

Promoter	Inducer	Expressed gene(s)	Expression vectors	Genes source	Production microorganism	Melanin precursor	Carbon source	T (°C)	Q _M (mg/L/h)	Titer (g/L)	Reference
<i>Lac</i>	Not reported	<i>Mel</i>	pGEM-7Zf	<i>Bacillus thuringiensis 4D11</i>	<i>Escherichia coli</i>	Casein	Casein	NR	155.5	5.6	Ruan et al. 2005
T5	IPTG 0.36 mM	<i>Mel</i>	pQE32	<i>Streptomyces antibioticus</i>	<i>Escherichia coli</i>	L-tyrosine	LB medium	37	8.3	0.4	Lin et al. 2005
<i>Trc</i>	IPTG 0.1 mM	<i>MumelA</i>	pTrec99A	<i>Rhizobium etli</i>	<i>Escherichia coli</i>	L-tyrosine	Glucose	30	75	6	Lagunas-Muñoz et al. 2006
None	None	None	None	<i>Pseudomonas putida</i> strain F6	<i>Pseudomonas putida</i> strain F6-HDO	L-tyrosine	Citrate	30	17.5	0.35	Nikodinovic-Runic et al. 2009
P _{kinel}	Constitutive	<i>melC</i>	pU86	<i>Streptomyces kathirae</i>	<i>Streptomyces kathirae</i>	L-tyrosine	Amylodextrine, yeast extract	28	225	28.8	Guo et al. 2015
None	None	Not identified	None	<i>Escherichia coli</i>	<i>Escherichia coli</i>	Caffeic acid	Glucose	30	16.7	0.15	Jang et al. 2018
T7	IPTG 1 mM	<i>Fcs</i>	pRSF duet-1 pET duet-1	<i>Burkholderia glumae</i> BGR1	<i>Escherichia coli</i>	Caffeic acid	Glucose	30	NR	0.20	Jang et al. 2018
T7	IPTG 1 mM	<i>Ech</i>	pRSF duet-1 pET duet-1	<i>Burkholderia glumae</i> BGR1	<i>Escherichia coli</i>	*					Jang et al. 2018
pBAD	Arabinose 0.1 %	<i>Hpd</i>	pVO	<i>Pseudomonas auruginosa</i> PAO1	<i>Escherichia coli</i>	CAA L-tyrosine	Glucose	37	NR	0.213	Bolognese et al. 2019
T7	IPTG 0.25 mM	<i>Hppd</i>	pET-28a(+)	<i>Ralstonia pickettii</i>	<i>Escherichia coli</i>	L-tyrosine	Glucose	30	13.1	0.315	Seo and Choi 2020
T7	IPTG 1 mM	<i>Hpd</i>	pET-21a(+)	<i>Flavobacterium kingsejongii</i>	<i>Escherichia coli</i>	L-tyrosine	NR	30	40	3.76	Lee et al. 2022
pTEF	None	<i>4HPPD</i>	Chromosome	<i>Yarrowia lipolytica</i>	<i>Yarrowia lipolytica</i>	None	Glucose	28	NR	4.5	Larroude et al. 2021

T7	IPTG 0.25 mM	<i>melC</i>	pET-24a(+)	<i>Bacillus megaterium</i>	<i>Escherichia coli</i>	L-tyrosine and L-tryptophan	NR	30	100	3.5	Park et al. 2020
T7	IPTG 0.25 mM	<i>cyp102G4</i>	pETDuet-1	<i>Streptomyces catleya</i>	<i>Escherichia coli</i>	L-tyrosine and L-tryptophan	NR	30			Park et al. 2020
T7	IPTG 0.1 mM	<i>TAL</i>	pRSFduet-1	<i>Rhodotorula glutinis</i>	<i>Escherichia coli</i>	Caffeic acid, L-tyrosine and L-lysine	NR	30	NR		Ahn et al. 2021
T7	IPTG 0.1 mM	<i>C3H</i>	pRSFDuet-1	<i>Saccharothrix espanaensis</i>	<i>Escherichia coli</i>	*					Ahn et al. 2021
T7	IPTG 0.1 mM	<i>FCS</i>	pETDuet-1	<i>Burkholderia glumae</i>	<i>Escherichia coli</i>	*					Ahn et al. 2021
T7	IPTG 0.1 mM	<i>ECH</i>	pETDuet-1	<i>Burkholderia glumae</i>	<i>Escherichia coli</i>	*					Ahn et al. 2021
T7	IPTG 0.1 mM	<i>melC</i>	pACYCDuet-1	<i>Bacillus megaterium</i>	<i>Escherichia coli</i>	*					Ahn et al. 2021
T7	IPTG 0.1 mM	<i>GadA</i>	pACYCDuet-1	<i>Klebsiella pneumoniae</i>	<i>Escherichia coli</i>	*					Ahn et al. 2021
<i>Lac</i>	IPTG 0.1 mM	<i>aroG^{hbr}</i>	pTtrc99A	<i>Escherichia coli</i>	<i>Escherichia coli</i>	None	Glucose	30	26.8	3.2	Chávez-Béjar et al. 2013
<i>Trc</i>	IPTG 0.1 mM	<i>tyrC</i>	pTtrc99A	<i>Zymomonas mobilis</i>	<i>Escherichia coli</i>	*					Chávez-Béjar et al. 2013
<i>Trc</i>	IPTG 0.1 mM	<i>pheA_{CM}</i>	pTtrc99A	<i>Escherichia coli</i>	<i>Escherichia coli</i>	*					Chávez-Béjar et al. 2013
<i>Trc</i>	IPTG 0.1 mM	<i>MumelA</i>	pTtrc99A	<i>Rhizobium etli</i>	<i>Escherichia coli</i>	*					Chávez-Béjar et al. 2013
<i>Lac</i>	IPTG 0.1 mM	<i>aroG^{hbr}</i>	pTtrc99A	<i>Escherichia coli</i>	<i>Escherichia coli</i>	None	Glycerol	30	16.8	1.21	Mejía-Caballero et al. 2016
<i>PtkA</i>	None	<i>tkiA</i>	pTtrc99A	<i>Escherichia coli</i>	<i>Escherichia coli</i>	*					Mejía-Caballero et al. 2016

(continued)

Table 1 (continued)

Promoter	Inducer	Expressed gene(s)	Expression vectors	Genes source	Production microorganism	Melanin precursor	Carbon source	T (°C)	Q _M (mg/L/h)	Titer (g/L)	Reference
<i>Trc</i>	IPTG 0.1 mM	<i>antABC</i>	pTrc99A	<i>Pseudomonas aeruginosa</i> PAOI	<i>Escherichia coli</i>	*					Mejía-Caballero et al. 2016
<i>Trc</i>	IPTG 0.1 mM	<i>MumelA</i>	pTrc99A	<i>Rhizobium etli</i>	<i>Escherichia coli</i>	*					Mejía-Caballero et al. 2016

Q_M Volumetric productivity, NR not reported
*Only the first line of each example provides production data, the rest of the lines indicate the types of genetic modifications performed in the production strain

These findings suggested that in the genome of this organism there should be a gene encoding for tyrosinase. Considering that the genome sequence of *B. thuringiensis* 4D11 was unknown, a cloning technique was then developed based on the predicted sequence similarities with a tyrosinase gene from *Bacillus cereus* 10987. Based on the tyrosinase gene sequence from *B. cereus* 10987, a set of PCR primers was created and used to amplify an 1179 bp DNA fragment from *B. thuringiensis* 4D11 DNA. This DNA fragment shared 99% of its encoded amino acid sequence with the tyrosinase from *B. cereus* 10987. The *lac* promoter was used to express the PCR product in plasmid pGEM-7zf. This plasmid was then used to transform *E. coli* DH5. The resulting recombinant strain produced eumelanin at a titer of 5.6 g/L when cultured in a casein liquid medium (Table 1). Intriguingly, it was found that in trials involving exposure to UV radiation, this recombinant strain outperformed DH5 in terms of survival rates (Ruan et al. 2005). These findings demonstrate how, in addition to enabling the biotechnological production of melanin, the heterologous expression of a gene encoding a tyrosinase might improve the host's UV radiation resistance, a characteristic that might be advantageous in the case of microorganisms used in the field, such as *B. thuringiensis*. Moreover, microorganisms that can endure intense UV exposure could be of benefit in future long-term space missions and planet-colonization initiatives, as microbes are thought to be crucial to help maintain human existence by producing food, valuable compounds, and recycling trash (Horneck et al. 2010; <https://blogs.scientificamerican.com/observations/microbes-might-be-key-to-a-mars-mission/>). Furthermore, melanin can absorb X and γ rays, which may help engineered bacteria survive in conditions outside of our planet.

Rhizobium etli, a soil bacterium, is particularly significant for agriculture, as it can fix nitrogen by forming nodules in the roots of *Phaseolus vulgaris* plants. This bacterium can also synthesize melanin in the symbiotic nodules through a symbiotic plasmid that contains a gene encoding tyrosinase (*mela*) (González et al. 2003; Piñero et al. 2007). The expression vector pTrc99A was used to clone the *mela* gene under the strong *trc* promoter, resulting in pTrcmela, which was used to transform *E. coli*. When L-tyrosine was used as a substrate, the recombinant *E. coli* strain was able to produce eumelanin at 30 °C, yet, increasing the temperature to 37 °C significantly lowered melanin yields (Cabrera-Valladares et al. 2006). Moreover, it was also discovered that melanin production occurred only in the stationary culture phase and, when compared to other colonies, a recombinant *E. coli* colony on media containing L-tyrosine showed a deeper color. Following DNA sequencing of this clone's *mela* gene, it was discovered that it had undergone a spontaneous mutation, changing the Asp535 residue in the MelA tyrosinase enzyme to a Gly residue. Therefore, MutMelA was the name given to this mutant version of MelA. When compared to a strain that expresses the wild-type enzyme, it was observed that eumelanin synthesis in liquid cultures begins sooner in cultures of *E. coli* expressing *Mutmela*. A study was performed to find the best conditions for pigment synthesis in liquid cultures utilizing a recombinant *E. coli* strain expressing *Mutmela*. The influence of culture temperature, pH, isopropyl-d-thio-galactopyranoside (IPTG) as a gene inducer, antibiotic concentration for plasmid selection pressure, and eumelanin concentration was assessed. It was found that the ideal bioreactor

conditions were: 0.1 mmol/L of IPTG, a culture temperature of 30 °C, and a change in medium pH from 7.0 to 7.5 at the beginning of the eumelanin production phase. Additionally, L-tyrosine was added to the culture medium at 6 g/L as a eumelanin precursor. With a final titer of 6 g/L under these conditions, a 100% conversion yield of L-tyrosine to eumelanin was observed (Table 1) (Lagunas-Muñoz et al. 2006). These findings emphasize the significance of optimizing culture conditions as a factor in achieving the highest yield and productivity while using a recombinant melanogenic strain.

As part of a bioprospecting investigation, microorganisms capable of producing melanin were identified from soil samples in China. Among these isolates, *Streptomyces kathirae* SC-1 had the best potential for melanin synthesis among all isolates. Employing this organism and a surface response approach to enhance the medium and growth conditions, 13.7 g/L of melanin was produced (Guo et al. 2014). It is significant to note that yeast extract, which provides a variety of melanin precursors, was a component of the culture medium used in this investigation. Therefore, to identify the type of melanin generated, the resultant polymer needs to be analyzed to ascertain its chemical makeup. To provide further light on this organism's melanogenesis process, a tyrosinase was homogeneously purified, which is a 30-kDa enzyme (called tyrosinase MelC) that has a K_m of 0.42 mM for L-DOPA and 0.25 mM for L-tyrosine. The primers used to amplify the *melC* gene and its promoter region were designed using the partial amino acid sequence of this tyrosinase. Two potential promoters, Pskmel and P135, were discovered by sequence analysis. In the replicative plasmid pIJ86, the gene *melC* was cloned under the transcriptional control of either the putative promoter or the constitutive promoter PermE*. The resultant constructs were then transformed into *S. lividans* and *S. kathirae*. After characterizing the recombinant strains of *S. lividans*, it was demonstrated that Pskmel is the functional promoter for *melC*. *S. kathirae* recombinant strains that were grown in melanin-producing conditions. It was also found that the amounts of melanin generated by strains expressing *melC* from PermE* or Pskmel were 24.9 and 28.8 g/L, respectively (Table 1) (Guo et al. 2015). It should be emphasized that these are the highest reported melanin titers, showing the possibility of using genetic engineering methods to significantly increase a melanogenic organism's production capability (Table 1). This manufacturing method can be further optimized, particularly in terms of the culture medium composition, as yeast extract, at the concentration used in the referenced work (37 g/L), becomes a costly ingredient. Moreover, some of the components of yeast extract can interact with melanin precursors to produce a polymer that isn't completely derived from L-tyrosine. To enhance the existing manufacturing method, future research should aim at finding a growth medium that only contains salts and a simple carbon source.

3.2 Pyomelanin Production

When cultured on a medium containing L-tyrosine, the soil bacterium *Pseudomonas putida* strain F6 exhibits the ability to produce a dark pigment. Thus, transposon mutagenesis was done to learn more about the function of the genes involved in the production of this pigment. Two mutants with improved synthesis were obtained by this approach. When compared to *P. putida* F6, one of these mutants (F6-HDO) generated 0.35 g/L of the pigment, which was identified as a type of melanin (Table 1). It is interesting to note that, when compared to the wild-type strain, this mutant showed greater resistance to UV radiation and H₂O₂. Genetic testing revealed that a gene encoding HGA 1,2-dioxygenase (HGO) was disrupted by transposon mutagenesis. This enzyme participates in the degradation process that turns HGA into 4-maleylacetoacetate. As a result, it is expected that this mutation will cause HGO to use less HGA. This finding suggests that in this mutant strain, HGA is the pyomelanin precursor (Fig. 3) (Nikodinovic-Runic et al. 2009). Precursors for HGA synthesis originate from the L-tyrosine biosynthetic pathway. Furthermore, the enzyme hydroxyphenylpyruvate dehydrogenase (HPPD) converts the intermediate 4-hydroxyphenylpyruvate (HPP) into HGA (Fig. 3).

A recombinant strain of *E. coli* for pyomelanin production was developed by cloning the chromosomal *hpd* gene that encodes the 4 hydroxyphenylpyruvate dioxygenase from *Pseudomonas auruginosa* PAO1, and then placing it in the pVO vector under transcriptional control of the arabinose promoter pBAD. A biotransformation protocol for pyomelanin synthesis with the recombinant *E. coli* strain was developed by defining the parameters influencing growth and production. The optimal growth conditions were determined to be as follows: use of mineral medium with glucose as carbon and energy source, arabinose 0.1% to induce gene *hpd*, casamino acids at 0.2%, and tyrosine 1 mM. Under these conditions, after 6 days of culture, 213 mg/L of pyomelanin was produced (Bolognese et al. 2019).

In another report, a strain of *Ralstonia pickettii* that produces pyomelanin was isolated from soil samples. From this strain, gene *hppD* encoding 4-hydroxyphenyl pyruvate dioxygenase was amplified and cloned in plasmid pET-28a(+). This plasmid was then transformed into *E. coli* that in turn was cultured to produce pyomelanin. In these experiments, a dependency on metal ions was observed. In this case, the highest pyomelanin production was achieved while supplementing Cu²⁺, resulting in a titer of 315 mg/L (Seo and Choi 2020).

A new strain of *Flavobacterium kingsejongi* could produce a dark pigment when L-tyrosine was present in the culture medium. The chemical characterization of such pigment showed properties consistent with melanin. However, it was not clear if this pigment was eumelanin, pyomelanin or a mixture of both polymers. Regardless, the *hpd* gene encoding 4-hydroxyphenyl pyruvate dioxygenase from *F. kingsejongi* was amplified and cloned in expression vector pET-21a (+). The resulting plasmid was then transformed into *E. coli*. Afterward, this recombinant strain was cultured in a 5-L bioreactor containing TB medium supplemented with 10 g/L L-tyrosine and

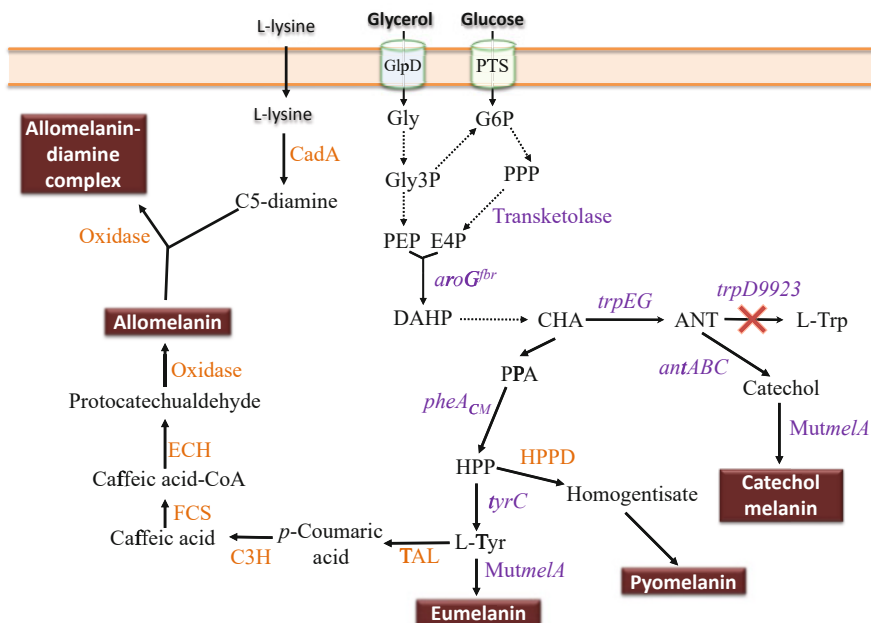


Fig. 3 Metabolic pathways and expressed genes related to the synthesis of melanins with engineered microorganisms. Dashed arrows indicate two or more enzyme reactions. Abbreviations: PTS phosphotransferase system glucose transport protein, Gly glycerol, Gly3P glycerol-3-phosphate, G6P glucose-6-phosphate, E4P D-erythrose 4-phosphate, PEP phosphoenolpyruvate, DAHP 3-deoxy-D-arabino-heptulosonate 7-phosphate, HPP 4-hydroxyphenylpyruvate, CHA chorismate, ANT anthranilate, PPA phenylpyruvate, HPPD hydroxyphenylpyruvate dehydrogenase, L-Tyr L-tyrosine, L-Trp L-tryptophan, *aroG^{fbr}* feedback inhibition resistant DAHP synthase, CadA L-lysine decarboxylase, *trpEG* anthranilate synthase component I, *trpD9923* mutant version of TrpD causing the loss of anthranilate phosphoribosyl transferase activity and retaining anthranilate synthase activity, *tyrC* cyclohexadienyl dehydrogenase, C3H p-coumarate 3-hydroxylase, TAL tyrosine ammonia-lyase, FCS feruloyl-CoA synthetase, ECH enoyl-CoA hydratase/aldolase, AntABC terminal oxygenase and the reductase components of anthranilate 1,2-dioxygenase, *pheA_{CM}* chorismate mutase domain from chorismate mutase-prephenate dehydratase, *Mutmela* mutant version of tyrosinase (Martínez et al. 2019)

1 mM IPTG. Under these conditions, 3.76 g/L of melanin was produced (Lee et al. 2022).

Random mutagenesis is a reasonably simple approach for strain enhancement; however, it can only be used with organisms that naturally produce melanin. A drawback of this approach is that the site and type of mutation are not easily determined. This restricts the application of genetic engineering methodologies for strain enhancement. Additionally, the strain may return to a low producer phenotype since the genetic alterations caused by random mutagenesis might be unstable. The enhanced strain's genome may be sequenced to learn more about the type of

mutation that caused it as well as the genes and pathways that contributed to the observed phenotype. Knowing this, the melanogenic organism can be “reverse-engineered” by reintroducing the detected mutations through genetic engineering techniques. Furthermore, by using this method, it is possible to distinguish between genetic alterations that are connected to an enhanced phenotype from those that might be harmful to production purposes. In the preceding examples, recombinant strains and procedures for converting various aromatic chemicals into melanins were detailed. Tyrosinases may use different precursors as substrates to produce melanins with different colors (Table 1). Despite these benefits, several disadvantages might be thought. One of them is the use of expensive of using pure melanin precursors. Therefore, to decrease expenses, less pure melanin precursors such as protein hydrolysates or yeast extract are used. Yet, using these more affordable precursors causes new issues. For example, these culture media may contain a variety of substances that can act as substrates of tyrosinases or that can react with melanin precursor molecules, therefore, their usage can lead to diversity in the composition of the generated melanins. Additionally, techniques for purifying melanin become more complicated and costly when non-defined media are used.

4 Production of Allomelanin and Novel Types of Melanin

In the chemical and food industries, chemicals known as phenolic aldehydes are commonly used. Thus, a project was launched that aimed to synthesize this class of compounds through engineered *E. coli* strains that have been altered to produce caffeic acid from L-tyrosine. To do so, the expression of the enzyme tyrosine ammonia-lyase (TAL) converted L-tyrosine to p-coumaric acid and p-coumarate 3-hydroxylase (C3H) converted p-coumaric acid to caffeic acid (Fig. 3). The resulting product was a black pigment with melanin-like properties, which was probably created by some of the oxidases encoded in the *E. coli* genome that can oxidize the catechol moiety of various molecules. Additionally, it was shown that by culturing *E. coli* with protocatechualdehyde in the media, a brown melanin pigment was produced, whereas when caffeic acid was added, a black pigment was generated. Additionally, the genes from *Burkholderia glumae* BGR1's encoding for feruloyl-CoA synthetase (FCS) and enoyl-CoA hydratase/aldolase (ECH) were expressed in *E. coli* (Fig. 3), resulting in a recombinant strain with the capacity to transform caffeic acid into protocatechualdehyde. Furthermore, this study found that wild-type *E. coli* BL21(DE3) generated 0.15 g/L of melanin when exposed to 5 mM caffeic acid. (Table 1). The production of melanin increased when the same quantity of caffeic acid was given to a culture of a recombinant strain expressing *fcs* and *ech*, reaching a titer of 0.2 g/L (Jang et al. 2018). Although the produced melanin chemical makeup has not been determined, it is most likely a polymer made up of a combination of protocatechualdehyde and caffeic acid moieties. These findings show that recombinant *E. coli* can produce caffeic acid and protocatechualdehyde melanins. It can also be expected that this strain's FCS and ECH activities affect how

much melanin and/or melanin precursors are produced, but the exact processes behind these effects are not yet entirely known. Therefore, the synthesized melanin's detailed characterization should shed further light on the chemical precursors involved in its synthesis. Additionally, finding the native *E. coli* enzyme responsible for the oxidation of protocatechualdehyde and caffeic acid, which results in their polymerization into melanin, should also be of interest as the development of melanin-producing strains should be possible by the cloning and overexpression of the gene encoding this yet undiscovered oxidase. In a subsequent publication, it was shown that soft contact lenses may be dyed using protocatechualdehyde-based melanin (Ahn et al. 2019), providing an advantage when compared to chemically produced dyes, as the antibacterial and antioxidant properties of melanins could benefit these products.

The synthesis of a novel melanin polymer was explored in *E. coli* by the co-expression of tyrosinase (MelC) and cytochrome P450 monooxygenase (CYP102G4). The tyrosinase MelC synthesizes eumelanin in the presence of L-tyrosine as substrate, whereas CYP102G4 is involved in the synthesis of indigo dye from L-tryptophan-derived indole. The gene *melC* was obtained from *Bacillus megaterium*, and cloned in the pET-24a(+) vector. Gene *cyp102G4* was amplified from *Streptomyces cattleya* and cloned in pETduet-1. Single plasmids or both were transformed into the *E. coli* BL21 (DE3) strain. Cultures with a strain expressing *melC* in the presence of L-tyrosine and L-tryptophan resulted in the production of 1 g/L of melanin. In contrast, under the same conditions, a strain expressing both *melC* and *cyp102G4* produced 3.5 g/L of melanin. The characterization of this novel melanin demonstrated it had noticeable dyeing capabilities on cellulose paper. In addition, it displayed electrical conductivity, rendering it a potential material for organic electrodes (Park et al. 2020).

In another study, the production of novel synthetic melanin was explored by employing C5-diamine to increase the crosslinking of melanin units. *E. coli* strains expressing combinations of the following enzymes were evaluated: Tyrosine ammonia lyase, p-coumarate 3-hydroxylase, feruloyl-CoA synthetase, enoyl-CoA hydratase, lysine decarboxylase, and tyrosinase. Some of these strains produced melanin derived from caffeic acid, protocatechualdehyde, or L-DOPA to a maximum level of 400 mg/L.

A strain expressing all the previous enzymes showed the capacity to produce a melanin-diamine complex. Using this strain in biotransformation experiments, 20 mg/L of a melanin-diamine complex was formed while supplying 5 mM caffeic acid, L-tyrosine, and L-lysine (Ahn et al. 2021). This relatively low production level is attributed to toxicity from the C5-diamine, which is formed by lysine decarboxylase. Therefore, to improve the production of melanin-diamine, further studies must be done to contend with C5-diamine toxicity.

5 Metabolic Engineering Applied for De Novo Synthesis of Melanins

Developing microbial strains for the complete synthesis of melanins from simple carbon sources is one possible solution for the challenges stated previously. Based on metabolic engineering techniques, it is possible to increase flux into the shikimate pathway, which is responsible for producing the precursors of aromatic amino acids. For instance, L-tyrosine, a precursor of eumelanin, was produced from glucose by an *E. coli* strain modified through metabolic engineering techniques (Chávez-Béjar et al. 2008). To do so, carbon flow to the L-tyrosine biosynthetic pathway was increased by overexpressing the genes for cyclohexadienyl dehydrogenase (TyrC) from *Zymomonas mobilis*, the chorismate mutase domain from the original enzyme chorismate mutase-prephenate dehydratase, and a feedback-insensitive version of the enzyme 3-deoxy-D-arabino-heptulosonate 7-phosphate (DAHP) synthase (*aroG^{fbr}*). Additionally, this strain expressed the tyrosinase MutMelA (Fig. 3). The resulting strain was able to produce eumelanin from glucose. But it was found that the L-tyrosine pool was decreased by MutMelA activity, which led to a defect in cell growth. It was then found that Cu is required as a cofactor for the correct functioning of the enzyme tyrosinase. Thus, to prevent L-tyrosine depletion by MutMelA, Cu was left out of the medium during the first half of the culture. Then, tyrosinase was activated by the addition of CuSO₄ to the medium, which began the eumelanin synthesis phase. This method was used in bioreactor cultures where the only carbon source was glucose. In this culture, 3.2 g/L of eumelanin was produced in 120 h (Table 1) (Chávez-Béjar et al. 2013). These results were the first instance of the application of metabolic engineering to create a strain for the complete synthesis of eumelanin from glucose. This work shed light on the possible detrimental effects on cell physiology brought on by tyrosinase expression at high levels. Yet, by using a delayed activation of the heterologous enzyme, this issue was solved. A different approach might be based on the precise regulation of gene induction during a particular stage of the production culture.

During the characterization of the enzyme MutMelA, it was found that in addition to L-tyrosine, catechol may be used as a substrate. Therefore, this enzyme might be used to produce catechol melanin. To put this theory to the test, a bioconversion process was created using an *E. coli* strain that expresses MutMelA and grows on a medium that contains catechol (0.85 g/L) as a tyrosinase substrate, and glycerol 40 g/L as a carbon source. In this experiment, 0.29 g/L of catechol melanin was generated after 54 h. To further enhance this process, metabolic engineering was evaluated to create a strain capable of producing catechol melanin from a simple carbon source. The method used was based on employing an engineered strain of *E. coli* capable of generating catechol from a simple carbon source (Balderas-Hernández et al. 2014). The chosen mutant strain was *E. coli* W3110 *trpD9923*, which overproduces the intermediate anthranilate in the L-tryptophan biosynthesis pathway (Yanofsky et al. 1971). This strain was altered to enhance carbon flow to anthranilate by overexpressing the *aroG^{fbr}* and *tktA* genes that encode for the feedback-insensitive

form of the enzyme DAHP synthase and transketolase, respectively (Fig. 3). These modifications resulted in a twofold increase of the anthranilate titer in flask cultures (Balderas-Hernández et al. 2009). This strain was further modified through the expression of the genes *antABC* which encodes anthranilate 1,2-dioxygenase from *P. aeruginosa* PAO1, granting it the capacity to convert anthranilate to catechol (Fig. 3). Lastly, the strain was further modified by integrating the gene *MutmelA* into the chromosome at the location of the *lacZ* gene. The resultant strain was assessed in 1-liter bioreactor cultures. The carbon source in the culture medium was glycerol, 40 g/L. This carbon source was chosen instead of glucose because it does not utilize the aromatics precursor PEP during its internalization and phosphorylation. Furthermore, glycerol is a very affordable, plentiful, and renewable carbon source, as it is a byproduct of biodiesel and soap manufacturing (Tan et al. 2013). Additionally, 2 g/L of yeast extract was added to the culture medium because the employed strain is an L-tryptophan auxotroph. Under these conditions, the modified strain showed growth for 17 h before entering the stationary phase, which lasted 72 h. At 18 h, just at the beginning of the stationary phase, catechol melanin started to accumulate. A total of 1.21 g/L of catechol melanin were recovered from the culture medium, while 0.73 g/L of catechol was accumulated at the end of the culture (Table 1) (Mejía-Caballero et al. 2016). This finding suggests that the rate of synthesis of this precursor is greater than the capacity of MutMelA to metabolize it. Therefore, tyrosinase activity should be increased as a goal to improve strain performance.

The yeast *Yarrowia lipolytica* displays a natural capacity to produce pyomelanin. To improve the de novo pyomelanin synthesis capacity in this yeast, a strategy was followed based on the utilization of *Y. lipolytica* strain JMY8032 which was engineered for aromatic amino acid production. In this strain, flow into the L-tyrosine and L-phenylalanine pathways was increased by expressing unregulated mutant versions of enzymes DAHP synthase, chorismate mutase, and aromatic aminotransferase I. Meanwhile, gene *4HPPD* encoding 4-hydroxyphenyl pyruvate dioxygenase was disrupted. The resulting mutant strain did not produce pyomelanin, confirming that this gene is involved in HGA synthesis. Thus, to generate a strain that overexpresses *4HPPD*, this gene was cloned under the control of the strong constitutive pTEF promoter. The Golden Gate cloning procedure was employed to generate strain JMY8208 with *4HPPD* integrated into the chromosome (Larroude et al. 2021). Genetic characterization of this strain showed that it contained three copies of the *4HPPD* overexpression cassette. Then, this strain was grown in YNB medium supplemented with glucose at 28 °C in shake flasks, and, after 5 days of culture, 4.5 g/L of pyomelanin was synthesized (Larroude et al. 2021).

6 Conclusions and Perspectives

Melanins can be considered functional polymers with multiple potential industrial applications. Some significant technological problems related to melanins are achieving their large-scale synthesis while obtaining specific chemical composition

and maintaining affordable production costs. These challenges can be overcome by isolating and employing naturally occurring melanogenic bacteria. This proposal presents various benefits, such as the potential to rapidly establish a production process. However, using naturally occurring melanogenic organisms might have certain downsides, such as the need to use complicated conditions to activate the synthesis of melanin. Utilizing complex media makes purifying processes more difficult and increases the risk of producing melanin with undesirable chemical components. In turn, these issues can be solved by using genetic engineering techniques to create new melanogenic strains or to enhance the expression of naturally occurring genes involved in melanogenesis. Furthermore, it is increasingly easier to do so thanks to the growing body of information available regarding the biochemistry and genetics of melanin synthesis in many species. Through these innovative techniques, new melanogenic strains have been developed that can produce melanin from simple carbon sources. These efforts have resulted in strains and processes capable of producing melanin polymers at the gram scale (Table 1).

Tyrosinase gene overexpression is the primary genetic modification used to create or enhance melanogenic organisms. This process generally involves cloning the tyrosinase gene in a replicative plasmid vector controlled by an inducible promoter. By adding inducers, this method allows exact control of the amount and timing of gene expression, enabling the optimization of the production process. Furthermore, antibiotics must be added as a selective pressure when employing expression plasmids, for example, in cases when it is necessary to prevent the development of plasmid-less cells. The requirement for a chemical inducer to be present in the culture medium is another issue. Antibiotics and inducers drive up manufacturing costs and make purifying processes more challenging. Hence, alternative antibiotic-free plasmid selection methods, as well as non-chemically based gene induction techniques, need to be developed, including process optimization, to produce melanins at grams per liter level to simplify purification processes and to reduce production costs. (Vidal et al. 2008).

When comparing the strains that transform melanin precursors present in the culture medium, it can be observed that in several of the reports reviewed so far, the melanin titers and volumetric productivities are lower in processes where the production strain used was modified by metabolic engineering where the objective was challenging to convert the carbon sources into melanins (Table 1). In these cases, the reported titers and productivities for eumelanin are lower than those that have been seen when L-tyrosine was used as a precursor (Santos et al. 2012). This fact demonstrates that there may still be room for improvement in the production process and strain engineering.

To improve the currently available melanin production strains, the use of synthetic biology, mutagenesis techniques, and adaptive laboratory evolution (ALE), should be assessed (Bassalo et al. 2016). Specifically, the engineering of complicated phenotypes may be possible with the application of ALE. In one study, ALE was paired with a synthetic biosensor module that reacts to the intracellular concentration of aromatic amino acids, which resulted in an improved strain of *S. cerevisiae* able to produce muconic acid (Leavitt et al. 2017). This last strain displayed an

increased flux in the common aromatic amino acid pathway; thus, it could be further modified to enhance L-tyrosine synthesis by following established methods. The *S. cerevisiae* strain created in the such study could also serve as a platform for eumelanin production if such modifications are made. In a different publication, an *E. coli* strain expressing the MelA tyrosinase from *R. etli* was used to create a high-throughput screen for the manufacture of L-tyrosine by linking the synthesis of this amino acid to the production of melanin (Santos and Stephanopoulos 2008). This technique was used to find *E. coli* strains that have increased L-tyrosine synthesis capacity. In said work, *E. coli* was genetically modified using metabolic engineering techniques which resulted in high-level L-tyrosine synthesis. Global transcription machinery engineering (gTME) was applied to this strain to increase its capacity to synthesize L-tyrosine (Alper et al. 2006). This technique was performed by producing two different gTME libraries of the RNA polymerase *rpoA* and *rpoD* subunits in the modified strain of *E. coli*. Based on the melanin color intensity of colonies from these libraries, improved L-tyrosine producers from these two libraries were identified on agar plates. When compared to the modified parent strain, three mutant isolates showed a twofold increase in L-tyrosine titer (Santos et al. 2012). Additionally, it should be highlighted that these strains may be used for eumelanin production from glucose.

Tyrosinase activity is one of the factors limiting production in strains engineered to synthesize melanin from a simple carbon source (Chávez-Béjar et al. 2013; Mejía-Caballero et al. 2016), and it could also be limiting the synthesis of melanin in other modified strains. Thus, it is crucial to evaluate tyrosinase enzymes from various biological sources to identify those with the required characteristics for biotechnological application. The extensive genome and metagenome data that is currently available should provide many genes encoding tyrosinases that can be evaluated experimentally for melanin production. Meanwhile, protein engineering could be a practical way to enhance this family of enzymes. Furthermore, an advantage of working with tyrosinases is the simple activity assay based on visual detection of melanin production, which allows for high-throughput selection methods (Santos and Stephanopoulos 2008).

Despite the technological advancements in the design of strains and methods for the synthesis of melanin, there are still many fundamental concerns that need to be resolved. For instance, the kinetics of melanin polymerization is a significant issue, as it is believed that after being produced in the cytosol, melanin precursors leave the cell and begin to polymerize in the culture media. Consequently, as the polymer increases in size, a wide variety of melanin molecules are produced. These macromolecules should have unique physical characteristics. For example, distinct eumelanin isolates from different manufacturing cultures exhibit a range of hues, from yellow to black (Chávez-Béjar et al. 2013). Therefore, it is crucial to research the kinetics of melanin polymerization in production cultures and the features of polymers of specific sizes as this information could help isolate products with specific attributes.

As observed in the publications examined in this chapter, most of the published research on microbial melanin production is focused on eumelanin. This makes

sense, as it is a polymer that has undergone considerable characterization since it is the type of melanin found in humans. Therefore, the produced eumelanin may be applied in the medical and cosmetic fields. Additionally, it should be emphasized that in terms of their chemical composition, melanins are a diverse set of polymers. In consequence, only a small portion of this chemical diversity has been studied thus far. Yet, processes used for the production of catechol, caffeic acid, and protocatechualdehyde melanins have been reported, in addition to eumelanin. Therefore, it stands to reason that different forms of melanin would operate differently depending on the application. For example, a recent study found that protocatechualdehyde-based melanin performed better than eumelanin or caffeic acid melanin when used as a pigment in soft contact lenses (Ahn et al. 2019). Additionally, synthetic non-natural amino acids and other substances that tyrosinases can use as substrates can be used to create non-natural melanins (Della-Cioppa et al. 1990). As a result, a wide variety of this class of polymers is expected to be produced soon. Finally, it is expected that the range of applications for these aromatic polymers should significantly increase when new strains and production techniques for novel natural and synthetic melanins are developed.

References

- Aguilera F, McDougall C, Degnan BM (2013) Origin, evolution and classification of type-3 copper proteins: lineage-specific gene expansions and losses across the Metazoa. *BMC Evol Biol* 13:96
- Ahn SY, Choi M, Jeong DW, Park S, Park H, Jang KS, Choi KY (2019) Synthesis and chemical composition analysis of protocatechualdehyde-based novel melanin dye by 15T FT-ICR: high dyeing performance on soft contact lens. *Dyes Pigments* 160:546–554
- Ahn SY, Jang S, Sudheer PD, Choi KY (2021) Microbial production of melanin pigments from caffeic acid and L-tyrosine using *Streptomyces glaucescens* and FCS-ECH-expressing *Escherichia coli*. *Int J Mol Sci* 22(5):2413
- Alper H, Moxley J, Nevoigt E, Fink GR, Stephanopoulos G (2006) Engineering yeast transcription machinery for improved ethanol tolerance and production. *Science* 314(5805):1565–1568
- Ambrico M, Vecchia NFD, Ambrico PF, Cardone A, Cicco SR, Ligonzo T et al (2014) A Photoresponsive red-hair-inspired polydopamine-based copolymer for hybrid photocapacitive sensors. *Adv Funct Mater* 24(45):7161–7172
- Balderas-Hernández VE, Sabido-Ramos A, Silva P, Cabrera-Valladares N, Hernández-Chávez G, Báez-Viveros JL et al (2009) Metabolic engineering for improving anthranilate synthesis from glucose in *Escherichia coli*. *Microb Cell Factories* 8(1):19
- Balderas-Hernández VE, Treviño-Quintanilla LG, Hernández-Chávez G, Martínez A, Bolívar F, Gosset G (2014) Catechol biosynthesis from glucose in *Escherichia coli* anthranilate-overproducer strains by heterologous expression of anthranilate 1, 2-dioxygenase from *Pseudomonas aeruginosa* PAO1. *Microb Cell Factories* 13(1):136
- Bassalo MC, Liu R, Gill RT (2016) Directed evolution and synthetic biology applications to microbial systems. *Curr Opin Biotechnol* 39:126–133
- Bolognese F, Scanferla C, Caruso E, Orlandi VT (2019) Bacterial melanin production by heterologous expression of 4-hydroxyphenylpyruvate dioxygenase from *Pseudomonas aeruginosa*. *Int J Biol Macromol* 133:1072–1080

- Cabrera-Valladares N, Martínez A, Pinero S, Lagunas-Munoz VH, Tinoco R, De Anda R et al (2006) Expression of the *melA* gene from *Rhizobium etli* CFN42 in *Escherichia coli* and characterization of the encoded tyrosinase. *Enzym Microb Technol* 38(6):772–779
- Chávez-Béjar MI, Lara AR, López H, Hernández-Chávez G, Martínez A, Ramírez OT et al (2008) Metabolic engineering of *Escherichia coli* for L-tyrosine production by expression of genes coding for the chorismate mutase domain of the native chorismate mutase-prephenate dehydratase and a cyclohexadienyl dehydrogenase from *Zymomonas mobilis*. *Appl Environ Microbiol* 74(10):3284–3290
- Chávez-Béjar MI, Balderas-Hernández VE, Gutiérrez-Alejandre A, Martínez A, Bolívar F, Gosset G (2013) Metabolic engineering of *Escherichia coli* to optimize melanin synthesis from glucose. *Microb Cell Factories* 12(1):108
- d'Ischia M, Wakamatsu K, Cicoira F, Di Mauro E, Garcia-Borrón JC, Commo S et al (2015) Melanins and melanogenesis: from pigment cells to human health and technological applications. *Pigment Cell Melanoma Res* 28(5):520–544
- Della-Cioppa G, Garger SJ, Sverlow GG, Turpen TH, Grill LK (1990) Melanin production in *Escherichia coli* from a cloned tyrosinase gene. *Bio/Technology* 8(7):634
- Esposito R, D'Aniello S, Squarzone P, Pezzotti MR, Ristatore F, Spagnuolo A (2012) New insights into the evolution of metazoan tyrosinase gene family. *PLoS One* 7(4):e35731
- Fairhead M, Thöny-Meyer L (2012) Bacterial tyrosinases: old enzymes with new relevance to biotechnology. *New Biotechnol* 29(2):183–191
- García-Molina F, Munoz JL, Varon R, Rodríguez-Lopez JN, García-Canovas F, Tudela J (2007) A review on spectrophotometric methods for measuring the monophenolase and diphenolase activities of tyrosinase. *J Agric Food Chem* 55(24):9739–9749
- Gibello A, Ferrer E, Sanz J, Martín M (1995) Polymer production by *Klebsiella pneumoniae* 4-hydroxyphenylacetic acid hydroxylase genes cloned in *Escherichia coli*. *Appl Environ Microbiol* 61(12):4167–4171
- Glass K, Ito S, Wilby PR, Sota T, Nakamura A, Bowers CR et al (2012) Direct chemical evidence for eumelanin pigment from the Jurassic period. *Proc Natl Acad Sci* 109(26):10218–10223
- González V, Bustos P, Ramírez-Romero MA, Medrano-Soto A, Salgado H, Hernández-González I et al (2003) The mosaic structure of the symbiotic plasmid of *Rhizobium etli* CFN42 and its relation to other symbiotic genome compartments. *Genome Biol* 4(6):R36
- Guo J, Rao Z, Yang T, Man Z, Xu M, Zhang X (2014) High-level production of melanin by a novel isolate of *Streptomyces kathirae*. *FEMS Microbiol Lett* 357(1):85–91
- Guo J, Rao Z, Yang T, Man Z, Xu M, Zhang X, Yang ST (2015) Cloning and identification of a novel tyrosinase and its overexpression in *Streptomyces kathirae* SC-1 for enhancing melanin production. *FEMS Microbiol Lett* 362(8):fnv041
- Horneck G, Klaus DM, Mancinelli RL (2010) Space microbiology. *Microbiol Mol Biol Rev* 74(1):121–156
- Ito S (2003) A chemist's view of melanogenesis. *Pigment Cell Res* 16(3):230–236
- Jaenicke E, Decker H (2004) Functional changes in the family of type 3 copper proteins during evolution. *Chembiochem* 5:163–169
- Jang S, Gang H, Kim BG, Choi KY (2018) FCS and ECH dependent production of phenolic aldehyde and melanin pigment from l-tyrosine in *Escherichia coli*. *Enzym Microb Technol* 112:59–64
- Kaintz C, Mauracher SG, Rempel A (2014) Type-3 copper proteins: recent advances on polyphenol oxidases. In: Christov CZ (ed) *Advances in protein chemistry and structural biology: metal-containing enzymes*. Academic, pp 1–35
- Kampatsikas I, Rempel A (2021) Similar but still different: which amino acid residues are responsible for varying activities in type-iii copper enzymes? *ChemBioChem* 22:1161–1175
- Kim H, Yeon YJ, Cho YR, Song W, Pack SP, Choi YS (2016) A cold-adapted tyrosinase with an abnormally high monophenolase/diphenolase activity ration originating from the marine archaeon *Candidatus Nitrosopumilus koreensis*. *Biotechnol Lett* 38:1535–1542

- Krol ES, Liebler DC (1998) Photoprotective actions of natural and synthetic melanins. *Chem Res Toxicol* 11(12):1434–1440
- Lagunas-Muñoz VH, Cabrera-Valladares N, Bolívar F, Gosset G, Martínez A (2006) Optimum melanin production using recombinant *Escherichia coli*. *J Appl Microbiol* 101(5):1002–1008
- Larroude M, Onésime D, Rué O, Nicaud JM, Rossignol T (2021) A *Yarrowia lipolytica* strain engineered for pyomelanin production. *Microorganisms* 9(4):838
- Leavitt JM, Wagner JM, Tu CC, Tong A, Liu Y, Alper HS (2017) Biosensor-enabled directed evolution to improve muconic acid production in *Saccharomyces cerevisiae*. *Biotechnol J* 12(10):1600687
- Lee HS, Choi JY, Kwon SJ, Park ES, Oh BM, Kim JH, Lee PC (2022) Melanin biopolymer synthesis using a new melanogenic strain of *Flavobacterium kingsejongi* and a recombinant strain of *Escherichia coli* expressing 4-hydroxyphenylpyruvate dioxygenase from *F. kingsejongi*. *Microb Cell Factories* 21(1):1–15
- Lin WP, Lai HL, Liu YL, Chiung YM, Shiau CY, Han JM et al (2005) Effect of melanin produced by a recombinant *Escherichia coli* on antibacterial activity of antibiotics. *J Microbiol Immunol Infect* 38(5):320–326
- Lindgren J, Moyer A, Schweitzer MH, Sjövall P, Uvdal P, Nilsson DE et al (2015) Interpreting melanin-based coloration through deep time: a critical review. *Proc R Soc B Biol Sci* 282(1813): 20150614
- Martínez LM, Martínez A, Gosset G (2019) Production of melanins with recombinant microorganisms. *Front Bioeng Biotechnol* 7:285
- Mejía-Caballero A, de Anda R, Hernández-Chávez G, Rogg S, Martínez A, Bolívar F et al (2016) Biosynthesis of catechol melanin from glycerol employing metabolically engineered *Escherichia coli*. *Microb Cell Factories* 15(1):161
- Montefiori DC, Zhou J (1991) Selective antiviral activity of synthetic soluble L-tyrosine and L-dopa melanins against human immunodeficiency virus in vitro. *Antivir Res* 15(1):11–25
- Nikodinovic-Runic J, Martin LB, Babu R, Blau W, O'Connor KE (2009) Characterization of melanin-overproducing transposon mutants of *Pseudomonas putida* F6. *FEMS Microbiol Lett* 298(2):174–183
- Nofsinger JB, Liu Y, Simon JD (2002) Aggregation of eumelanin mitigates photogeneration of reactive oxygen species. *Free Radic Biol Med* 32(8):720–730
- Park H, Yang I, Choi M, Jang KS, Jung JC, Choi KY (2020) Engineering of melanin biopolymer by co-expression of MelC tyrosinase with CYP102G4 monooxygenase: structural composition understanding by 15 tesla FT-ICR MS analysis. *Biochem Eng J* 157:107530
- Piñero S, Rivera J, Romero D, Cevallos MA, Martínez A, Bolívar F, Gosset G (2007) Tyrosinase from *Rhizobium etli* is involved in nodulation efficiency and symbiosis-associated stress resistance. *J Mol Microbiol Biotechnol* 13(1–3):35–44
- Pretzler M, Rompel A (2018) What causes the different functionality in type-III-copper enzymes? A state of the art perspective. *Inorg Chim Acta* 481:25–31
- Prieto MA, Perez-Aranda A, Garcia JL (1993) Characterization of an *Escherichia coli* aromatic hydroxylase with a broad substrate range. *J Bacteriol* 175(7):2162–2167
- Rózanowska M, Sarna T, Land EJ, Truscott TG (1999) Free radical scavenging properties of melanin: interaction of eu- and pheo-melanin models with reducing and oxidising radicals. *Free Radic Biol Med* 26(5–6):518–525
- Ruan L, Yu Z, Fang B, He W, Wang Y, Shen P (2004) Melanin pigment formation and increased UV resistance in *Bacillus thuringiensis* following high temperature induction. *Syst Appl Microbiol* 27(3):286–289
- Ruan L, He W, He J, Sun M, Yu Z (2005) Cloning and expression of *mel* gene from *Bacillus thuringiensis* in *Escherichia coli*. *Antonie Van Leeuwenhoek* 87(4):283–288
- Saini AS, Melo JS (2015) One-pot green synthesis of eumelanin: process optimization and its characterization. *RSC Adv* 5(59):47671–47680
- Santos CNS, Stephanopoulos G (2008) Melanin-based high-throughput screen for L-tyrosine production in *Escherichia coli*. *Appl Environ Microbiol* 74(4):1190–1197

- Santos CNS, Xiao W, Stephanopoulos G (2012) Rational, combinatorial, and genomic approaches for engineering L-tyrosine production in *Escherichia coli*. *Proc Natl Acad Sci* 109(34):13538–13543
- Sarna T, Hyde JS, Swartz HM (1976) Ion-exchange in melanin: an electron spin resonance study with lanthanide probes. *Science* 192(4244):1132–1134
- Seo D, Choi KY (2020) Heterologous production of pyomelanin biopolymer using 4-hydroxyphenylpyruvate dioxygenase isolated from *Ralstonia pickettii* in *Escherichia coli*. *Biochem Eng J* 157:107548
- Tan HW, Aziz AA, Aroua MK (2013) Glycerol production and its applications as a raw material: a review. *Renew Sust Energ Rev* 27:118–127
- Valderrama B, Oliver P, Medrano-Soto A, Vazquez-Duhalt R (2003) Evolutionary and structural diversity of fungal laccases. *Antonie Van Leeuwenhoek* 84(4):289–299
- Van Holde KE, Miller KI, Decker H (2001) Hemocyanins and invertebrate evolution. *J Biol Chem* 279(19):15563–15566
- Vidal L, Pinsach J, Striedner G, Caminal G, Ferrer P (2008) Development of an antibiotic-free plasmid selection system based on glycine auxotrophy for recombinant protein overproduction in *Escherichia coli*. *J Biotechnol* 134(1–2):127–136
- Wogelius RA, Manning PL, Barden HE, Edwards NP, Webb SM, Sellers WI et al (2011) Trace metals as biomarkers for eumelanin pigment in the fossil record. *Science* 333(6049):1622–1626
- Yanofsky C, Horn V, Bonner M, Stasiowski S (1971) Polarity and enzyme functions in mutants of the first three genes of the tryptophan operon of *Escherichia coli*. *Genetics* 69(4):409
- Zhang F, Kearns SL, Orr PJ, Benton MJ, Zhou Z, Johnson D et al (2010) Fossilized melanosomes and the colour of cretaceous dinosaurs and birds. *Nature* 463(7284):1075

Extraction, Purification, and Characterization of Microbial Melanin Pigments



Vishal A. Ghadge, Sanju Singh, Pankaj Kumar, Doniya Elze Mathew, Asmita Dhimmar, Harshal Sahastrabudhe, Apexa Gajjar, Satish B. Nimse, and Pramod B. Shinde

1 Introduction

‘Melanins’ are natural polymeric pigments present in all forms of life, having a heterogeneous origin with an extensive diversity extending from structure, and functions to different colored pigments (Gosset 2017; Stepien et al. 2013). The melanin word was derived from ‘melanos’ meaning dark. However, a Swedish scientist proved the appearance of melanin in the 1840s after isolating the pigment from the iris of the eye. The initial procedure for the formation of polymeric pigments is via the oxidation of phenolic or indolic monomeric substrates involving enzyme catalysis. Melanin has slowly diversified from three different types into five different classes based on the monomeric unit involved in their formation. Those five types are eumelanin, pheomelanin, allomelanin, pyomelanin, and neuromelanin. Eumelanin and allomelanin contribute dark brown to black coloration to the cells

V. A. Ghadge · S. Singh · P. Kumar · A. Dhimmar · H. Sahastrabudhe · A. Gajjar · P. B. Shinde (✉)

Natural Products & Green Chemistry Division, CSIR-Central Salt and Marine Chemicals Research Institute (CSIR-CSMCRI), Council of Scientific and Industrial Research (CSIR), Bhavnagar, Gujarat, India

Academy of Scientific and Innovative Research (AcSIR), Ghaziabad, Uttar Pradesh, India
e-mail: pramodshinde@csmcri.res.in

D. E. Mathew

Academy of Scientific and Innovative Research (AcSIR), Ghaziabad, Uttar Pradesh, India

Applied Phycology and Biotechnology Division, CSIR-Central Salt and Marine Chemicals Research Institute (CSIR-CSMCRI), Council of Scientific and Industrial Research (CSIR), Bhavnagar, Gujarat, India

S. B. Nimse

Institute of Applied Chemistry and Department of Chemistry, Hallym University, Chuncheon, Republic of Korea

unbiased for any specific kingdom. Whereas pheomelanin is mainly found in the animal kingdom and provides yellow to red pigmentation to the cells (Nicolaus 1968; Pralea et al. 2019). The precursor units of these melanins play an important role in understanding the synthesis, structure, and function of these pigments. Precursor units for the polymer eumelanin consist primarily of indole-type monomeric units that are formed as a result of L-tyrosine or L-DOPA (L-3,4-dihydroxyphenylalanine) oxidation reactions. Similarly, pheomelanins are also the products of tyrosine as eumelanins, however, cysteine moieties are incorporated in their structures (Singh et al. 2021). The synthesis of allomelanins is quite different and is derived by the oxidation of nitrogen-free diphenols such as catechol, 1,8-dihydroxynaphthalene, and γ -glutaminy-3,4-dihydroxybenzene. Pyomelanins are polymers of 2,5-dihydroxyphenylacetic acid, a byproduct of tyrosine metabolism, and display better photo- and thermo-stability. Whereas neuromelanin is synthesized from catechol and quinones in the human substantia nigra (Haining and Achat-Mendes 2017; Pralea et al. 2019). Knowledge of the structure and biosynthetic pathways that lead to the various melanins found in nature can act as inspiration for the development of new artificial pigments and their materials. Melanins are well-known for providing pigmentation to cells, however, they play many major roles in different niches of life. Melanins provide shielding from harmful radiations, perform oxidation of reactive oxygen species, are responsible for a range of functions across kingdoms, help with defense mechanisms in arthropods, molluscs, and microbes, and enhance pathogenicity in various fungi and bacteria (Singh et al. 2021). Further, due to the intramolecular electronic interactions, melanins have applications in semiconductors (Bothma et al. 2008), as metal chelators, as optical imagers (Abbas et al. 2009), extending to cosmeceuticals and pharmaceuticals, MRI probes, soil bioremediations, etc. (Martinez et al. 2019). The presence of melanin plays an irreplaceable role in human lives, wherein the absence of melanin can lead to diseases like cancer, vitiligo, Waardenburg syndrome, etc. Despite such promising and diverse attributes, the complete potential of melanin is not harvested because of its heterogeneous nature, resulting in a lack of specific genetic makeup responsible for melanin biosynthesis and sequential metabolic pathways. Further, the capabilities of microbes to employ multiple precursors like tyrosine and DOPA for melanin synthesis ultimately leads to a complex process of biosynthesis (Cao et al. 2021). The isolation and complete characterization of melanin is very difficult because of its insolubility in organic solvents. The narrow-spectrum solubility of melanins makes the extraction process costly and hence reduces its industrial production (Borovansky and Riley 2011; Sun et al. 2016). As a result of such physical problems, the isolation of melanin from eukaryotic sources is hindered; in such conditions, microbial melanin can pave the way (Pavan et al. 2020; Sun et al. 2016). Culturing aspects of microbial melanin makes them feasible for easier upscaling for commercial production and efficient utilization in various sectors.

2 Extraction of Melanin

Due to the amorphous nature and structural diversity, extraction of melanin employs different methods which highly rely on factors like melanin source (fungal, bacterial, human hair) and its cellular localization (intracellular/extracellular) (Aghajanyan et al. 2005, 2017; Gómez-Marín and Sánchez 2010; Tarangini and Mishra 2014). For example, extracellular melanin extraction involves acid precipitation (Choi 2021), whereas intracellular melanin extraction employs alkali extraction, acid precipitation, ultrasonic-assisted extraction (Hu et al. 2015; Zou et al. 2010), and microwave-assisted extraction (Lu et al. 2014). The most conventional method for melanin extraction is alkali extraction and acid precipitation as melanins normally solubilize in alkaline solutions and precipitate as sediments in acidic solutions (Lu et al. 2014; Sajjan et al. 2010; Sun et al. 2016). Many alkali solutions such as sodium hydroxide, potassium hydroxide, ammonium hydroxide, calcium hydroxide, etc. are reported to be used at different concentrations of 0.1, 0.5, 1, 1.5, and 2 N for melanin extraction, whereas for precipitation purposes, double strength acid like HCl is used under slow magnetic stirring conditions. Many research groups have employed this conventional method to extract melanin from different microbial sources as summarized in review articles (Singh et al. 2021; Choi 2021). Apart from alkali extraction assisted with ultrasonication/microwave, an enzymatic method is also used for extraction of intracellular melanin due to the ability of enzymes to increase hydrolysis as well as degradation of impermeable cell walls. This method mainly utilizes specific cell wall lysing enzymes such as guanidine thiocyanate for protein denaturation and a serine proteinase for cleavage (Dadachova et al. 2007; Youngchim et al. 2004). This traditional method is economically feasible but has low extraction efficiency and is time-consuming; so nowadays there is a trend for advanced cavitation-based extraction methods which minimize the use of toxic solvents, improve extraction yield, shorten extraction duration, and use green solvents that are recycled and reusable (Ghadge et al. 2022; Panda and Manickam 2019; Zou et al. 2010). For example, melanin is extracted from *Streptomyces hyderabadensis* 7VPT5-5R using tetrabutylammonium hydroxide (40% w/w TBAOH in water) solvent which led to a 66% increase in the yield of melanin in comparison to the conventional method of extraction (Ghadge et al. 2022).

Cavitation is a phenomenon where a small low-pressure vapor-filled cavity is formed due to a rapid change in pressure under the liquid medium. Based on this phenomenon, various cavitation-based extraction techniques such as ultrasound-assisted extraction (UAE), negative-pressure cavitation (NPC) extraction, microwave-assisted extraction (MAE), and hydrodynamic cavitation extraction (HCE) have been reported (Lu et al. 2014; Zou et al. 2010). In 2010, melanin from *A. auricula* fruit bodies was extracted using cavitation-based UAE (ultrasound-assisted extraction) technology due to its numerous benefits in comparison to conventional ones such as improved extraction yield, reduced power consumption, and extraction time (Zou et al. 2010). UAE employs ultrasound pressure waves due to the resulting energy generated from these collapsing cavitation

bubbles that provide greater penetration of the solvent into the cellular material and increases mass transfer to and from interfaces. This also causes disruption of cell walls and the release of cellular materials that ultimately leads to increased extraction yield. In UAE, cavitation occurs due to the passage of ultrasound waves in the liquid medium. Whereas if it occurs, due to the pressure variations in the flowing liquid concerning the change in the geometry of constriction, then it is called hydrodynamic cavitation extraction (HCE). The limitations associated with UAE are attenuation of ultrasound waves for highly concentrated dispersed phases and lack of uniformity for dispersed extract materials (Panda and Manickam 2019). In the case of NPC, the creation of negative pressure governs cavitation. NPC extraction proved to be more effective in the extraction of heat-sensitive compounds such as polyphenols and polysaccharides (Panda and Manickam 2019). MAE uses microwave energy to heat solvents in contact with a sample to partition analytes from the sample matrix into the solvent (Lu et al. 2014; Tatke and Jaiswal 2011), but a problem with this technique is the rapid increase in temperature of the extraction mixture that may terminate the extraction process early due to the boiling of the solvent. Thus, the desired compounds are not sufficiently diffused from the material into the solvent and consequently, the extraction yield is reduced (Chuyen et al. 2018). The UAE method was reported to yield 37.33% pure melanin (Hou et al. 2019), whereas another study reported that a purification yield of 11.08% could be achieved through an MAE method, which was 40.43% higher than that obtained by alkali extraction and acid precipitation (Lu et al. 2014).

Due to the presence of various biological sources for production, structural diversity, amorphous nature, and insolubility of melanin have resulted in the non-availability of a standard method for extraction and purification of melanin. But the above-described modern extraction techniques can be alternatively used owing to numerous advantages over conventional methods like reduced energy and solvent consumption, increase in extraction yield, improvement of extract quality, reduction in extraction time, and protection of thermo-labile compounds in the extract (Panda and Manickam 2019; Tatke and Jaiswal 2011; Zou et al. 2010).

3 Purification of Melanin

Purification of melanin can be achieved by performing different steps such as redissolution, centrifugation, acid hydrolysis, precipitation, boiling, dialysis, and column chromatography followed by successive washing steps with organic solvents such as chloroform, petroleum ether, ethyl acetate, acetone, or absolute ethanol (Aghajanyan et al. 2005; Choi 2021; Dong and Yao 2012; Madhusudhan et al. 2014; Selvakumar et al. 2008; Suryanarayanan et al. 2004). Acid hydrolysis is usually performed using 6 M HCl to remove impurities like carbohydrates and protein associated with melanin pigment, whereas organic solvent aid helps in the removal of secondary metabolites. Non-hydrolyzable melanin are redissolved in NaOH and precipitated out with HCl followed by several washing steps with organic solvent

and deionized water. An additional boiling step helps to avoid the formation of melanoidins (Eskandari and Etemadifar 2021). Dialysis was reportedly used to remove salt and other impurities like low molecular weight organic and inorganic compounds (Wibowo et al. 2022). Finally, washing with absolute ethanol removes water molecules with the melanin pigment. The resulting content is lyophilized and stored as pure melanin. In 2022, one research group purified melanin with help of dialysis tubing and the resulting melanin yield was 670 mg/L, which was significantly higher than the 116 mg/L obtained from the acid precipitation method (Wibowo et al. 2022). The combination of the above-described extraction technologies has been observed to bring synergistic extraction yield compared to the conventional method paving way for the development of more advanced and efficient techniques for melanin extraction and purification.

4 Preliminary Confirmation of Melanin

The melanin pigment is insoluble in water and almost all inorganic/organic solvents. Based on this observation, a solubility test is used for the preliminary confirmation of melanin. Melanin is slightly soluble in dimethyl sulphoxide (DMSO), in water at alkaline pH, phosphate saline buffer (pH 7.2), and on the other hand, melanin gets precipitated at acidic conditions (pH 2) (Kamarudheen et al. 2019; Pralea et al. 2019). Melanin contains different functional groups in the structure like catechol, NH, and COOH that shows reactivity with certain chemicals and shows distinguishable characters helping in the identification of melanin type. When melanin is treated with hydrogen peroxide (H_2O_2), it results in decolorization due to oxidative degradation of melanin. In this reaction, the nucleophilic attack of OOH^- ions from H_2O_2 leads to the production of quinone epoxide causing bleaching of melanin (Korytowski and Sarna 1990). The reduction of AgNO_3 occurs when it reacts with microbial melanin leading to the formation of gray colour on the walls of the test tube due to the precipitation of melanin (Carriel et al. 2011; Lopusiewicz 2018). Similarly, when melanin reacts with KMnO_4 , it leads to a change in color from brown to green with precipitation and decoloration of the solution. The color change is due to the reduction of KMnO_4 by the redox property of melanin. This reaction indicates the presence of quinone and phenol groups in the structure of melanin (Aghajanyan et al. 2005).

Chemical degradation methods are also used in the identification of different types of melanins based on the analysis of their degradation products. Melanin gets degraded by strong oxidants and reductants yielding different types of degraded products. These degraded products are further separated by chromatographic techniques and identification by different spectroscopic techniques (Dzierżęga-Lęcznar et al. 2002). Generally, gas chromatography and mass spectrometry with pyrolysis (Py-GC/MS) are used to identify pyrrole, indole, and their alkyl derivatives as pyrrole di- and tricarboxylic acids are precursors of eumelanin biosynthesis (Dzierżęga-Lęcznar et al. 2002, 2012). Likewise, in the case of pheomelanin,

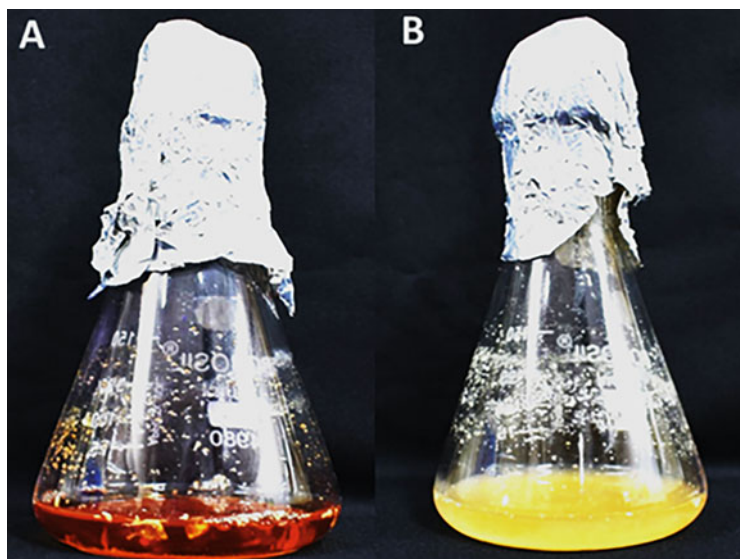


Fig. 1 Melanin synthesis inhibition: control (a) and treatment with kojic acid (b) (Ghadge et al. 2022)

precursors are thiazole or benzothiazole carboxylic acids including some other melanin pigment markers, i.e., isomeric aminohydroxyphenylalanines and aminohydroxyphenylethylamines (Donato and Napolitano 2003; Dzierżęga-Lęcznar et al. 2012; Greco et al. 2009; Ito et al. 2019).

The melanin synthesis inhibition is used to identify the enzyme involved in melanin biosynthesis by the producer strain and type of melanin. The most commonly used inhibitors are kojic acid as a tyrosinase inhibitor, tricyclazole as a DHN-melanin inhibitor, and sodium azide as a laccase inhibitor. Inhibition of melanin synthesis by kojic acid was observed for strains *Actinoalloteichus* sp. MA-32, *Streptomyces hyderabadensis* 7VPT5-5R (Fig. 1) (Ghadge et al. 2022; Manivasagan et al. 2013). The inhibition of melanin-like pigments by sodium azide was previously reported for *Bacillus weihenstephanensis*, *Bacillus subtilis* 4NP-BL (Fig. 2) (Drewnowska et al. 2015; Ghadge et al. 2020). A higher concentration of sodium azide ($>50 \mu\text{g mL}^{-1}$) led to the inhibition of bacterial growth. The inhibition of melanin synthesis is reported in the black yeasts *Trimmatostroma salinum*, *Phaeothea triangularis* and *Hortaea werneckii* by use of tricyclazole, a specific inhibitor for polyketide melanin biosynthesis (Kogej et al. 2003).


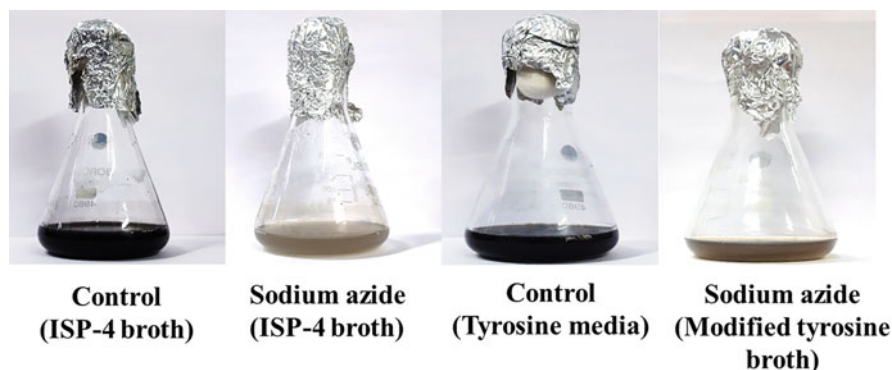


Fig. 2 Inhibition of melanin synthesis by sodium azide (Ghadge et al. 2020)

Fig. 3 UV/vis spectra of purified melanin (black) and synthetic melanin (red) (Ghadge et al. 2022)

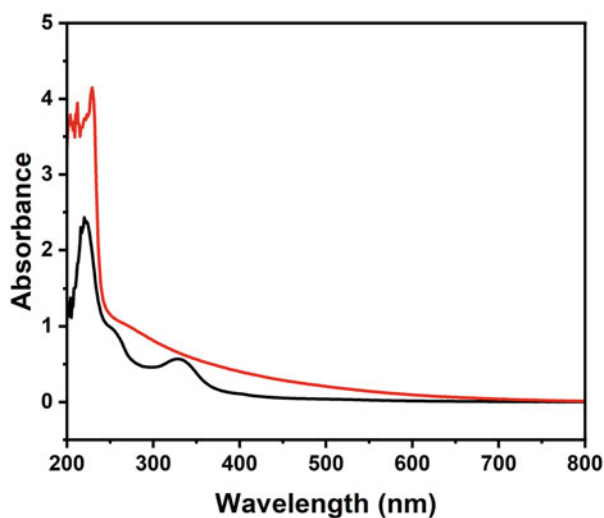

5 Characterization of Melanin

5.1 UV–Visible Spectroscopy

UV/visible spectroscopy is the most common and widely accepted technique used for the primary identification/confirmation of melanin. The absorbance of melanin monotonically increases towards the UV region (high energy). It decreases towards the visible region (low energy radiation), which is a unique characteristic property found in melanin and this property is employed for melanin identification (Fig. 3) (Gao and Garcia-Pichel 2011). Melanin of microbial origin shows maximum absorption in the almost entire UV region (200–400 nm). The ratio of A_{650}/A_{500} is used to quantify eumelanin concentration from the mixture as well as for the differentiation

of eumelanin and pheomelanin. The ratio of melanin above 0.25 is referred as eumelanin, while a ratio below 0.15 is considered pheomelanin (Saini and Melo 2015).

As we know, photoprotection is the main function of eumelanin and it is due to broadband absorption, but its origin is still mysterious. The recent theoretical (computational) and experimental studies indicated that broadband absorption emerges from the chemical disorder of eumelanin due to the chemical diversity of building blocks at the oligomeric level and it is widely accepted (Singh et al. 2021). Based on previous studies, the oligomeric model is most acceptable for the origin of broadband absorption due to the formation of different types of chemically-modified oligomers having different configurations and conformations. These oligomers interact with each other mainly by π - π interactions, which affect the electron delocalization resulting in the absorption spectrum of eumelanin (Arzillo et al. 2012). The different studies speculated that non-covalent interactions play a major role during eumelanin oligomerization in multilevel structural organization, like stacking interactions (π - π) (Chen et al. 2013). The close association of oligomers in a multilevel organized structure determines the alteration of absorption spectra. DHI and DHICA precursors are used to study the aggregation model of eumelanin and its UV/VIS properties to understand broadband absorption (Ju et al. 2018). Their investigation revealed that monomeric units (DHI and DHICA) undergo polymerization from monomer to oligomers and then oligomers form small stacks. These stacked oligomers further oligomerize and stacked to form larger aggregates called protomolecules (Spano 2010). Their findings provided strong support to postulate that broad absorption bands due to delocalization of intrinsic π -electron within integral eumelanin oligomers and altered by other interactions such as attractive stacking between aromatic rings and aggregation in the stratified framework of complex structure (Simpson et al. 2014).

The recent studies on eumelanin supported the hypothesis of an aggregate model of eumelanin but its detailed structure is still unknown due to a lack of experimental proof. Because eumelanin precursor is redox-active and has different polymeric sites it makes it very difficult to understand its structure-property relationship. The complexity and heterogeneity of eumelanin hinder the experimental approaches to understanding its structural and optical properties (Yildirim and Bayindir 2014).

5.2 *Electron Paramagnetic Resonance (EPR)*

“Paramagnetism” is one of the main fundamental properties of eumelanin. Eumelanin is a redox-active macromolecule due to the presence of indolequinone group precursor molecule 5,6-dihydroxyindole (DHI) and 5,6-dihydroxyindole-2-carboxylic acid (DHICA). Eumelanin contains different paramagnetic centers, which is due to quinone groups in the structure (Gessler et al. 2014). Recent studies on eumelanin identified two types of paramagnetic centers in solid-state- and liquid-state. These centers are differentiated from each other by their g -factors and

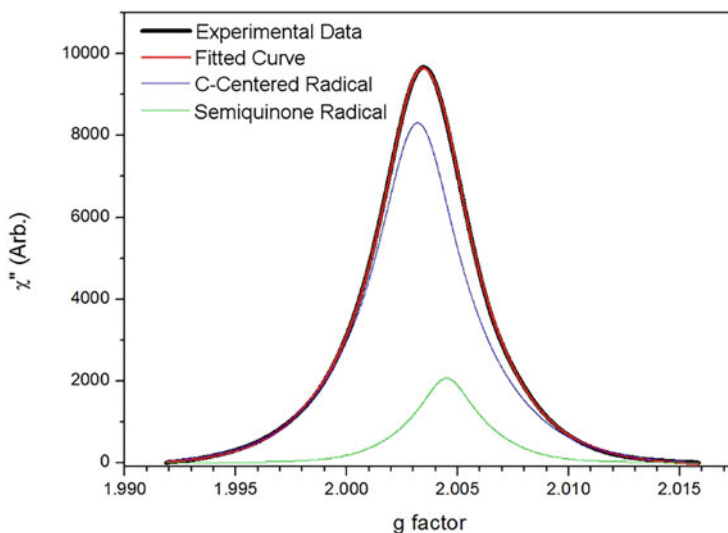


Fig. 4 Deconvolution of the integrated EPR spectrum associated with the basic sample. The spectrum is best explained by the presence of two free radicals, the more dominant carbon-centered signal ($g = 2.0032$) and the small semiquinone signal ($g = 2.0045$). Data at a water content of 14.0% and microwave power of 0.71 mW/2 (Mostert et al. 2013)

line shapes (Paulin et al. 2019). It is hypothesized that carbon-centered radicals (CCR) come from the internal skeleton of the eumelanin structure, and it is prevented by the external environment (Paulin et al. 2021a). CCRs were mainly found in solid samples (dry powder) and they are less affected by temperature and pH. The semiquinone free radicals (SFR) are observed in the liquid state (solution) and strongly affected (change in intensity of signal) by pH. Furthermore, these two types of free radicals have constant g -factors, 2.003 for CCR and 2.005 for SFR (Fig. 4).

Paulin et al. 2019 performed experimental and theoretical work on the paramagnetic behavior of melanin. They used a computational model (DFT) to compare g -factors and hyperfine coupling constants to correlate the structure and free radical centers of melanin. The precursors of eumelanin, DHI, and DHICA, are redox-active molecules with different redox states (Fig. 5), containing both positive and negative charged states having an unpaired electronic and zwitterionic state of an odd number of electrons (Cuba et al. 2021).

The results show that the partially oxidized molecules (indolequinone and semiquinone) are associated with semiquinone free radicals (SFR), while fully reduced state (hydroquinone) and nitrogen-protonated species (DHICA) are associated with carbon-centered radicals (CCR). The positively charged species are referred to as a secondary product of eumelanin and such types of species are found in eumelanin derivatives (Paulin et al. 2019). The results revealed that the

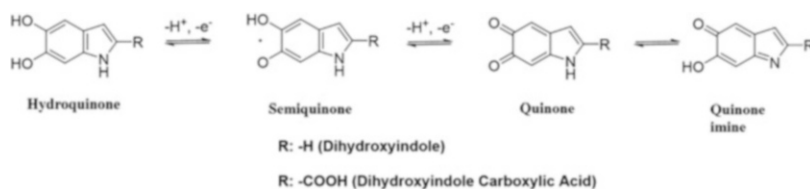


Fig. 5 Different redox forms of melanin monomeric structures: R = H (DHI) or COOH (DHICA) (Realí et al. 2021)


presence of three types of EPR signals comes from typical eumelanin structures. Based on experimental data, it is observed that the EPR signals of CCR from two precursors DHI and DHICA can be differentiated. In this work, the main focus was on the differentiation of paramagnetic species present in eumelanin. The experimental results of EPR spectra of eumelanin and its precursor molecules (DHI and DHICA) revealed that it contains three different types of free radicals, among them, two are CCRs and another is SFR. Investigation of EPR variables and energy state of different substructures of eumelanin indicated that the carbon-centered radicals (CCRs) mainly come from the reduced state of eumelanin structural organization (Paulin et al. 2019, 2021a).

Eumelanin is associated with the presence of *O*-semiquinone radicals, while pheomelanin contains *O*-semiquinoneimine radicals. EPR spectrum can distinguish different types of melanins, eumelanin shows a single line with a hyperfine shape at variable temperature (low to high) and is less affected by microwave power, while that of pheomelanin has a complex line shape with hyperfine structure arising through the interplay between free electrons with electrons of adjacent nitrogen nuclei (Zdybel et al. 2017). Natural melanin can be differentiated from synthetic melanin by observing spectral patterns and line width. These characteristic differences in line shape and width of the EPR spectrum were used to distinguish natural melanin from synthetic melanin.

5.3 Electrical Properties of Melanin

Melanin has two main properties, broadband absorption, and redox activity, which are responsible for electric charge conduction. The property of melanin to conduct electrical charge was studied in the 1970s, and its semiconducting charge behavior was demonstrated by Mott-Davis amorphous semiconductor (MDAS) theory (McGinness 1972; McGinness et al. 1974; Powell and Rosenberg 1970). The electric conductivity of melanin is due to the presence of different functional groups (carboxylates, aromatic amines, and catechols) having different redox states which generate protons and electrons during oxidation-reduction reactions. The various types of charge transport mechanisms are reported to be present in eumelanin i.e. intra- and inter-atomic interaction (H-bonding), and π - π interaction (Gouda

Fig. 6 The comproportionation equilibrium reaction involves two steps: hydroquinone deprotonates leading to hydronium formation; and the hydroquinone reacts with a quinone in a 1-electron redox reaction to form semiquinone radicals, a moiety of an intermediate oxidative state (Sheliakina et al. 2018)

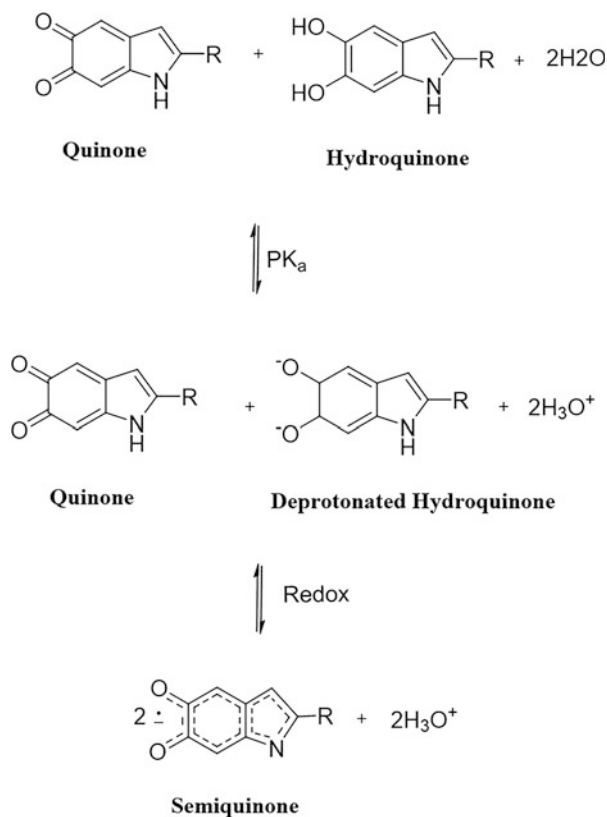

et al. 2020). The current charge transport model of melanin was explained by comproportionation equilibrium (Fig. 6), where quinone and hydroquinone species react in the presence of water to generate semiquinone species and protons. From recent work, it is observed that the previous amorphous semiconductor model is replaced by the comproportionation equilibrium model in which the formation of free radicals (electron) and hydronium ions (protons) takes place where hydronium ions are mobile charge carriers showing hybrid ionic-electronic behavior (Mostert et al. 2012; Sheliakina et al. 2018; Tian et al. 2019).

5.4 Fourier-Transform Infrared Spectroscopy (FT-IR)

FT-IR spectroscopy utilizes the infrared part of the spectrum comprising wavelengths from 4000 to 700 cm^{-1} . Absorption of a specific wavelength in the infrared spectrum is a characteristic of functional groups. This absorption in the infrared spectrum varied by wavelength and intensity is measured by FT-IR spectroscopy and these details are used to detect the presence of different functional groups in

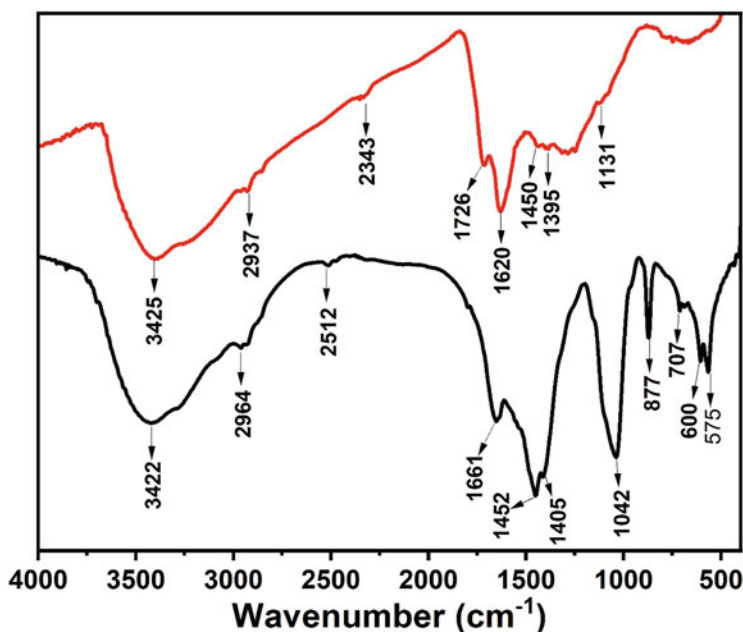


Fig. 7 FT-IR spectra of purified melanin (black) and synthetic melanin (red) (Ghadge et al. 2022)

given samples (Mbonyiriyivu et al. 2015). The complexity of melanin structure made it difficult to study using spectrometry techniques. Melanin has functional groups like amides, hydroxy, carboxylic, phenolics, aromatic rings, aliphatic carbon, and indole ring. Given the different functional groups present in the melanin, FT-IR can serve as a technique for the identification of melanin, detection of impurity, metal conjugation, and type of melanin (Sajjan et al. 2013). A careful investigation of the literature reveals some signature patterns of melanin in IR spectra. A broad peak of O–H and N–H stretching in the range of $3600\text{--}2800\text{ cm}^{-1}$, a sharp peak due to stretching of CH_3 group in the range of $2900\text{--}3000\text{ cm}^{-1}$. In some cases of eumelanin, CH_3 and CH_2 stretching absorption give 2 to 3 peaks in the range of $2800\text{--}3000\text{ cm}^{-1}$, these peaks are generally small and fall in the broad peak of O–H and N–H stretching. Stretching of C=O , C=C , and COO^- represented by a sharp deep peak in the range of $1620\text{--}1650\text{ cm}^{-1}$. Next to this small peak in the range of $1500\text{--}1600\text{ cm}^{-1}$, there is a characteristic peak of melanin having an indole ring due to the bending of the N–H group. Other characteristic peaks of melanin in the range of $1400\text{--}1500\text{ cm}^{-1}$ are due to aliphatic carbons. In this range, peaks appear due to C–H, $\text{CH}_2\text{--CH}_3$ bending vibration. The phenolic stretching vibration of microbial melanin gives a small peak in the range of $1200\text{--}1300\text{ cm}^{-1}$. Weak peaks in the range of $900\text{--}600\text{ cm}^{-1}$ are due to N–H wagging, aromatic C–H, and the substitution of alkene C–H (Ammanagi et al. 2021; El-Naggar and El-Ewasy 2017; Ghadge et al. 2020; Vasanthabharathi et al. 2011) (Fig. 7).

5.5 X-Ray Photoelectron Spectroscopy (XPS)

XPS is used to analyze the elemental composition and state of elements on the surface of the solid samples. Due to the problems in solubility of the melanin, XPS is quite a handy technique to analyze the composition, hybridization, oxidation state of elements, and conformation of functional groups present in the melanin. To analyze the average surface chemistry of the sample, XPS uses low energy X-ray (Soft X-ray). This low-energy photon then generates a photoelectron from the atoms present on the sample surface. Thus, XPS utilizes the difference in the binding energy of the electrons in different atoms by measuring the kinetic energy of the photoelectron emitted from the sample surface and uses this data to generate the information about surface chemistry of the sample (Van der Heide 2011).

Selection of the energy range of photoelectrons allowed screening of one element at a time. Each atomic orbit of every element has characteristic binding energy, thus giving a specific peak for every atom. The binding energy of electrons depends on the chemical and physical environment of the atom. This helps in the identification of different types of bonds formed by elements in the material. For example, in the process of screening of C1s photoelectron, the presence of C–O–C, C=O, C=OH, –O–C=O, –O–CO–O will cause the sifting of the peak, while the main peak consists of signals of C–C, C=C, and CH (Bregadiolli et al. 2021). The values for different states of elements or chemical shifts are available in databases like ‘The International XPS Database’ (<https://xpsdatabase.com/>).

A study on the eumelanin from four different sources using XPS gives an insight into the structure of the composition and structural differences among them. Elemental composition of the natural eumelanin from sepia, crow feather, turkey feather, and human hair gives us a range of composition in eumelanin like carbon 66.3–67.4%, oxygen 18.8–22.2%, and nitrogen 8.7–12.9%. Natural eumelanin is made up of DHI, DHICA, and their derivatives, so the calculation of the ratio between C=O and O–C=O and the amount and concentration of O–C=O is directly equal to the amount of DHICA and its oxidized forms of monomers. The scanning of the C1s will give the largest peak at 285 eV, peak fitting of this peak can be done using chemical shifts for C–C(H) at $284.9 + 0.2$ eV, C–OH/C–N $286.3 + 0.2$ eV, C=O at $288.1 + 0.2$ eV, O–C=O at $289.3 + 0.2$ eV approximately (Xiao et al. 2018).

The surface layer of the material is susceptible to absorption of water, CO, and oxidative modification, which can result in the wrong quantification of the composition of melanin. The problem of surface modification can be eliminated by a cluster beam of 500 Argon ions (Paulin et al. 2021b).

5.6 Raman Spectroscopic Analysis

Peak around 1590 cm^{-1} denoted the stretching vibrations of aromatic C=C bond in the indole ring. Bands around 1690 cm^{-1} arise due to quinone C=O stretching.

Signals around 1510 cm^{-1} are related to the C=N stretching. The band around 1341 cm^{-1} is observed due to aromatic C–N stretching of the indole structure. C–O stretching of the carboxylic acid is visible at about 1220 cm^{-1} (Capozzi et al. 2005).

Four bands were found to be visible in the spectrum of pheomelanin in the range of $500\text{--}2000\text{ cm}^{-1}$. A band around wavenumber 500 cm^{-1} is considered an out-of-plane deformation of the phenyl ring in the benzothiazine structure. The stretching vibrations of the C–N bond are also observed in pheomelanin at about 1150 cm^{-1} . Stretching vibrations of phenyl ring arise in the Raman spectrum at around 1490 cm^{-1} . High Raman intensity in the range of $1750\text{--}2000\text{ cm}^{-1}$ is considered the characteristic pattern for the pheomelanin because eumelanin shows a flat line in this region (Galvan et al. 2013).

5.7 Nuclear Magnetic Resonance (NMR) Spectroscopy

There are four major classes of melanin named eumelanin, pheomelanin, allomelanin, and pyromelanin. The basic moiety of the eumelanin structure is comprised of 5,6-dihydroxy indole (DHI) and 5,6-dihydroxy indole carboxylic acid (DHICA). The monomeric unit in the pheomelanin is composed of a benzothiazine ring. Allomelanin is made up of the 1,8-dihydroxy naphthalene moiety. These structural differences within the different types of melanin are observed due to variations in the precursor moiety or intermediate compounds during melanin production. Spectroscopic data is important to study the structural characteristics of melanin. ^1H NMR and ^{13}C NMR are widely used techniques to determine the structural features of melanin.

^1H NMR spectrum of eumelanin showed prominent peaks of resonance around 7.286 and 7.21 ppm (Fig. 8) which are attributed to the indole/pyrrole ring. –NH groups of melanin moiety give signals around 8.00 ppm as a singlet. Peaks in the range of 3.4 and 4.4 ppm are ascribed to the protons attached to the methyl or methylene group, which are attached to nitrogen and/or oxygen atoms. Signals at 2.2 and 2.8 ppm provide evidence for the presence of the methylene group. Signals at 1.00 and 3.00 ppm denoted the presence of the –NH group lined to the indole. Resonance signals around 0.9–1.00 ppm are described for aliphatic fragments such as CH_2CH_3 and $\text{CH}(\text{CH}_3)_2$ (Barretto and Vootla 2020; Ghadge et al. 2020). In the ^{13}C NMR spectrum, peaks in the range of 120–140 ppm are due to the aromatic carbons involved in the indole or pyrrole system. The peaks from 50–60 ppm arise due to the carbon atom linked to the nitrogen. The peaks for the methyl and methylene groups are observed within the 10–40 ppm range.

^{13}C NMR spectra of pheomelanin show characteristic peaks from 30–70 ppm which resemblance to = C–S and C–H from the aliphatic chain present in cysteine. Resonance around 170–200 ppm is attributed to the carbonyl carbon. Signals around 110–160 are observed in the spectra indicating the presence of aromatic carbons (De Souza et al. 2018).

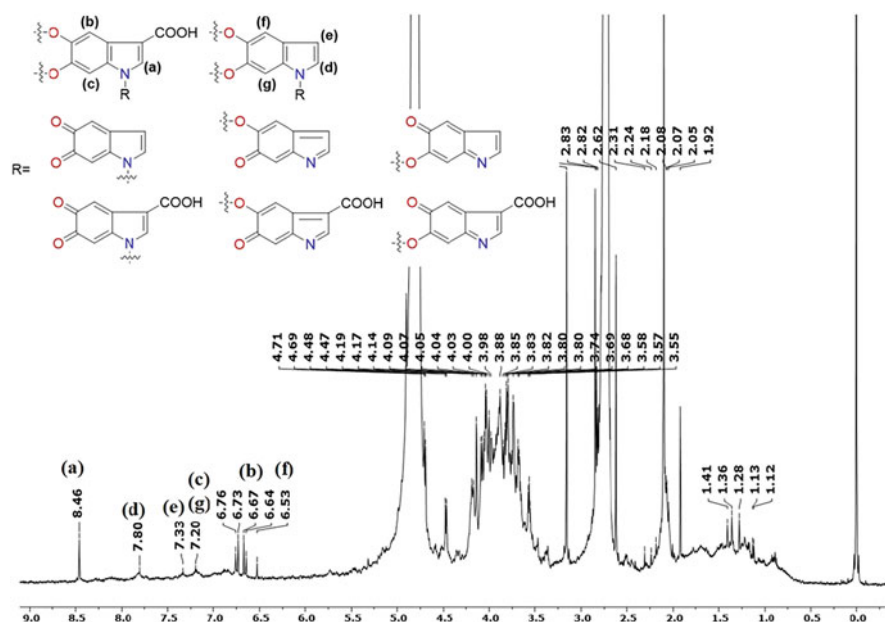


Fig. 8 ^1H NMR spectrum of the purified melanin (Ghadge et al. 2022)

In the past literature, allomelanin was characterized by Cross-Polarization Magic-angle spinning (CP/MAS) NMR spectroscopy. ^{13}C spin echo (SE) CP/MAS NMR spectrum shows a broad range of peaks from 100 to 160 ppm due to the presence of protonated and non-protonated aromatic carbons. Peaks in the range of 20–40 ppm are due to the protonated aliphatic carbon (Singla et al. 2021). A characteristic peak of phenoxy carbon can also be found at around 152 ppm in the solid-state NMR (Zhou et al. 2019).

6 Conclusion

Microorganisms can produce different types of melanin and utilize a variety of precursor molecules for synthesis. Heterogeneity due to different sources, metabolic pathways, and precursor molecules has resulted in the complex supramolecular structure of melanin. Microbial melanin has gained interest due to its diverse functions within the host and various biological activities and also it has an advantage over other sources of melanin for production due to scalability, sustainability, and cheaper production cost. Despite such importance of melanin, its commercial utilization is restricted due to its insolubility, and low yield which results in higher production costs. The extraction and purification of melanin is a difficult job due to its diverse origin, location, and complex structure. So, there is an urgent need to

develop sustainable extraction methods which will increase the yield and solubility of melanin. The complexity and heterogeneity of melanin are the main hurdles for structure elucidation, which will need the use of different modern analytical techniques and approaches. This book chapter covers microbial melanin production, extraction techniques, and its structural properties through different analytical techniques. Due to the multifunctionality and biocompatibility of melanin, it has become a tunable biomaterial of application in various fields. Still, the fundamental structural-property relationship is not fully understood which will attract the researchers and has scope for further development.

Acknowledgments Vishal Ghadge thanks SERB-DST for a project fellowship (GAP-2050 and GAP-2057), Sanju Singh, Doniya Elze Mathew, Asmita Dhimmar acknowledges CSIR-JRF fellowship from the Council of Scientific and Industrial Research (CSIR), Pankaj Kumar and Apexa Gajjar acknowledges DBT-JRF fellowship from Department of Biotechnology (DBT), and Harshal Sahastrabudhe acknowledges GATE-JRF fellowship from Council of Scientific and Industrial Research (CSIR).

Funding This research was supported by the Scientific and Engineering Research Board (SERB), Department of Science and Technology [ECRA/2016/000788 and EEQ/2016/000268]; and Council of Scientific and Industrial Research [MLP/0027].

References

- Abbas M, D'Amico F, Morresi L, Pinto N, Ficcadenti M, Natali R, Ottaviano L, Passacantando M, Cuccioloni M, Angeletti M, Gunnella R (2009) Structural, electrical, electronic and optical properties of melanin films. *Eur Phys J* 28:285–291
- Aghajanyan AE, Hambardzumyan AA, Hovsepyan AS, Asaturian RA, Vardanyan AA, Saghiyan AA (2005) Isolation, purification and physicochemical characterization of water-soluble *Bacillus thuringiensis* melanin. *Pigment Cell Res* 18:30–135
- Aghajanyan AE, Vardanyan AA, Hovsepyan AC, Hambardzumyan AA, Filipenia V, Saghyan AC (2017) Development of technology for obtaining water-soluble bacterial melanin and determination of some of pigment properties. *Biotechnologia* 98:315–322
- Ammanagi A, Shivasharana CT, Badiger A, Ramaraj V (2021) Functional and structural characterization of melanin from *Brevibacillus invocatus* strain IBA. *Dokl Biol Sci* 500:159–169
- Arzillo M, Mangiapia G, Pezzella A, Heenan RK, Radulescu A, Paduano L, d'Ischia M (2012) Eumelanin buildup on the nanoscale: aggregate growth/assembly and visible absorption development in biomimetic 5,6-dihydroxyindole polymerization. *Biomacromolecules* 13:2379–2390
- Barretto DA, Vootla SK (2020) Biological activities of melanin pigment extracted from *Bombyx mori* gut-associated yeast *Cryptococcus rajasthanensis* KY627764. *World J Microbiol Biotechnol* 36:159
- Borovansky J, Riley PA (2011) Melanins and melanosomes: biosynthesis, structure, physiological and pathological functions. Wiley-VCH, Australia
- Bothma JP, De Boor J, Divakar U, Schwenn PE, Meredith P (2008) Device quality electrically conducting melanin thin films. *Adv Mater* 20:3539–3542
- Bregadiolli BA, Paulin JV, Albano LGS, Martins LM, De Camargo DHS, da Silva-Filho LC, Bufon CCB, de Oliveira Graeff CF (2021) A strategy towards melanin-based functional material: rGO and sulfonated melanin composites. *J Mater Chem C* 9:16991–17002

- Cao W, Zhou X, McCallum NC, Hu Z, Ni QZ, Kapoor U, Heil CM, Cay KS, Zand T, Mantanona AJ, Jayaraman A, Dhinojwala A, Deheyn DD, Shawkey MD, Burkart MD, Rinehart JD, Gianneschi NC (2021) Unraveling the structure and function of melanin through synthesis. *J Am Chem Soc* 143:2622–2637
- Capozzi VITO, Perna G, Gallone A, Biagi PF, Carmone P, Fratello A, Guida G, Zanna P, Cicero R (2005) Raman and optical spectroscopy of eumelanin films. *J Mol Struct* 744:717–721
- Carriel VS, Aneiros-Fernandez J, Arias-Santiago S, Garzón IJ, Alaminos M, Campos A (2011) A novel histochemical method for a simultaneous staining of melanin and collagen fibers. *J Histochem Cytochem* 59:270–277
- Chen CT, Ball V, de Almeida GJJ, Singh MK, Toniazzo V, Ruch D, Buehler MJ (2013) Self-assembly of tetramers of 5,6-dihydroxyindole explains the primary physical properties of eumelanin: experiment, simulation, and design. *ACS Nano* 7:1524–1532
- Choi KY (2021) Bioprocess of microbial melanin production and isolation. *Front Bioeng Biotechnol* 9:765110
- Chuyen HV, Nguyen MH, Roach PD, Golding JB, Parks SE (2018) Microwave-assisted extraction and ultrasound-assisted extraction for recovering carotenoids from Gac peel and their effects on antioxidant capacity of the extracts. *Food Sci Nutr* 6:189–196
- Cuba JP, Alves GG, Galindo LA, Paulin JV, Batagin-Neto A (2021) Sulfonated melanin derivatives: theoretical evaluation of local reactivities and chemical structures. *J Mol Model* 27:362
- Dadachova E, Bryan RA, Huang X, Moadel T, Schweitzer AD, Aisen P, Nosanchuk JD, Casadevall A (2007) Ionizing radiation changes the electronic properties of melanin and enhances the growth of melanized fungi. *PLoS One* 2:e457
- De Souza RA, Kamat NM, Nadkarni VS (2018) Purification and characterisation of a Sulphur rich melanin from edible mushroom *Termitomyces albuminosus* Heim. *Mycology* 9:296–306
- Donato PD, Napolitano A (2003) 1,4-Benzothiazines as key intermediates in the biosynthesis of red hair pigment pheomelanins. *Pigment Cell Res* 16:532–539
- Dong C, Yao Y (2012) Isolation, characterization of melanin derived from *Ophiocordyceps sinensis*, an entomogenous fungus endemic to the Tibetan Plateau. *J Biosci Bioeng* 113:474–479
- Drewnowska JM, Zambrzycka M, Kalska-Szostko B, Fiedoruk K, Swiecicka I (2015) Melanin-like pigment synthesis by soil *Bacillus weihenstephanensis* isolates from Northeastern Poland. *PLoS One* 10:e0125428
- Dzierżęga-Lęcznar A, Chodurek E, Stępień K, Wilczok T (2002) Pyrolysis-gas chromatography-mass spectrometry of synthetic neuromelanins. *J Anal Appl Pyrolysis* 62:239–248
- Dzierżęga-Lęcznar A, Kurkiewicz S, Stępień K (2012) Detection and quantitation of a pheomelanin component in melanin pigments using pyrolysis–gas chromatography/tandem mass spectrometry system with multiple reaction monitoring mode. *J Mass Spectrom* 47:242–245
- El-Naggar NEA, El-Ewasy SM (2017) Bioproduction, characterization, anticancer and antioxidant activities of extracellular melanin pigment produced by newly isolated microbial cell factories *Streptomyces glaucescens* NEAE-H. *Sci Rep* 7:42129
- Eskandari S, Etemadifar Z (2021) Biocompatibility and radioprotection by newly characterized melanin pigment and its production from *Dietzia schimae* NM3 in optimized whey medium by response surface methodology. *Ann Microbiol* 71:17
- Galvan I, Jorge A, Solano F, Wakamatsu K (2013) Vibrational characterization of pheomelanin and trichochrome F by Raman spectroscopy. *Spectrochim Acta A Mol Biomol Spectrosc* 110:55–59
- Gao Q, Garcia-Pichel F (2011) Microbial ultraviolet sunscreens. *Nat Rev Microbiol* 9:791–802
- Gessler NN, Egorova AS, Belozerskaya TA (2014) Melanin pigments of fungi under extreme environmental conditions. *Appl Biochem Microbiol* 50:105–113
- Ghadge V, Kumar P, Maity TK, Prasad K, Shinde PB (2022) Facile alternative sustainable process for the selective extraction of microbial melanin. *ACS Sustain Chem Eng* 10:2681–2688
- Ghadge V, Kumar P, Singh S, Mathew DE, Bhattacharya S, Nimse SB, Shinde PB (2020) Natural melanin produced by the endophytic *Bacillus subtilis* 4NP-BL associated with the halophyte *Salicornia brachiata*. *J Agric Food Chem* 68:6854–6863

- Gómez-Marín AM, Sánchez CI (2010) Thermal and mass spectroscopic characterization of a sulphur-containing bacterial melanin from *Bacillus subtilis*. *J Non-Cryst Solids* 356:1576–1580
- Gosset G (2017) Biotechnological production of melanins with microorganisms. In: Singh OV (ed) *Bio-pigmentation and biotechnological implementations*. Wiley, pp 161–171
- Gouda A, Soavi F, Santato C (2020) Eumelanin electrodes in buffered aqueous media at different pH values. *Electrochim Acta* 347:136250
- Greco G, Wakamatsu K, Panzella L, Ito S, Napolitano A, d'Ischia M (2009) Isomeric cysteinylidopas provide a (photo) degradable bulk component and a robust structural element in red human hair pheomelanin. *Pigment Cell Melanoma Res* 22:319–327
- Haining RL, Achat-Mendes C (2017) Neuromelanin one of the most overlooked molecules in modern medicine, is not a spectator. *Neural Regen Res* 12:372–375
- Hou R, Liu X, Xiang K, Chen L, Wu X, Lin W, Zheng M, Fu J (2019) Characterization of the physicochemical properties and extraction optimization of natural melanin from *Inonotus hispidus* mushroom. *Food Chem* 277:533–542
- Hu WL, Dai DH, Huang GR, Zhang ZD (2015) Isolation and characterization of extracellular melanin produced by *Chroogomphus rutilus* D447. *Am J Food Technol* 10:68–77
- Ito S, Kolbe L, Weets G, Wakamatsu K (2019) Visible light accelerates the ultraviolet A-induced degradation of eumelanin and pheomelanin. *Pigment Cell Melanoma Res* 32:441–447
- Ju KY, Fischer MC, Warren WS (2018) Understanding the role of aggregation in the broad absorption bands of eumelanin. *ACS Nano* 12:12050–12061
- Kamarudheen N, Naushad T, Rao KVB (2019) Biosynthesis, characterization and antagonistic applications of extracellular melanin pigment from marine *Nocardiopsis Sps*. *Indian J Pharm Educ Res* 53:112–120
- Kogej T, Wheeler MH, Rižner TL, Gunde-Cimerman N (2003) Inhibition of DHN-melanin biosynthesis by tricyclazole in *Hortaea werneckii*. In: *Non-conventional yeasts in genetics, biochemistry and biotechnology*. Springer, Heidelberg, pp 143–148
- Korytowski W, Sarna T (1990) Bleaching of melanin pigments. Role of copper ions and hydrogen peroxide in autooxidation and photooxidation of synthetic dopa-melanin. *J Biol Chem* 265: 12410–12416
- Lopusiewicz L (2018) *Scleroderma citrinum* melanin: isolation, purification, spectroscopic studies with characterization of antioxidant, antibacterial and light barrier properties. *World Sci News* 94:114–129
- Lu Y, Ye M, Song S, Li L, Shaikh F, Li J (2014) Isolation, purification, and anti-aging activity of melanin from *Lachnum singerianum*. *Appl Biochem Biotechnol* 174:762–771
- Madhusudhan DN, Mazhari BBZ, Dastager SG, Agsar D (2014) Production and cytotoxicity of extracellular insoluble and droplets of soluble melanin by *Streptomyces lusitanus* DMZ-3. *Biomed Res Int* 2014:2014
- Manivasagan P, Venkatesan J, Senthilkumar K, Sivakumar K, Kim SK (2013) Isolation and characterization of biologically active melanin from *Actinoalloteichus sp.* MA-32. *Int J Biol Macromol* 58:263–274
- Martínez LM, Martínez A, Gosset G (2019) Production of melanins with recombinant microorganisms. *Front Bioeng Biotechnol* 7:285
- Mbonyiriyivuze A, Mwakikunga BW, Dhlamini SM, Maaza M (2015) Fourier transform infrared spectroscopy for sepia melanin. *Mater Chem Phys* 3:25–29
- McGinness J, Corry P, Proctor P (1974) Amorphous semiconductor switching in melanins. *Science* 183:853–855
- McGinness JE (1972) Mobility gaps: a mechanism for band gaps in melanins. *Science* 177:896–897
- Mostert A, Hanson G, Sarna T, Gentle I, Powell BJ, Meredith P (2013) Hydration-controlled X-band EPR spectroscopy: A tool for unravelling the complexities of the solid-state free radical in eumelanin. *J Phys Chem B* 117:4965–4972
- Mostert AB, Powell BJ, Pratt FL, Hanson GR, Sarna T, Gentle IR, Meredith P (2012) Role of semiconductivity and ion transport in the electrical conduction of melanin. *Proc Natl Acad Sci* 109:8943–8947

- Nicolaus RA (1968) Melanins. Herman Press, Paris
- Panda D, Manickam S (2019) Cavitation technology—the future of greener extraction method: A review on the extraction of natural products and process intensification mechanism and perspectives. *Appl Sci* 9:766
- Paulin JV, Batagin-Neto A, Graeff CF (2019) Identification of common resonant lines in the EPR spectra of melanins. *J Phys Chem B* 123:1248–1255
- Paulin JV, Batagin-Neto A, Naydenov B, Lips K, Graeff CF (2021a) High-field/high-frequency EPR spectroscopy on synthetic melanin: on the origin of carbon-centered radicals. *Adv Mater Sci* 2:6297–6305
- Paulin JV, McGettrick JD, Graeff CFO, Mostert AB (2021b) Melanin system composition analyzed by XPS depth profiling. *Surf Interfaces* 24:101053
- Pavan ME, Lopez NI, Pettinar IMJ (2020) Melanin biosynthesis in bacteria, regulation and production perspectives. *Appl Microbiol Biotechnol* 104:1357–1370
- Powell MR, Rosenberg B (1970) The nature of the charge carriers in solvated biomacromolecules. *J Bioenerg* 1:493–509
- Pralea IE, Moldovan RC, Petrache AM, Ilies M, Heghes SC, Ielciu I, Nicoara R, Moldovan M, Ene M, Radu M, Uifalean A, Iuga CA (2019) From extraction to advanced analytical methods: the challenges of melanin analysis. *Int J Mol Sci* 20:3943
- Realí M, Saini P, Santato C (2021) Electronic and protonic transport in bio-sourced materials: a new perspective on semiconductivity. *Adv Mater Sci Eng* 2:15–31
- Saini AS, Melo JS (2015) One-pot green synthesis of eumelanin: process optimization and its characterization. *RSC Adv* 5:47671–47680
- Sajjan S, Kulkarni G, Yaligara V, Lee K, Karegoudar TB (2010) Purification and physiochemical characterization of melanin pigment from *Klebsiella sp.* *J Microbiol Biotechnol* 20:1513–1520
- Sajjan SS, Anjaneya O, Kulkarni GB, Nayak AS, Mashetty SB, Karegoudar TB (2013) Properties and functions of melanin pigment from *Klebsiella sp.* *Microbiol Biotechnol Lett* 4:60–69
- Selvakumar P, Rajasekar S, Periasamy K, Raaman N (2008) Isolation and characterization of melanin pigment from *Pleurotus cystidiosus* (telomorph of *Antromyces macrocarpa*). *World J Microbiol Biotechnol* 24:2125–2131
- Sheliakina M, Mostert AB, Meredith P (2018) Decoupling ionic and electronic currents in melanin. *Adv Funct Mater* 28:1–7
- Simpson MJ, Wilson JW, Robles FE, Dall CP, Glass K, Simon JD, Warren WS (2014) Near-infrared excited state dynamics of melanins: the effects of iron content, photo- damage, chemical oxidation, and aggregate size. *J Phys Chem A* 118:993–1003
- Singh S, Nimse SB, Mathew DE, Dhimmara A, Sahastrabudhe H, Gajjar A, Ghadge VA, Shinde PB (2021) Microbial melanin: recent advances in biosynthesis, extraction, characterization, and applications. *Biotechnol Adv* 53:107773
- Singla S, Htut KZ, Zhu R, Davis A, Ma J, Ni QZ, Burkart MD, Maurer C, Miyoshi T, Dhinojwala A (2021) Isolation and characterization of allomelanin from pathogenic black knot fungus—a sustainable source of melanin. *ACS Omega* 6:35514–35522
- Spano FC (2010) The spectral signatures of frenkel polarons in H- and J-aggregates. *Acc Chem Res* 43:429–439
- Stepien K, Dzierzega-Lecznar A, Tam I, Kurkiewicz S (2013) Structure and biological activity of natural melanin pigments. In: Bramhchari G (ed) Chemistry and pharmacology of naturally occurring bioactive compounds. CRC Press, Florida, pp 211–238
- Sun S, Zhang X, Sun S, Zhang L, Shan S, Zhu H (2016) Production of natural melanin by *Auricularia auricula* and study on its molecular structure. *Food Chem* 190:801–807
- Suryanarayanan TS, Ravishankar JP, Venkatesan G, Murali TS (2004) Characterization of the melanin pigment of a cosmopolitan fungal endophyte. *Mycol Res* 108:974–978
- Tarangini K, Mishra S (2014) Production of melanin by soil microbial isolate on fruit waste extract: two step optimization of key parameters. *Biotechnol Rep* 4:139–146
- Tatke P, Jaiswal Y (2011) An overview of microwave assisted extraction and its applications in herbal drug research. *J Med Plant Res* 5:21–31

- Tian Z, Hwang W, Kim YJ (2019) Mechanistic understanding of monovalent cation transport in eumelanin pigments. *J Mater Chem B* 7:6355–6361
- Van der Heide P (2011) X-ray photoelectron spectroscopy: an introduction to principles and practices. Wiley, New york
- Vasanthabharathi V, Lakshminarayanan R, Jayalakshmi S (2011) Melanin production from marine *Streptomyces*. *Afr J Biotechnol* 10:11224–11234
- Wibowo JT, Kellermann MY, Petersen LE, Alfiansah YR, Lattyak C, Schupp PJ (2022) Characterization of an insoluble and soluble form of melanin produced by *Streptomyces cavourensis* SV 21, a sea cucumber associated bacterium. *Mar Drugs* 20:54
- Xiao M, Chen W, Li W, Zhao J, Hong YL, Nishiyama Y, Miyoshi T, Shawkey MD, Dhinojwala A (2018) Elucidation of the hierarchical structure of natural eumelanins. *J R Soc Interface* 15: 20180045
- Yildirim A, Bayindir M (2014) Turn-on fluorescent dopamine sensing based on in situ formation of visible light emitting polydopamine nanoparticles. *Anal Chem* 86:5508–5512
- Youngchim S, Morris-Jones R, Hay RJ, Hamilton AJ (2004) Production of melanin by *Aspergillus fumigatus*. *J Med Microbiol* 53:175–181
- Zdybel M, Pilawa B, Drewnowska JM, Swiecicka I (2017) Comparative EPR studies of free radicals in melanin synthesized by *Bacillus weihenstephanensis* soil strains. *Chem Phys Lett* 679:185–192
- Zhou X, McCallum NC, Hu Z, Cao W, Gnanasekaran K, Feng Y, Stoddart JF, Wang Z, Gianneschi NC (2019) Artificial allomelanin nanoparticles. *ACS Nano* 13:10980–10990
- Zou Y, Xie C, Fan G, Gu Z, Han Y (2010) Optimization of ultrasound-assisted extraction of melanin from *Auricularia auricula* fruit bodies. *Innovative Food Sci Emerg Technol* 11:611–615

Exploiting Melanin-Metal Interactions for Emerging Technologies



Yasser Matos-Peralta , Zhaojing Gao , Afzal Ahmed Dar,
and Clara Santato 

Abbreviations

DHI	5,6-dihydroxyindole
DHICA	5,6-dihydroxyindole 2-carboxylic acid
HOMO	Highest Occupied Molecular Orbital
LUMO	Lowest Unoccupied Molecular Orbital
OECT	Organic ElectroChemical Transistor
PEDOT:PSS	Poly(3,4-ethylenedioxythiophene)-poly(styrenesulfonate)
WEEE (e-waste)	Waste electrical and electronic equipment
XPS	X-ray Photoelectron Spectroscopy

1 Introduction

Electronics have dramatically impacted the everyday life, at the global level. The use of organic electronic materials extracted from natural sources (biosourced) opens new venues for electronics: less relying on critical chemical elements and eco-designed in terms of end-of-life scenarios, possibly including compostability (Santato and Alarco 2022). Organic electronic materials can sustain ionic and electronic transport, with implications in the concept itself of semiconductivity (Reali et al. 2021). Melanins are a family of biopigments relevant for sustainable organic electronics. Among melanins, eumelanin has been the member of the family most investigated by physicists, materials scientists and physical chemists (Reali et al. 2020, 2021). Eumelanin features a range of functional properties, such as ionic

Y. Matos-Peralta · Z. Gao · A. A. Dar · C. Santato (✉)
Engineering Physics, Polytechnique Montréal, Montréal, Québec, Canada
e-mail: clara.santato@polymtl.ca

and electronic transport, redox activity, metal binding affinity, biocompatibility, and biodegradability (Di Mauro et al. 2017; Liu et al. 2004). These properties are relevant for optical, electrochemical, electronic, and metal recovery applications. This chapter will review the chemical, structural and physicochemical properties of eumelanin and its interactions with metal ions, focusing on recent developments and building on the state-of-the-art in this same field, we proposed in 2017 (Di Mauro et al. 2017).

2 Chemical Structure and Physicochemical Properties of Eumelanin

The term melanin indicates a set of indole/quinone-based natural pigments resulting from biochemical syntheses taking place in different living organisms (animals, plants, fungi, and bacteria) (Galeb et al. 2021; Xie et al. 2019; Cao et al. 2021).

Based on their chemical precursors, these pigments can be organized into five categories: eumelanin, pheomelanin, neuromelanin, pyromelanin, and allomelanin (Fig. 1).

In all cases, except for allomelanin, the pigments are obtained through the oxidation/polymerization of the amino acid tyrosine molecules. Allomelanins are synthesized from phenolic compounds by fungi and plants through a process of biosynthesis (Singla et al. 2021).

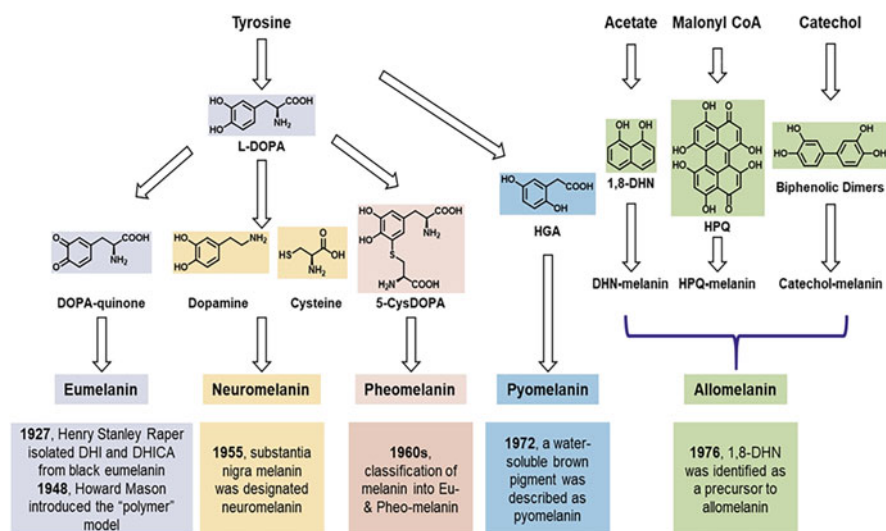


Fig. 1 Biosynthetic pathways of the structures of melanin: eumelanin, neuromelanin, pheomelanin, and the two nitrogen-free analogues, pyromelanin and allomelanin. Compilation of converging data for pathways from a wide range of literature sources with a historical timeline highlighting melanin discoveries. Adapted from ref. (Cao et al. 2021)

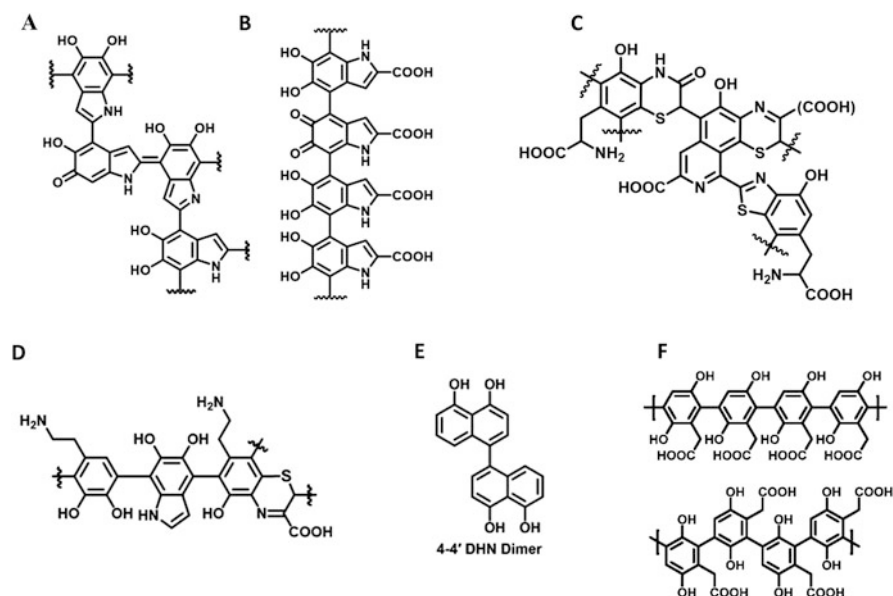


Fig. 2 Potential structures of natural melanins: (a) DHI eumelanin and (b) DHICA eumelanin; (c) Pheomelanin; (d) Neuromelanin; (e) Dimer of allomelanin; and (f) Two possible structures of pyomelanin. Adapted from ref. (Cao et al. 2021)

For any of these melanin categories, as given in Fig. 2, it is necessary to use rigorous extraction methods to isolate the melanin component from all the other components present in the medium where the biosynthesis took place.

The preparation processes and sampling techniques can drastically change the chemical composition of the extracted sample, thus affecting the physicochemical properties of the extracted samples. (Liu and Simon 2003; Madaras et al. 2010). For example, eumelanin extracted from the ink sac of cuttlefish using the “syringe” method brings about an ink including L-DOPA (L-3,4-dihydroxyphenylalanine), dopamine, and taurine. In contrast, the “milking” method bring about an ink including tyrosinase and epinephrine (Madaras et al. 2010; Derby 2014).

2.1 Eumelanin

Within the melanin family of biopigments, eumelanin has been the most explored and studied, because of its application in various fields, such as electrochemical energy storage, bioelectronics and green electronics (João Paulin and Graeff 2021). Eumelanin is a natural biomacromolecule composed of two building blocks: 5,6-dihydroxyindole (DHI) and 5,6-dihydroxyindole 2-carboxylic acid form (DHICA). The molecular ratio between DHI and DHICA building blocks affects

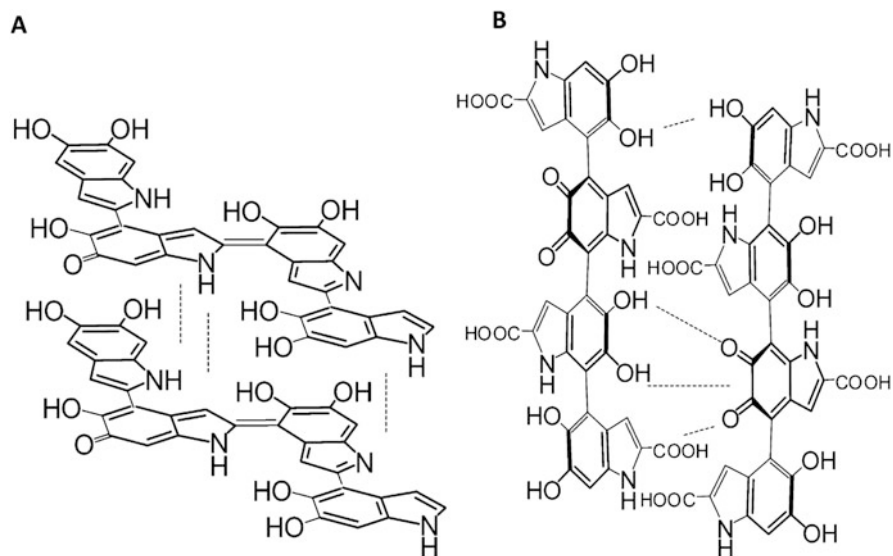


Fig. 3 Supramolecular structures of DHI- and DHICA-melanins. **(a)** DHI melanin represented as planar oligomeric scaffolds, **(b)** DHICA melanin is made up of twisted linear oligomer structures featuring atropisomerism. Adapted from ref. (d'Ischia et al. 2014)

the physicochemical properties of eumelanin (Terranova and Tamburri 2021). The presence of a quinone group in the building blocks, besides the presence of the carboxylic group in one of the two building blocks, is among the distinctive molecular features of eumelanin.

The carboxylic group is essential to differentiate the structure of eumelanin from that of synthetic polydopamine, so explored in the last decade. The absence of the carboxylic group brings about planarity in the molecular structure of polydopamine. As opposed to that, eumelanin features a structure with twists in its carbon backbone, where it is possible to observe atropisomerism by adjacent DHICA moieties (Pezzella et al. 2002; d'Ischia et al. 2014). The existence of these stable conformational isomers is due to the sizeable torsional barrier along the inter-unit bond (Fig. 3). In agreement with that, in the ultraviolet (UV)-visible spectra, no intense absorption bands are observed above 400 nm for DHICA-based melanin structures whereas intense absorption bands are observed for the DHI-based melanin structures in the visible region (Micillo et al. 2016).

2.2 Eumelanin vs Other Melanins

The presence of the nitrogen atom also permits to differentiate among different melanin structures. Allomelanin and pyromelanin are nitrogen-free melanins whereas in eumelanin the nitrogen atom is part of a pyrrole ring and in pheomelanin it is part

of a thiazine ring. Neuromelanin results from the combination of 5-S-cysteinyl-dopamine and dopaminochrome (Fig. 2d).

It is worth noticing that, in general, the presence of the nitrogen atom in aromatic heterocycles causes the non-bonding electron pair of the nitrogen to occupy a sp^2 hybrid orbital. Therefore, the non-bonding electrons pair will be in orbitals with significant “s” character, close to the nucleus (and as such less prone to engage in chemical bondings). Despite reports on the participation of nitrogen atoms in chelation bondings, the effects of sp^2 hybridization should be taken into consideration when studying melanin-metals interactions.

2.3 Chemical and Physical Disorder

Eumelanin features chemical disorder due to its two building blocks, several polymerization sites connecting the building blocks, and three redox states bringing about comproportionation and tautomeric equilibria (Fig. 4). The chemical disorder is associated to physical disorder, in the sense that several supramolecular organizations are possible considering the different chemical species available in the macromolecular eumelanin biopigment.

2.4 Functional Properties of Eumelanin

Beyond applications as UV–Vis absorbers, eumelanin features metal ion binding properties, radical scavenging activity against reactive oxygen species, antioxidant activity, and charge transfer/charge carrier (electronic and ionic) transport properties. In what follows, we will discuss charge transfer and electrochemical properties.

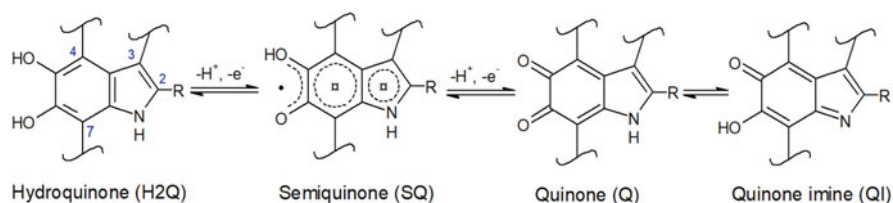


Fig. 4 Molecular structures of DHI and DHICA, with R is $-H$ in DHI and $-COOH$ in DHICA. The redox forms of DHI and DHICA are: hydroquinone (H2Q), semiquinone (SQ), quinone (Q) and quinone imine (QI) (the tautomer of Q). The building blocks can polymerize into eumelanin oligomers and polymers at different sites of the monomers (shown as 2, 3, 4, 7 in the figure). Adapted from ref. (Di Mauro et al. 2017)

3 Electrochemical Properties of Eumelanin: Focus on Metal Ions

When dealing with redox-active materials and devices, electrochemistry helps to shed light on electronic properties and chemical changes in materials upon charge transfer processes (Zhu and Shi 2019). Most of natural redox active materials tend to be non-soluble in aqueous media and form unstable colloidal suspensions. In addition, their immobilization on the surfaces of working electrodes can be challenging.

3.1 *Aspects of Redox Properties in Eumelanin, in Presence of Alkaline and Ammonium Ions*

Eumelanin can feature proton-coupled electron transfer (PCET) (Costentin et al. 2010). Considering its quinone functionality (Fig. 4), it is reasonable to make the hypothesis that, during an electron transfer process in aqueous media, 2H^+ and 2e^- are simultaneously transferred.

For *Sepia* melanin (eumelanin extracted from the ink sac of cuttlefish) (Kim et al. 2014; Xu et al. 2017; Gouda et al. 2020), Kim et al. report values between -0.2 and 0.25 V vs. Ag/AgCl (Kim et al. 2014) whereas Xu et al. (Xu et al. 2017) report values of -0.06 V and 0.15 V vs. Ag/AgCl. These potentials are expected to depend on the pH value of the electrolyte (Gouda et al. 2020), although some authors report on potentials independent on pH (Serpentini et al. 2000). The interaction with alkaline metal ions produces shifts in the redox potentials, likely because the ions interact with the binding sites of eumelanin or intercalate within the supramolecular π - π stacks (Xu et al. 2017; Borghetti et al. 2010; Tian et al. 2019).

The cyclic voltammetries for eumelanin in presence of different alkaline and ammonium ions (Figs. 5a, b) show the presence of various redox signals. Voltammograms obtained with DHICA-melanin are better resolved compared to DHI-melanin, possibly because in DHICA-melanin, electron transfers, and ion exchanges are more localized than in DHI-melanin. Instead, voltammograms of DHI-melanin show higher values of the current owing to the more efficient π - π stacking in DHI-melanin concerning DHICA-melanin (Xu et al. 2017; Lucia et al. 2013).

Tian et al. studied the mechanisms behind electron and ionic transfer in eumelanin pigments immersed in aqueous electrolytes including the monovalent cations Li^+ , Na^+ and K^+ (Tian et al. 2019). Their research succeeded in revealing structure-electron transfer (redox) property relationships, beyond the expected redox signals associated to the quinone/hydroquinone redox couple. In particular, redox processes were associated to specific interactions between metal ions and carboxylates pendant groups or aromatic amines. Further, the effect of the size of the metal ions was investigated.

On the one hand, there is a difference between natural and synthetic eumelanin, in terms of redox properties. For natural eumelanin, redox signals may vary from

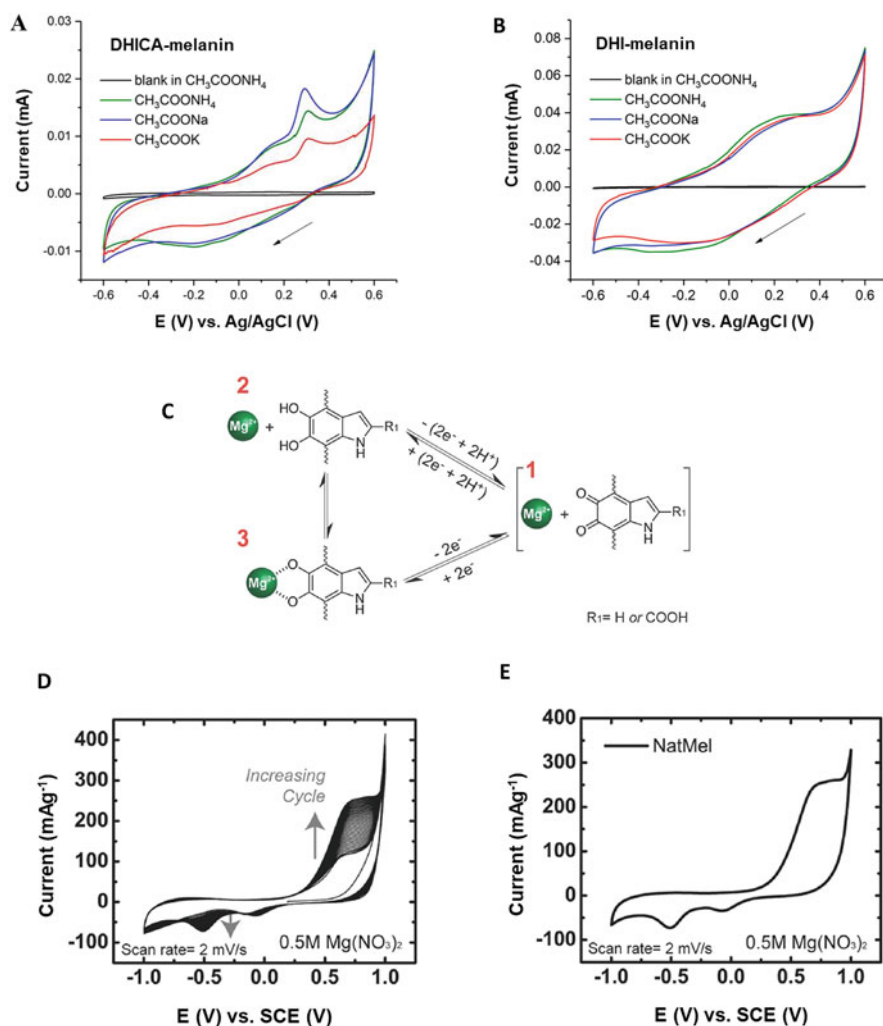


Fig. 5 Electrochemical behavior of eumelanin. DHICA-melanin (a) and DHI-melanin (b) in the presence of monovalent ions, $\nu = 5 \text{ mV/s}$, acid buffers. Adapted from ref. (Xu et al. 2017). (c) Mechanism proposed for the interaction/cooordination of Mg^{2+} ions in the catechol groups in Sepia melanin during voltammetry cycles. States 1 and 3 represent the melanin in the direction of oxidation and reduction states, respectively. State 2 represents an intermediate state of a catechol group before forming a coordination bonding. (d) and (e) represent the cyclic voltammeteries of Sepia melanin in the presence of an electrolyte based on Mg^{2+} ions, $0.5 \text{ M Mg(NO}_3)_2$. Adapted from ref. (Kim et al. 2014)

sample to sample due to the different ratios of DHI:DHICA. On the other hand, for synthetic eumelanin, redox signals are more reproducible. Here, however, heterogeneities can manifest if, for instance, during the polymerization process not

all quinone groups are equally oxidized (Rózanowska et al. 1999; Mostert 2021; Panzella et al. 2013).

3.2 Redox Properties (Multivalent Ions)

Currently, multivalent ions (such as Mg^{2+} , Ca^{2+} , Zn^{2+} , etc.) are investigated to replace Li-ions in energy storage devices with high energy densities. Eumelanin presents different binding sites to interact with these multivalent ions (Hong and Simon 2007). For divalent ions, catechol groups are responsible for chelation under an electrochemical regimen (Xu et al. 2017; Kim et al. 2014). In an interesting electrochemical fingerprinting study aiming at assessing structural changes in Sepia melanin-based electrodes during cycling, Kim et al. reported on porphyrin-like structures formed by tetramers of Sepia melanin building blocks (Kim et al. 2016).

4 The Effect of Metal Ions on the Electronic Transport of Eumelanin

In the 1970s, McGinness et al. observed a reversible electrical switching in hydrated eumelanin pellets (McGinness et al. 1974). This observation led to the description of the electrical behavior of eumelanin within the amorphous semiconductor model (McGinness et al. 1974; Davis and Mott 1970). More recent experimental results challenged such description proposing the possibility of predominant electronic transport in dry eumelanin and mixed ionic electronic transport in wet eumelanin (Mostert et al. 2012; McGinness et al. 1974; Davis and Mott 1970).

4.1 Monovalent Cations

Borghetti et al. studied the morphological and electrical properties of eumelanin after mixing with potassium-including salts (Borghetti et al. 2010). They both drop cast and electrodeposited eumelanin films on ITO and Au substrates from a mixture of potassium bromide and eumelanin-dimethyl sulfoxide (DMSO) solution, to study the effect of the salt on the formation of eumelanin aggregates. They propose that the interaction between potassium cations and nitrogen atoms in the pyrrole ring brings about additional electronic states in the valence band, as indicated by a transfer of spectral weight involving the HOMO level in XPS spectra, thus increasing the number of possible applications of the multifunctional eumelanin biomacromolecule.

4.2 Multivalent Cations

Mostert et al. reported that the modulation of the proton concentration in eumelanin by the chelation of the transition metal ion Cu^{2+} induces a modulation of the conductivity (Mostert et al. 2020). The modulation of the proton conductivity was characterized using Electron Paramagnetic Resonance (EPR). For this study, $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$ was added to a eumelanin solution (eumelanin powder obtained from D–L, dopa, dissolved in water and NH_3) and then processed in thin film form. Cu^{2+} was chelated by hydroquinone/quinone moieties of melanin. The presence of Cu^{2+} increases its conductivity due to the increase in proton concentration in melanin. Afterwards, Organic Electrochemical Transistors (OECTs) were fabricated with the melanin-based copper-including quasi solid-electrolyte as the ionic gating medium and PEDOT:PSS as the transistor channel material. The enhancement of the proton conductivity in melanin is relevant for proton-to-electron transducing devices.

5 On the Interactions Between Eumelanin and Metal Electrodes

Wünsche et al. reported on the interaction between gold electrodes and hydrated eumelanin films deposited on gold electrode-pre-patterned SiO_2 substrates (Wünsche et al. 2013). They showed that interaction between Au and eumelanin under electrical bias in wet environment results in the formation of Au-eumelanin nanoaggregates and dendrites. These dendrites can bridge one electrode to the other after the bias, leading to a dramatic increase of the current. The formation of the *bridging* dendrites following the dissolution of the Au electrodes was attributed to both the metal-binding properties of phenolic hydroxyl groups in eumelanin and Cl^- (present low amounts of in eumelanin). It is worth mentioning that eumelanin also features reducing properties that can bring, chemically (i.e., in absence of electrical bias, gold cations to metallic gold. Di Mauro et al. (2016) later studied in detail the chemical and structural changes occurring at interfaces between metal electrodes (Pd, Cu, Fe, Ni and Au) and hydrated films of eumelanin, under bias (Di Mauro et al. 2016, 2019).

6 On the Possibility to Use Eumelanin in Metal Extraction from E-Waste

The field of electronics has profoundly modified the life quality of everyone, from information and communication technologies to education and industrial production (Patwa et al. 2021). Unfortunately, planned obsolescence and rapid upgrading of consumer electronics have led to the dramatic accumulation of waste electrical and

electronic equipment (WEEE). Globally, about 50 million tons of electronic-waste (e-waste) are produced per year, with detrimental effects on human health and the environment (Dar et al. 2020; Tchounwou et al. 2012).

The composition of e-waste includes organic and inorganic materials such as plastics, flame-retardants, and metals (Du et al. 2023). The global recycling rate for e-waste is about 20% (31% in Europe and North America, 12% in Eastern and South Eastern Asia, 5% in Central and Southern Asia, 4% Sub-Saharan Africa and 1% Latin America) (Boubellouta and Kusch-Brandt 2022). A relevant portion of e-waste is exported, sometimes illegally, to sub-Saharan and South-East Asian countries.

Precious metals, e.g., gold, palladium and platinum, have high economic value by considering their primary application in the electrical and electronics industry (Rafiee et al. 2021; Gunarathne et al. 2022). Recovering precious metals from e-waste represents an important economic opportunity.

There are several physicochemical and biological methods to extract metals from e-waste.

6.1 Hydrometallurgy

In hydrometallurgy, liquid chemistry based on the use of different chemicals (cyanide, thiourea, thiosulfates and acids) is employed to extract metals. After leaching (where solutions are used to solubilize the metal-containing materials by converting them into soluble salts), metals are usually further processed for purification and extraction (Gaydardjiev 1998; Whitworth et al. 2022). Cyanide ions (CN^-) and *aqua regia* are used to recover gold in hydrometallurgy (La Brooy et al. 1994; Syed 2012).

6.2 Biohydrometallurgy

The biohydrometallurgical method is based on the use of different bacteria including chemolithoautotrophic bacteria, heterotrophic bacteria and fungi, such as *Aspergillus Niger* and *Penicillium simplicissimum* (Esmaeili et al. 2022), to transform insoluble metal oxides/sulfides into soluble metal ions for their subsequent recovery (Gu et al. 2018). There are different types of bacteria that have been used for bioleaching, such as mesophilic (temperature range 25–35 °C) and thermophilic (50 °C) (Gu et al. 2018; Kaksonen et al. 2017). A frequently used microorganism in sulfide ores bioleaching is *Acidithiobacillus ferrooxidans* (Watling 2006).

Bioleaching has been used in metal mining from the decades (Ji et al. 2022). Recently, this low cost and environmentally friendly method has been employed to extract heavy metals from ash and sewage sludge for bioremediation purposes (Gu et al. 2018).

6.3 *Pyrometallurgy*

Pyrometallurgy is based on the thermal treatment of materials, such as minerals and ores, to obtain precious metals (Harvey et al. 2022; Zhu et al. 2022). Compared to hydrometallurgy, it involves partial or complete conversion of chemical compounds into their elemental form. For example, pyrite is converted into pyrrhotite and elemental sulphur (Whitworth et al. 2022). During the pyrometallurgy process, different oxides and reducing agents are being used. For instance, to extract platinum-based metals (PBMs), lead oxides are used (Kim et al. 2013; Peng et al. 2017).

6.4 *A Possible Perspective on the Interaction of Melanin with Metals for e-Waste Recovery*

There are number of physicochemical mechanisms that can be exploited for the extraction of metals with melanin (Di Mauro et al. 2017; Meredith and Sarna 2006; Pilas et al. 1988; Hong et al. 2007).

We propose that in the future natural chelating agents could be used to promote metal recovery in urban mining, to recover precious, critical or strategic metals (Electronic Waste: Recycling and Reprocessing for a Sustainable Future, Maria E. Holuszko (Editor), Amit Kumar (Editor), Denise C. R. Espinosa (Editor) ISBN: 978-3-527-34,490-1).

Literature reports that, melanin extracted from squid ink features high adsorption tendency for lead (Xue et al. 2009). Systematic studies are needed to shed light on the effect of the source of melanin and its molecular and supramolecular structures (as well as possible presence of other chemical compounds in the natural or synthetic melanin material) on its binding affinity to metals, for metal recovery purposes. For instance, eumelanin prepared by L-DOPA can remove 95% of initial lead present in the investigated sample, a percentage dramatically higher than that one observed with eumelanin extracted from human hair (Sono et al. 2012). Results reported by Darwish et al. show that synthetic melanin nanoparticles (5,6-diacetoxy indole precursor that is hydrolyzed in situ into dihydroxy indole (DHI)) adsorb different metal ions; here highest adsorption values from 50 ppm solutions were observed for Co^{2+} , Ni^{2+} and Zn^{2+} and lowest for Cu^{2+} , Cd^{2+} and Pb^{2+} (Darwish et al. 2021).

Well beyond eumelanin, we wish to encourage the research community active in the field of metal recovery and water and soil remediation to explore, at large scale, the use of biosourced organic chelating agents considering their abundance, low cost, biodegradability and, possibly, biocompatibility.

References

- Borghetti P, Goldoni A, Castellarin-Cudia C et al (2010) Effects of potassium on the supramolecular structure and electronic properties of eumelanin thin films. *Langmuir* 26:19007–19013. <https://doi.org/10.1021/la102973u>
- Boubellouta B, Kusch-Brandt S (2022) Driving factors of e-waste recycling rate in 30 European countries: new evidence using a panel quantile regression of the EKC hypothesis coupled with the STIRPAT model. *Environ Dev Sustain*:1–28. <https://doi.org/10.1007/s10668-022-02356-w>
- Cao W, Zhou X, McCallum NC et al (2021) Unraveling the structure and function of melanin through synthesis. *J Am Chem Soc* 143:2622–2637. <https://doi.org/10.1021/jacs.0c12322>
- Costentin C, Robert M, Savéant JM (2010) Concerted proton-electron transfers: electrochemical and related approaches. *Acc Chem Res* 43:1019–1029. <https://doi.org/10.1021/ar9002812>
- d'Ischia M, Napolitano A, Ball V et al (2014) Polydopamine and eumelanin: from structure–property relationships to a unified tailoring strategy. *Acc Chem Res* 47:3541–3550. <https://doi.org/10.1021/ar500273y>
- Dar AA, Chen J, Shad A et al (2020) A combined experimental and computational study on the oxidative degradation of bromophenols by Fe(VI) and the formation of self-coupling products. *Environ Pollut* 258:113678. <https://doi.org/10.1016/j.ENVPOL.2019.113678>
- Darwish ER, Kalil H, Alqahtani W et al (2021) Fast and reliable synthesis of melanin nanoparticles with fine-tuned metal adsorption capacities for studying heavy metal ions uptake. *Nanotechnol Sci Appl* 14:101–111. <https://doi.org/10.2147/NSA.S296722>
- Davis EA, Mott NF (1970) Conduction in non-crystalline systems V. Conductivity, optical absorption and photoconductivity in amorphous semiconductors. *Philos Mag* 22:0903–0922. <https://doi.org/10.1080/14786437008221061>
- Derby C (2014) Cephalopod ink: production, chemistry, functions and applications. *Mar Drugs* 12:2700–2730. <https://doi.org/10.3390/md12052700>
- Di Mauro E, Carpentier O, Yáñez Sánchez SI, Ignoumba Ignoumba N, Lalancette-Jean M, Lefebvre J, Zhang S, Graeff CFO, Cicoirab F, Santato C (2016) Resistive switching controlled by the hydration level in thin films of the biopigment eumelanin. *J Mater Chem C* 4:9544–9553. <https://doi.org/10.1039/C6TC02793H>
- Di Mauro E, Xu R, Soliveri G, Santato C (2017) Natural melanin pigments and their interfaces with metal ions and oxides: emerging concepts and technologies. *MRS Commun* 7:141–151. <https://doi.org/10.1557/mrc.2017.33>
- Di Mauro E, Hebrard E, Boulahia Y et al (2019) On the interfaces between organic bio-sourced materials and metals for sustainable electronics: the eumelanin case. *Jpn J Appl Phys* 58:051014. <https://doi.org/10.7567/1347-4065/ab1061>
- Du J, Waite TD, Biesheuvel PM, Tang W (2023) Recent advances and prospects in electrochemical coupling technologies for metal recovery from water. *J Hazard Mater* 442:130023. <https://doi.org/10.1016/J.JHAZMAT.2022.130023>
- Esmaili A, Arshadi M, Yaghmaei P, PEDS (2022) Simultaneous leaching of Cu, Al, and Ni from computer printed circuit boards using *Penicillium simplicissimum*. *Resour Conserv Recycl* 177:105976. <https://doi.org/10.1016/j.resconrec.2021.105976>
- Galeb HA, Wilkinson EL, Stowell AF et al (2021) Melanins as sustainable resources for advanced biotechnological applications. *Glob Challenges* 5:2000102. <https://doi.org/10.1002/gch2.202000102>
- Gaydardjiev SS (1998) Hydrometallurgy of precious metals: effects on the environment. In: *Mineral processing and the environment*. Springer, Netherlands, pp 257–280
- Gouda A, Soavi F, Santato C (2020) Eumelanin electrodes in buffered aqueous media at different pH values. *Electrochim Acta* 347:136250. <https://doi.org/10.1016/j.electacta.2020.136250>
- Gu T, Rastegar SO, Mousavi SM et al (2018) Advances in bioleaching for recovery of metals and bioremediation of fuel ash and sewage sludge. *Bioresour Technol* 261:428–440. <https://doi.org/10.1016/J.BIORTECH.2018.04.033>

- Gunaratne V, Rajapaksha AU, Vithanage M et al (2022) Hydrometallurgical processes for heavy metals recovery from industrial sludges. *Crit Rev Environ Sci Technol* 52:1022–1062. <https://doi.org/10.1080/10643389.2020.1847949>
- Harvey J-P, Courchesne W, Vo MD et al (2022) Greener reactants, renewable energies and environmental impact mitigation strategies in pyrometallurgical processes: a review. *MRS Energy Sustain* 2022:1–36. <https://doi.org/10.1557/S43581-022-00042-Y>
- Hong L, Liu Y, Simon JD (2007) Binding of metal ions to melanin and their effects on the aerobic reactivity. *Photochem Photobiol* 80:477–481. <https://doi.org/10.1111/j.1751-1097.2004.tb00117.x>
- Hong L, Simon JD (2007) Current understanding of the binding sites, capacity, affinity, and biological significance of metals in melanin. *J Phys Chem B* 111:7938–7947. <https://doi.org/10.1021/jp071439h>
- Ji X, Yang M, Wan A et al (2022) Bioleaching of typical electronic waste–printed circuit boards (WPCBs): a short review. *Int J Environ Res Public Health* 19:7508. <https://doi.org/10.3390/ijerph19127508>
- João Paulin SV, CF OG, Hamed MM, Paulin JV (2021) From nature to organic (bio)electronics: a review on melanin-inspired materials. *J Mater Chem C* 9:14514–14531. <https://doi.org/10.1039/D1TC03029A>
- Kaksonen AH, Morris C, Wylie J et al (2017) Continuous flow 70 °C archaeal bioreactor for iron oxidation and jarosite precipitation. *Hydrometallurgy* 168:40–48. <https://doi.org/10.1016/J.HYDROMET.2016.08.015>
- Kim YJ, Khetan A, Wu W et al (2016) Evidence of porphyrin-like structures in natural melanin pigments using electrochemical fingerprinting. *Adv Mater* 28:3173–3180. <https://doi.org/10.1002/adma.201504650>
- Kim BS, Lee JC, Jeong J et al (2013) A novel process for extracting precious metals from spent Mobile phone PCBs and automobile catalysts. *Mater Trans* 54:1045–1048. <https://doi.org/10.2320/MATERTRANS.M2013051>
- Kim E, Liu Y, Leverage WT et al (2014) Context-dependent redox properties of natural phenolic materials. *Biomacromolecules* 15:1653–1662. <https://doi.org/10.1021/bm500026x>
- Kim YJ, Wu W, Chun S-E et al (2014) Catechol-mediated reversible binding of multivalent cations in eumelanin half-cells. *Adv Mater* 26:6572–6579. <https://doi.org/10.1002/adma.201402295>
- La Brooy SR, Ling HG, Walker GS (1994) Review of gold extraction from ores. *Miner Eng* 7: 1213–1241. [https://doi.org/10.1016/0892-6875\(94\)90114-7](https://doi.org/10.1016/0892-6875(94)90114-7)
- Liu Y, Hong L, Kempf VR et al (2004) Ion-exchange and adsorption of Fe(III) by Sepia melanin. *Pigment Cell Res* 17:262–269. <https://doi.org/10.1111/J.1600-0749.2004.00140.X>
- Liu Y, Simon JD (2003) The effect of preparation procedures on the morphology of melanin from the ink sac of Sepia officinalis. *Pigment Cell Res* 16:72–80. <https://doi.org/10.1034/J.1600-0749.2003.00009.X>
- Madaras F, Gerber JP, Peddie F, Kokkinn MJ (2010) The effect of sampling methods on the apparent constituents of ink from the squid *Sepioteuthis australis*. *J Chem Ecol* 36:1171–1179. <https://doi.org/10.1007/s10886-010-9869-0>
- McGinness J, Corry P, Proctor P (1974) Amorphous semiconductor switching in Melanins. *Science* 183:853–855. <https://doi.org/10.1126/SCIENCE.183.4127.853>
- Meredith P, Sarna T (2006) The physical and chemical properties of eumelanin. *Pigment Cell Res* 19:572–594. <https://doi.org/10.1111/J.1600-0749.2006.00345.X>
- Micillo R, Panzella L, Koike K et al (2016) “Fifty shades” of black and red or how carboxyl groups fine tune eumelanin and pheomelanin properties. *Int J Mol Sci* 17:746. <https://doi.org/10.3390/IJMS17050746>
- Mostert AB (2021) Melanin, the what, the why and the how: an introductory review for materials scientists interested in flexible and versatile polymers. *Polymers* 13:1670. <https://doi.org/10.3390/polym13101670>

- Mostert AB, Powell BJ, Pratt FL et al (2012) Role of semiconductivity and ion transport in the electrical conduction of melanin. *Proc Natl Acad Sci* 109:8943–8947. <https://doi.org/10.1073/pnas.1119948109>
- Mostert AB, Rienecker SB, Sheliakina M et al (2020) Engineering proton conductivity in melanin using metal doping. *J Mater Chem B* 8:8050–8060. <https://doi.org/10.1039/D0TB01390K>
- Panzella L, Gentile G, D'Errico G et al (2013) Atypical structural and π -electron features of a Melanin polymer that lead to superior free-radical-scavenging properties. *Angew Chem Int Ed* 52:12684–12687. <https://doi.org/10.1002/anie.201305747>
- Patwa N, Sivarajah U, Seetharaman A et al (2021) Towards a circular economy: an emerging economies context. *J Bus Res* 122:725–735. <https://doi.org/10.1016/J.JBUSRES.2020.05.015>
- Peng Z, Li Z, Lin X et al (2017) Pyrometallurgical recovery of platinum group metals from spent catalysts. *JOM* 69:1553–1562. <https://doi.org/10.1007/s11837-017-2450-3>
- Pezzella A, Vogna D, Prota G (2002) Atropoisomeric melanin intermediates by oxidation of the melanogenic precursor 5,6-dihydroxyindole-2-carboxylic acid under biomimetic conditions. *Tetrahedron* 58:3681–3687. [https://doi.org/10.1016/S0040-4020\(02\)00335-6](https://doi.org/10.1016/S0040-4020(02)00335-6)
- Pilas B, Sarna T, Kalyanaraman B, Swartz HM (1988) The effect of melanin on iron associated decomposition of hydrogen peroxide. *Free Radic Biol Med* 4:285–293. [https://doi.org/10.1016/0891-5849\(88\)90049-4](https://doi.org/10.1016/0891-5849(88)90049-4)
- Rafiee P, Ghassa S, Moosakazemi F et al (2021) Recovery of a critical metal from electronic wastes: germanium extraction with organic acid. *J Clean Prod* 315:128223. <https://doi.org/10.1016/J.JCLEPRO.2021.128223>
- Realí M, Gouda A, Bellemare J et al (2020) Electronic transport in the biopigment sepia melanin. *ACS Appl Bio Mater* 3:5244–5252. <https://doi.org/10.1021/acsabm.0c00373>
- Realí M, Saini P, Santato C (2021) Electronic and protonic transport in bio-sourced materials: a new perspective on semiconductivity. *Mater Adv* 2:15–31. <https://doi.org/10.1039/d0ma00579g>
- Rózanowska M, Sarna T, Land EJ, Truscott TG (1999) Free radical scavenging properties of melanin: interaction of eu- and pheo-melanin models with reducing and oxidising radicals. *Free Radic Biol Med* 26:518–525. [https://doi.org/10.1016/S0891-5849\(98\)00234-2](https://doi.org/10.1016/S0891-5849(98)00234-2)
- Santato C, Alarco PJ (2022) The global challenge of electronics: managing the present and preparing the future. *Adv Mater Technol* 7:2101265. <https://doi.org/10.1002/admt.202101265>
- Serpentini CL, Gauchet C, De Montauzon D et al (2000) First electrochemical investigation of the redox properties of DOPA–melanins by means of a carbon paste electrode. *Electrochim Acta* 45:1663–1668. [https://doi.org/10.1016/S0013-4686\(99\)00388-6](https://doi.org/10.1016/S0013-4686(99)00388-6)
- Singla S, Htut KZ, Zhu R et al (2021) Isolation and characterization of Allomelanin from pathogenic black knot fungus—a sustainable source of melanin. *ACS Omega* 6:35514–35522. <https://doi.org/10.1021/acsomega.1c05030>
- Sono K, Lye D, Moore CA et al (2012) Melanin-based coatings as lead-binding agents. *Bioinorg Chem Appl* 2012:361803. <https://doi.org/10.1155/2012/361803>
- Syed S (2012) Recovery of gold from secondary sources—a review. *Hydrometallurgy* 115–116: 30–51. <https://doi.org/10.1016/J.HYDROMET.2011.12.012>
- Tchounwou PB, Yedjou CG, Patlolla AK, Sutton DJ (2012) Heavy metal toxicity and the environment. *EXS* 101:133–164. https://doi.org/10.1007/978-3-7643-8340-4_6/COVER
- Terranova ML, Tamburri E (2021) Understanding the way eumelanin works: a unique example of properties and skills driven by molecular heterogeneity. *Polymer* 229:123952. <https://doi.org/10.1016/j.polymer.2021.123952>
- Tian Z, Hwang W, Kim YJ (2019) Mechanistic understanding of monovalent cation transport in eumelanin pigments. *J Mater Chem B* 7:6355–6361. <https://doi.org/10.1039/C9TB01211G>
- Watling HR (2006) The bioleaching of sulphide minerals with emphasis on copper sulphides—a review. *Hydrometallurgy* 84:81–108. <https://doi.org/10.1016/J.HYDROMET.2006.05.001>
- Whitworth AJ, Vaughan J, Southam G et al (2022) Review on metal extraction technologies suitable for critical metal recovery from mining and processing wastes. *Miner Eng* 182: 107537. <https://doi.org/10.1016/j.mineng.2022.107537>

- Wünsche J, Cardenas L, Rosei F et al (2013) In situ formation of dendrites in eumelanin thin films between gold electrodes. *Adv Funct Mater* 23:5591–5598. <https://doi.org/10.1002/adfm.201300715>
- Xie W, Pakdel E, Liang Y et al (2019) Natural eumelanin and its derivatives as multifunctional materials for bioinspired applications: a review. *Biomacromolecules* 20:4312–4331. <https://doi.org/10.1021/acs.biomac.9b01413>
- Xu R, Prontera CT, Di Mauro E et al (2017) An electrochemical study of natural and chemically controlled eumelanin. *APL Mater* 5:126108. <https://doi.org/10.1063/1.5000161>
- Xue C, Chen S, Wang J et al (2009) Adsorption of Pb(II) and Cd(II) by squid ommastrephes bartrami melanin. *Bioinorg Chem Appl* 2009:901563. <https://doi.org/10.1155/2009/901563>
- Zhu X, Shi L (2019) Electrochemistry. In: *Nano-inspired biosensors for protein assay with clinical applications*. Elsevier, Amsterdam, pp 209–236
- Zhu X, Yang J, Yang Y et al (2022) Pyrometallurgical process and multipollutant co-conversion for secondary aluminum dross: a review. *J Mater Res Technol* 21:1196–1211. <https://doi.org/10.1016/J.JMRT.2022.09.089>

Fundamentals and Applications of Optically Active Melanin-Based Materials



Ming Xiao and Weiyao Li

Abstract Melanin is a group of ubiquitous biological pigments. It has excellent photonic properties such as broadband light absorption and high refractive index, combined with other physicochemical functions like free radical quenching and metal chelating capabilities. In this chapter, we focus on the optical functions of melanin. We will first discuss chemical and physical structures in five different types of melanin. Next, we divide melanin's photonic properties into two parts. One is about broadband absorption, where we explore the mechanism behind it and how absorption leads to various applications such as UV protection, solar desalination, and photothermal therapy. The other is related to scattering, which includes the scattering from single particle and aggregates of particles. In both scenarios, structural colors can be produced. We believe this chapter will provide a clear understanding of melanin's optical properties and insights into the rational design of melanin-based optically active materials.

1 Introduction

Melanin is a family of dark polymeric pigments widely found in nature, ranging from animals, plants, and fungi to prehistoric organisms. It possesses superior multifunctional properties despite the fact that its precise hierarchical chemical structure remains unclear. These include a high refractive index, broadband absorption across UV to near IR region, radical quenching ability, strong metal chelating ability, and protection against high-energy radiation. In this chapter, we focus on the optical properties of melanin-based materials and, broadly speaking, how melanin interacts with electromagnetic waves. First, we introduce the chemical structures of melanin and make classifications based on the chemical structure of monomer

M. Xiao (✉)

College of Polymer Science and Engineering, Sichuan University, Chengdu, China
e-mail: mingxiao@scu.edu.cn

W. Li

Department of Polymer Science, The University of Akron, Akron, Ohio, USA

precursors. In the next two sections, we discuss absorption- and scattering-related properties. In the absorption section, we summarize the fundamentals of melanin's broadband absorption and how melanin dissipates absorbed energy, which is related to different applications, like UV protection, photothermal therapy, and fluorescent imaging. The scattering section includes the scattering from single particles and assemblies of particles, with detailed summary on summarize how melanin particles assemble into structurally colored materials. In the end, we present our views on the challenges and opportunities in this field.

2 Chemical Structure

In contrast to proteins or nucleic acids, melanin biosynthesis is not a genetic or sequence-controlled process. It starts with various monomeric precursors and ends with heterogeneous, hierarchical polymeric structures (Cao et al. 2021). The unique optical properties of melanin rely on the complexity of its molecular units, chemical structures, and physical packings. In this section, we will discuss five types of melanin and their complex hierarchical structures.

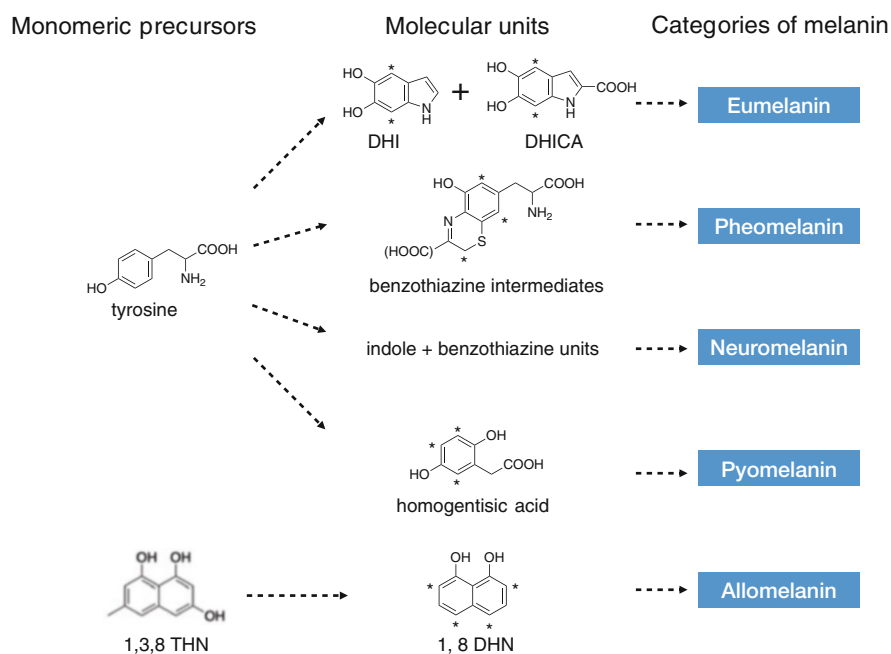


Fig. 1 Classifications of melanin based on the chemical structure of molecular unit. The star symbols indicate possible chemical bonding sites to other molecular units

2.1 *Classifications of Melanin*

There are five categories of melanin based on molecular units in their macromolecular structures: eumelanin, pheomelanin, neuromelanin, pyomelanin, and allomelanin (Fig. 1). They share similarities such as displaying dark colors (brown to black), containing conjugated aromatic structures, and being insoluble in most solvents. However, their chemical structures are quite different from each other, which will be discussed later.

Eumelanin, pheomelanin, and neuromelanin are mostly found in animals. They are produced initially from tyrosine by a series of enzymatic reactions in cells (commonly melanocytes). In their biosynthetic paths, tyrosinase oxidizes tyrosine to dopaquinone (DQ) and DQ polymerizes to eumelanin with two main building blocks 5,6-dihydroxyindole (DHI) or 5,6-dihydroxyindole-2-carboxylic acid (DHICA). The cysteine in the cell promotes the production of pheomelanin by forming cysteinyl-dopa and then benzothiazine intermediates, which prohibits the formation of eumelanin (Wakamatsu et al. 2021). Neuromelanin also originates from tyrosine, which is produced in the substantia nigra and locus coeruleus of brains. Neuromelanin is often mixed with other living tissues and it contains both indole and benzothiazine as molecular units. Pyomelanin and allomelanin are nitrogen-free melanins, which are produced mostly in fungi, bacteria, or plants. Pyromelanin biosynthetic process involves catabolism of tyrosine to homogentisic acid, while allomelanin is produced directly from nitrogen-free precursors such as 1,8-dihydroxynaphthalene (DHN).

In addition to biosynthesis in living tissues, melanin can be made in the laboratory through chemical oxidation or enzymatic oxidation using corresponding monomeric precursors. Synthetic melanin has dark coloration similar to natural melanin. Eumelanin, pheomelanin, and neuromelanin can be synthesized starting from various precursors such as tyrosine, dopamine, L-3,4-dihydroxyphenylalanine (L-DOPA), DHI, and DHICA via enzymatic reaction or oxidations (d'Ischia et al. 2013; Li et al. 2019; Napolitano et al. 2013; Wakamatsu et al. 2003). Both allomelanin and pyomelanin, can be synthesized in vitro from DHN and homogentisic acid, respectively (Zhou et al. 2019; Schmalzer-Ripcke et al. 2009). More details on the synthesis of different types of synthetic melanin can be referred to in a recent review from Gianneschi group (Cao et al. 2021).

Although the chemical structure of main molecular units in melanin has been intensively studied, melanin's polymeric structure has not been fully revealed. Melanin's monomeric precursors have more than two reactive sites, making its polymerization complicated. In the synthesis of eumelanin, the rearrangement of dopachrome to form DHI or DHICA not only diversifies the monomeric structures but also provides various arrangements of units in the polymeric chains (Swift 2009). In the pheomelanin, the cysteine not only attaches to a different site on DOPA, but also splits a fraction of the monomers to form benzothiazines, rather than indole-like eumelanin, which adds another level of complexity. Neuromelanin is produced from two monomeric precursors and has a more chemically disordered structure.

Pyomelanin can be made from the polymerization of homogentisic acid, which is a degradation product from tyrosine (Schmaler-Ripcke et al. 2009; Frases et al. 2007). However, the chemical structure of pyomelanin is less studied compared to other types of melanin. Both natural and synthetic allomelanin can be made from a universal monomeric precursor, DHN. Unlike dopachrome, DHN has fewer chances to rearrange, but allomelanin structure is also disordered due to various linkages in DHN dimers and mutations of DHN by reduction, oxidation, and dehydration (Zhou et al. 2019; Jackson et al. 2009).

2.2 Complex Hierarchical Structure of Melanin

Melanin often comes in the form of particles ranging from tens of nanometers to a few microns. Although its insolubility in most solvents makes it a challenge to quantify its chemical structure, it is clear that melanin has a complex hierarchical structure ranging from molecular to micrometer scales. The structure of eumelanin is the most widely studied. As the monomer precursor, the tyrosine converts to molecular units, DHI and DHICA. Several molecular units form planar oligomers that are called protomolecules and some models suggest that protomolecules are porphyrin-like tetramer structures (Chen et al. 2013; Kaxiras et al. 2006). These planar protomolecules stack with a spacing of 3–4 Å and stacked protomolecules pack with ordered or disordered structures to form primary nanoparticles 10–60 nm. Higher geometric packing order of these protomolecules will lead to broadening and red-shifts of the absorption band (Ju et al. 2018). The primary particles assemble into submicron-sized particles, ranging from solid spheres, solid rods, or hollow rods in natural melanin (Fig. 2) (Xiao et al. 2018).

As a model synthetic eumelanin, polydopamine has been utilized to aid in revealing the mysterious structure of natural eumelanin. Polydopamine, made via oxidation polymerization of dopamine, contains various molecular units, including uncyclized dopamine and DHI, which provide various chromophores to absorb light (Della Vecchia et al. 2013; Bisaglia et al. 2007). Although there is still some debate, it is mostly agreed that polydopamine particles are composed of linear polymer

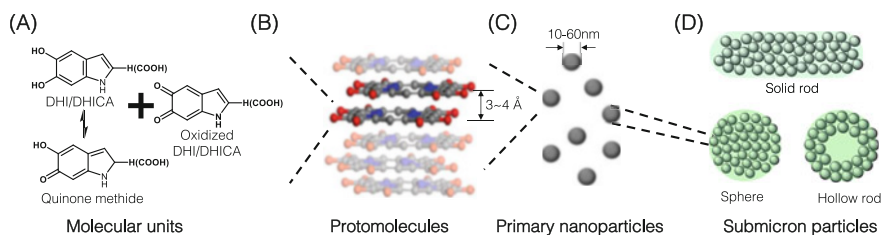


Fig 2 A hierarchical structure model for eumelanin: (a) melanin molecular units, (b) stacked protomolecules, (c) primary particles, and (d) melanin particles with different morphologies. Adapted from Xiao et al. (2018)

chains that are bound together via physical interactions such as hydrogen bonding, cation- π interaction, and π - π stacking (Büngeler et al. 2017; Li et al. 2015; Hong et al. 2018). The DHI units propagate through the six-membered ring to increase the molecular sizes in polydopamine (Li et al. 2019). Using matrix-assisted laser desorption/ionization mass spectroscopy, Reale et al. found that oligomers made from DHI can reach up to 30 units (Reale et al. 2012).

3 Absorption-Related Properties and Applications

Melanin can absorb light broadly from UV up to near-infrared (200–1700 nm) with decayed absorptivity at longer wavelengths (Li et al. 2020). As organic polymers, their broadband absorption is unique, making them ideal for black pigments and UV-protecting agents. Most of the light absorbed by melanin is dissipated as heat, and this photothermal effect can be used for saltwater desalination or photothermal therapy. In addition, melanin can be modified to fluoresce, expanding its applications. In this section, we will discuss the broadband absorption of melanin, the underlying mechanism of absorption, and related applications.

3.1 Optical Absorption

Melanin has a broadband absorption, unlike other pigments that often have significant absorption peaks at certain wavelengths. Its absorption spectrum varies with its chemical structure. Quantifying melanin absorption is challenging for several reasons. First, melanin is insoluble in most solvents without chemical degradation, so it is difficult to conduct conventional absorption measurements on solvent-casting melanin films. Second, melanin from biological systems is often mixed with other cellular components, making the purification process tremendously difficult. Third, melanin, often in the form of micron-scale or even larger particles, scatters light, which overestimates light absorption. Therefore, there is no perfect way to accurately measure the absorption of natural melanin. Stavenga et al. measured the refractive index of intact barbule cells that contained multilayered natural melanin particles and used an optical model to obtain a best-fitting value (Stavenga et al. 2015). Based on this method, they reported that the imaginary index varies from 0.127 to 0.029 at wavelengths of 400–800 nm (Fig. 3a).

Synthetic melanin can be chemically prepared in a more controlled manner, removing some barriers to absorption measurements. Xiao et al. measured melanin nanoparticles made from dopamine and the imaginary index decreased from 0.33 to 0.09 at 400–800 nm (Fig. 3a). To greatly reduce the scattering effect of the particles, they used dilute solutions (10^{-4} – 10^{-3} % v/v) and small particle sizes (120 nm) (Xiao et al. 2015). In addition to melanin nanoparticles, there are a few reports on quantifying the absorption of synthetic melanin films. Bothma et al. fabricated

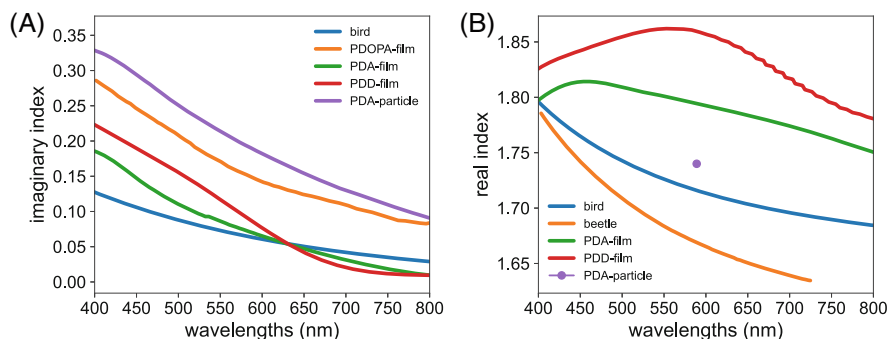


Fig. 3 Refractive indices of various types of melanin. (a) The imaginary part of refractive indices of melanin in bird feathers (Stavenga et al. 2015), PDOPA melanin films (Bothma et al. 2008), PDA and PDD melanin films (Li et al. 2020), and PDA melanin nanoparticles (Xiao et al. 2015). (b) Real part of refractive indices of melanin in beetle scales (Yoshioka and Kinoshita 2011), bird feathers (Stavenga et al. 2015), PDA and PDD films (Li et al. 2020), and PDA melanin nanoparticles (Xiao et al. 2015)

device-quality melanin films with DOPA and used an integrating sphere to measure absorption. We can calculate the imaginary indices of the PDOPA melanin film as 0.286–0.083 based on the absorption coefficient (Fig. 3a) (Bothma et al. 2008; Xiao et al. 2020). Li et al. made two types of smooth melanin films through oxidation polymerization at the water-air interface. One is polydopamine (PDA) and the other is poly(dopamine-L-DOPA) (PDD). They used ellipsometry to measure imaginary indices of PDA and PDD melanin films to be 0.185–0.0096 and 0.222–0.0094 (Fig. 3a) (Li et al. 2020). The reported synthetic melanin shows higher absorption than natural melanin, probably because natural melanin is mixed with non-absorbing components like proteins, lipids, or polysaccharides.

Understanding the mechanism behind melanin's broadband absorption will guide the rational design of novel black pigments. Different levels of heterogeneities contribute to melanin's broadband absorption. The first level is the chemical structure variation as mentioned in Sect. 2. Take eumelanin, for example, it is made of mixtures of DHI and DHICA units. These molecular units make protomolecules with different degrees of polymerization. DHI and DHICA have different connecting sites, leading to different chemical structures in protomolecules. Thus, the eumelanin contains different protomolecules that have absorption peaks at different wavelengths and the supposition of these peaks leads to broadband absorption (Tran et al. 2006). The second level of heterogeneity is the variation in redox states. The indole groups in melanin have a fully reduced state (hydro-quinone), half-reduced state (semi-quinone), and oxidized state (quinone). Density functional theory calculations show that the absorption peak of the reduced protomolecules is red-shifted as compared to the oxidized form and the half-reduced form exhibits intermediate behaviors with a broader absorption (Stark et al. 2005). On the third level, the stacking of planar melanin protomolecules plays a significant role in its absorption behavior. Eumelanin protomolecules pack with a spacing of 3–4 Å. Chen et al.

combined experiments and simulations to demonstrate excitonic coupling from geometric packing is a key reason for broadband optical absorption (Chen et al. 2014). Later, Ju et al. demonstrated that higher geometric packing ordering efficiently broadens and red-shifts the absorption band (Ju et al. 2018). Taken together, the unique blackness of melanin is a synergistic effect of heterogeneity in chemical structure, redox states, and geometric packing.

3.2 *Black Additives*

The basic function of melanin is to provide dark colorations in animals and fungi and the colors include black, brown, or grey colors (Evayanti and Artaria 2019; Itou et al. 2019; Surmacki et al. 2021; Mattoon et al. 2021). Dark pigmentations induced with melanin have significant biological functions such as warning color, camouflage, and courtship. Some animals like insects generate black patterns with melanin for aposematic signals, (Liu et al. 2014) while some like cephalopods generate dynamic patterns for camouflage by controlling the melanin density and distribution rapidly (Mäthger et al. 2009). Melanin patterns are also critical in sexual selection for animals like butterflies (Wiernasz 1995). In addition to exterior dark patterns, cuttlefish ejects inks for anti-predator defense (Derby 2014). The inks are a primary source of natural eumelanin used in research.

Melanin can be used as biocompatible hair dyes due to its excellent binding ability. Through the deposition of polydopamine or co-deposition of polydopamine and cysteine, one can obtain melanin-dyed dark hair with different hues (Battistella et al. 2020; Dong et al. 2019). The colors of the dyes can be tuned by doping different types of metals or melanin precursors (Fig. 4a). The melanin hair dye can be even made permanent using a pre-grafting method (Zheng et al. 2022).

Melanin can enhance color saturation by absorbing incoherent backscattering light. Advantages of melanin over other conventional broadband absorbers include biocompatibility, defined and controllable particle sizes, and tunable absorption. Non-iridescent structural colors in bird feathers are caused by coherent light scattering in the spongy layer, and the underlying amorphous melanin layer absorbs incoherent light scattering and enhances color saturation (Saranathan et al. 2012; Shawkey and Hill 2006). Synthetic melanin particles have been extensively doped into photonic colloidal packings to enhance color saturation, and the required doping ratio is as low as 0.5% w/w (Cai et al. 2014; Lee et al. 2019).

3.3 *Protection from Electromagnetic Radiation*

Melanin has a gradually descending absorption band from UV (200 nm) (Wang et al. 2017) to near-infrared (NIR, 900 nm) (Li et al. 2020) with two broad absorption humps in the mid-infrared range (MIR, 2.5–25 μm). Although some melanin

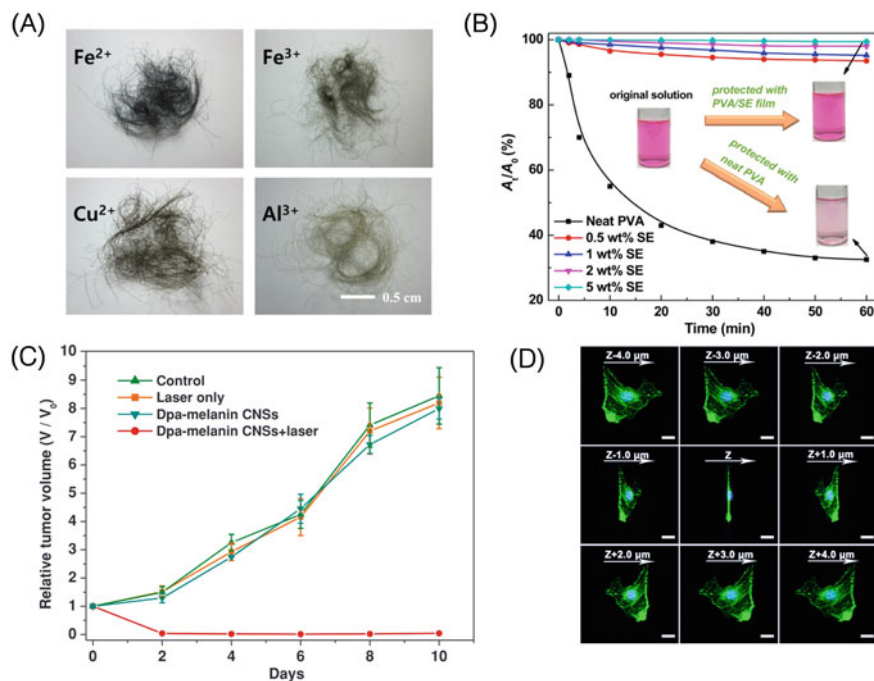


Fig. 4 Absorption-related applications of melanin in various fields. (a) Hairs are dyed with polydopamine melanin catalyzed by different metal ions. Reproduced with permission (Im et al. 2017). Copyright 2017, the American Chemical Society. (b) The absorption curves of rhodamine solutions change with the time of UV irradiation. The solutions are covered by PVA film that contains different concentrations of sepia melanin. Reproduced with permission (Wang et al. 2016). Copyright 2016, the American Chemical Society. (c) 4 T1 tumor growth curves of the mice after different treatments show the efficacy of photothermal therapy. Reproduced with permission (Liu et al. 2013). Copyright 2013, WILEY-VCH. (d) Confocal microscope images of A549 Cells stained with in situ synthesized PDA nanoparticles. Reproduced with permission (Ding et al. 2017). Copyright 2017, the American Chemical Society. Scale bars, 10 μm

can provide protection from high energy radiation like X-ray and γ -ray (Cao et al. 2020; Rageh et al. 2015), there is still a lack of more reliable quantitative evidence of absorption in such a high energy range.

UV light that reaches the earth's surface is mostly UVA and UVB (290–400 nm), which can cause DNA damage and even skin cancer in some extreme cases. Humans with darker skin pigmentation have less oxidative stress and a lower chance of sun-induced skin cancers (Shih et al. 2020; Brenner and Hearing 2008). Birds with melanin-enriched skins tend to be more common in regions with abundant sunshine, suggesting that UV protection is related to dark bird skins (Nicolăi et al. 2020). Melanin in skin, hair, and eye can absorb UV light and quench free radicals generated by UV radiation (Shih et al. 2020; Herrling et al. 2008; Hu et al. 2008). Melanin can release its absorbed energy from UV radiation to heat at a time scale of 160 fs, reducing the chance of excited state splitting to free radicals that will cause

damage to the living tissues (Corani et al. 2014; Qu et al. 2000). Corani et al. and Panzella et al. reported that DHICA melanin dissipated UV and scavenged free radicals faster than DHI melanin, suggesting the DHICA component played a major role in eumelanin's UV protection (Corani et al. 2014; Panzella et al. 2013). Melanin is doped into polymer films to enhance the resistance to UV exposure. A polyvinyl alcohol film doped with sepia melanin can efficiently protect rhodamine dyes from photodegradation (Fig. 4b) (Wang et al. 2016). In addition, doping sepia melanin largely decreases the UV damage to polymer mechanical properties.

Along with the photoprotection of surrounding tissues, the melanin structure may also undergo photodegradation when exposed to visible and UV light. Though melanin releases hydroxyl radicals to quench other free radicals upon visible and UV irradiation (Qu et al. 2000), a study showed that visible light can disrupt the structure of melanin and reduce the antioxidative capacity (Zareba et al. 2006). Li et al. studied the UV degradation behaviors of dopamine melanin, L-DOPA melanin, and sepia melanin. They demonstrated that strong UVA irradiation ($2.43 \pm 0.02 \text{ W/cm}^2$) degraded a fraction of the six-membered benzyl ring to furo[3,4-b]pyrrole and CO_2 while the pyrrole ring of the indole unit was still intact for all three types of melanin (Li et al. 2019).

3.4 Photothermal Effect

The absorption of light by melanin mainly converts into heat, and this photothermal effect leads to many applications. Liu et al. made a photothermal therapeutic (PPT) agent based on melanin nanoparticles for in vivo cancer therapy. With a photothermal conversion efficiency of 40%, the PPT agent can damage tumor cells under 808 nm lasering without affecting healthy tissues (Fig. 4c) (Liu et al. 2013). Later, Yang et al. developed a new type of synthetic melanin by copolymerizing arginine and dopamine, which significantly increased the photothermal conversion efficiency at 808 nm light (Yang et al. 2019).

In addition, the photothermal effect of melanin can be used for solar desalination. The solar energy absorbed by melanin can be harvested to evaporate brine to produce pure water. Zou et al. constructed donor-accepter pairs in synthetic melanin molecules to boost the absorption and used optimized melanin nanoparticles for solar desalination (Zou et al. 2020). When applied to thermoelectric devices, melanin can convert solar energy into heat, generating voltages up to 229 mV through the thermoelectric effect (Bai et al. 2022).

3.5 Fluorescence

Melanin is usually not fluorescent because it can absorb self-emitted light. Synthetic melanin made from dopamine can efficiently quench various fluorescent dyes that

are attached to the surface of melanin nanoparticles (Qiang et al. 2014; Ma et al. 2016). The fluorescence quenching mechanism is assumed to involve Forster resonance energy transfer and/or photoinduced electron transfer. To make melanin fluorescent, one needs to eliminate the aggregation-induced quenching effect by disrupting the stacking of planar melanin protomolecules. Researchers have used chemical oxidation (H_2O_2 , NaIO_4 , KMnO_4) to disrupt the stacking or degrade melanin particles in alkaline solutions to decrease particle sizes (Lin et al. 2015; Yin et al. 2018; Zhang et al. 2012; Xue et al. 2018).

Fluorescent melanin can be used as a novel biocompatible and surface-active dye for sensors and biomedicine. Melanin has strong chelating capabilities with metal ions, and its fluorescence disappears after binding with metal ions. Taking advantage of this phenomenon, researchers have designed fluorescent probes to detect Fe^{3+} or Pb^{2+} (Yin et al. 2018; Zhang et al. 2020). Another important application is to use melanin nanoparticles for cell imaging (Yang et al. 2016; Ding et al. 2017; Zhang et al. 2019). Ding et al. demonstrated that polydopamine nanoparticle (5–10 nm) was synthesized in situ within the nucleus of living cells, and this biomimetic nuclear dye showed high quantum yield (~35.8%), high photostability, low cytotoxicity, and long-term fluorescence tracking property (Fig. 4d) (Ding et al. 2017).

4 Scattering-Related Properties and Applications

Natural and synthetic melanins are often particulate shapes. When the size of melanin particles is comparable to the wavelength of light, they can scatter light and produce various optical effects. By controlling the size and packing of melanin particles, one can manipulate their scattering for different applications, for example, producing structural colors, monitoring the state of melanin-containing cells, or making a nanoprobe for Raman imaging.

The scattering property strongly depends on a material's refractive index. The refractive index of melanin typically reported to be as high as 2.0, is much higher than most common polymers (1.4–1.6). Recent efforts have been made to measure the refractive index of melanin, however, the reported index varies depending on the morphology and chemistry of melanin and measurement methods (Fig. 3b). Yoshinoka and Kinoshita determined the real refractive index of melanin in the Jewel beetle's elytra to be 1.65–1.78 from a typical multilayered model using experimental data (Yoshioka and Kinoshita 2011). Later, Stavenga et al. reported 1.7–1.8 for melanin in damselfly wings and bird feathers by fitting several parameters to match theoretical calculation with experimental data from interference microscopy (Stavenga et al. 2012, 2015). Xiao et al. measured the refractive index of synthetic melanin (PDA) nanoparticles to be 1.74 at 589 nm (Xiao et al. 2015). Li et al. used ellipsometry to measure indices of films for two different synthetic melanin: PDA melanin from only dopamine and PDD melanin from a mixture of dopamine and L-DOPA. PDA film has a maximum index of 1.81 at 485 nm and PDD film has a maximum index of 1.86 at 550 nm (Li et al. 2020). Despite some

discrepancies among different measurements (Fig. 3b), the real part of the refractive index ranges from 1.65 to 1.85 across the visible wavelengths, which is higher than common polymers.

4.1 *Single Particle Scattering*

Melanin particles cannot dissolve in solvents completely without a degradation reaction catalyzed by a strong base like NaOH. When measuring the absorption of melanin, the scattering of melanin particles cannot be completely avoided. Riesz et al. quantified that the contribution of scattering in dilute eumelanin solutions (0.0025% w/w) is less than 6% to the total optical attenuation in the UV regions (210–325 nm), and contribution at wavelengths of 325–800 nm is negligible (Riesz et al. 2006). They obtained a perfect match between calculations and experiments when fitting the scattering of eumelanin to Raileigh scattering with assuming particle sizes to be 38 nm. This suggested that small particle size and a very dilute solution is the key to minimizing the scattering effect when measuring the real absorption. When particles become larger or concentrations are not dilute enough, the scattering contributes more to the total extinction.

One can exploit the scattering of individual melanin particles for new applications. For example, Song et al. simulated wavelength-dependent scattering of melanosomes in retinal pigmented epithelial cells and found that optical properties of melanin particles changed when they were bleached. This method can be used to detect the changes in retinal pigmented epithelial cells (Song et al. 2017). When melanin particles are monodisperse and fall in sizes comparable to wavelengths of visible light, they can generate structural colors by Mie scattering from individual particles (Cho et al. 2017). The high absorption of melanin attenuates multiple scattering so that resonate Mie scattering of monodisperse melanin particles dominates. The Mie scattering makes structural colors and different colors are obtained depending on the size of melanin particles (Fig. 5a).

4.2 *Scattering from Assemblies of Particles*

The assemblies of melanin particles can generate more interesting optical phenomena. In bird feathers, natural melanin particles organize into various ordered packings, like multilayered structures, square packing, or hexagonal packing. These ordered structures made from melanin particles can selectively reflect light at certain wavelengths, producing structural colors. These types of colors depend only on the nanostructures, but not the chemical structure, in contrast to colors of pigments or dyes. We will summarize different types of assembled photonic structures that are made of melanin particles.

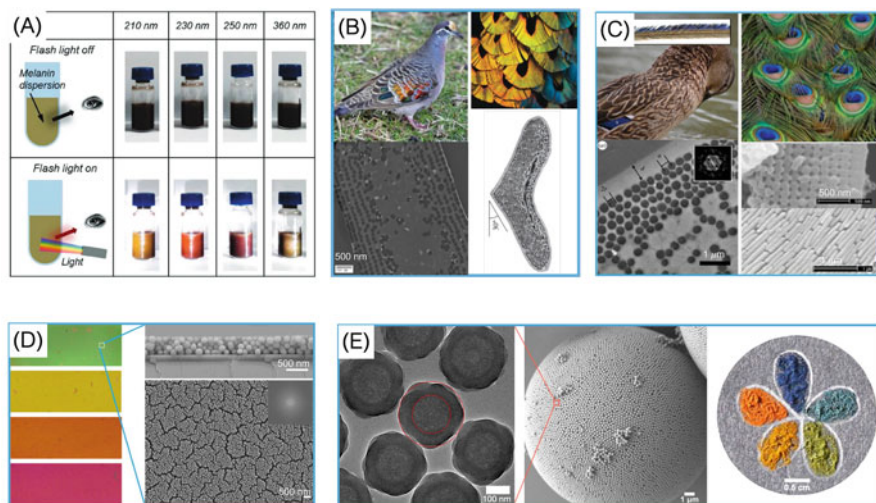


Fig. 5 Structural colors due to scattering from individual and assembled melanin particles. (a) Dilute melanin nanoparticle solutions (0.2% w/w) show different colors depending on the particle sizes, which is due to Mie scattering. Reproduced with permission (Cho et al. 2017). Copyright 2017, WILEY-VCH. (b) Photos and transmission electron microscopy images of structurally colored bird feathers that contain multilayered melanin particles. From left to right, common bronzewing (Reproduced with permission (Xiao et al. 2014). Copyright 2014, the Optical Society) and bird of paradise (Reproduced with permission (Stavenga et al. 2011). Copyright 2011, the Royal Society). (c) Photos and transmission electron microscopy images of structurally colored bird feathers where melanin particles form 2D ordered structures. From left to right, 2D hexagonal packing in mallard feathers (Reproduced with permission (Eliason and Shawkey 2012). Copyright 2012, the Royal Society) and 2D square packing in peacock feathers (Reproduced with permission (Zi et al. 2003). Copyright 2003, the National Academy of Sciences, USA). (d) Structural colors from films made of synthetic melanin particles. Reproduced with permission (Xiao et al. 2015). Copyright 2015, the American Chemical Society. (e) Core-shell melanin particles (melanin as cores) assemble into 3D photonic balls to produce bright and noniridescent structural colors (Xiao et al. 2017)

1. Layered Structures

Melanin particles assemble into a single layer or multiple layers in some bird feathers. When the layer thickness and spacing are hundreds of nanometers, they can reflect light with interference, producing structural colors. The simplest case is the iridescent colors in feathers of blue-black grassquits (*Volatinia jacarina*), where a 127-nm-thick keratin layer and a 422-nm-thick-melanosome layer form a two-layered structure (Maia et al. 2009). Another example is the tree swallow mantle feathers containing a keratin layer (148 nm) and a melanosome layer (173 nm). The keratin layer can absorb water and its thickness increases under high humid conditions, leading to color changes in these feathers (Eliason and Shawkey 2010).

In some bird feathers, there are multilayers of melanin particles dispersed in the keratin matrix with ~100 nm spacing. For example, common bronzewing (*Phaps*

chalcones) feathers contain 6–7 layers of melanin particles with equal spacings in the keratin matrix (Fig. 5b) (Xiao et al. 2014). The slight variations in both thickness and spacing of the melanin layer lead to a full-color spectrum from blue to red (462–647 nm) across a single feather. The bird of paradise (*Parotia lawesii*) has uniquely boomerang-shaped barbules in which reflectors are composed of multilayer melanin particles crossing at a 30 ° angle (Fig. 5b) (Stavenga et al. 2011). This boomerang-shaped geometry increases the angle dependence of the colors, which is biologically beneficial to mating.

Bird feathers have inspired researchers to assemble synthetic melanin particles into structurally colored films. Xiao et al. synthesized monodisperse melanin nanoparticles from dopamine and assembled them into hundreds of nanometers of films to produce structural colors (Xiao et al. 2015). Their colors vary with the film thickness (Fig. 5d). The high color saturation is due to the broadband absorption of melanin. In addition, they found the melanin nanoparticle films could reversibly absorb and desorb water, and melanin films change colors dramatically upon humidity variations (Xiao et al. 2016).

2. 2D Packing of Particles

Natural melanin particles in bird feathers are often rod-like shaped with hundreds of nanometers in diameter and several microns in length. They can be monodisperse with controlled aspect ratios (Xiao et al. 2018), however, it remains challenging to synthesize such rod-like melanin particles with controlled size and aspect ratios in the laboratory. In bird feathers, the rod-like melanin particles prefer to align parallel to the inner surface of barbules due to depletion attraction (Maia et al. 2011). Being monodisperse and rod-like shaped, natural melanin particles readily self-organize into 2D crystalline structures, square or hexagonal lattices, producing bright and iridescent structural colors (Fig. 5c). For example, iridescent peacock barbules contain 2D square packed melanin rod-like particles and different colors of these feathers originate from the variation in lattice spacing (Zi et al. 2003). In mallard feathers, melanin particles form a non-close packed 2D hexagonal lattice (Fig. 5c), resulting in a broader and larger reflectance peak, and thus brighter colors (Eliason and Shawkey 2012).

3. 3D Packing of Particles

Spherical particles can pack in crystalline or short-range correlated structures that can produce structural colors (Takeoka 2012). Natural melanin particles are spherical, rod-like, or irregular shapes, however, monodisperse spherical melanin particles are rarely found in nature. Nowadays, there are quite a few approaches to synthesizing monodisperse melanin particles from different monomers (Xiao et al. 2015; Cho and Kim 2015). This fundamentally supports recent research where synthetic melanin particles are assembled in various ways to produce structural colors.

Melanin has high broadband absorption with a reported absorption coefficient of about 1/μm (Bothma et al. 2008). Based on the beer-lambert's law, a melanin film of 5 μm absorbs more than 99% of light. This suggests that if one prepares 3D packing of pure melanin particles, black colors will be obtained due to too much absorption.

This issue has been resolved by using core-shell melanin particles, co-assembling melanin and other non-absorbing particles, or copolymerization melanin with other polymers.

There are two types of core-shell melanin particles. The first type is with melanin shells. Kishikawa and co-authors coated synthetic melanin (polydopamine) onto polystyrene nanoparticles with melanin shell thickness from 2.5 to 22 nm. They drop cast solutions of core-shell particles to 3D ordered assemblies with structural colors (Kawamura et al. 2016). When the melanin shell thickness increased, the surface of core-shell particles became rougher, prohibiting the formation of crystalline structures. Later, they assembled those core-shell particles to different morphologies, micron-sized photonic balls via membrane emulsification method and photonic fibers via a microfluidic approach (Kohri et al. 2018). Kohri et al. made ellipsoidal melanin particles by stretching uncross-linked polystyrene core and melanin shell particles. When depositing structurally colored films using these particles, they found higher aspect ratios caused a blue shift of reflected spectra (Kohri et al. 2019).

The second type is with melanin cores. Xiao et al. used optical simulations to demonstrate that higher reflectance and brighter colors could be achieved from 3D photonic assemblies made of core-shell nanoparticles with high refractive index core and low index shell. Based on this theory, they used a sol-gel method to coat a silica layer (index = 1.45) onto the surface of synthetic melanin nanoparticles (index = 1.74) to make core-shell nanoparticles with high index core and low index shell. They used a one-pot emulsion method to assemble these core-shell particles into photonic balls that showed bright colors (Fig. 5e). The colors were tuned either by varying core size and shell thickness or by mixing two sizes of core-shell nanoparticles.

Co-assembling melanin with other non-absorbing particles can avoid too much absorption. Random mixing is not always obtained when assembling two types of particles. Xiao et al. demonstrated that melanin particles completely segregate at the outmost layer of photonic balls during co-assembly of melanin and silica particles in an emulsion approach (Xiao et al. 2019). With interfacial tension measurements and molecular dynamic simulations, they revealed that the surface enrichment was caused by the larger interfacial contact angle of melanin than that of silica particles. Inspired by this, Patil et al. used molecular dynamic simulations and numerical optical calculations to systematically explore how the degree of surface enrichment influences the colors of photonic balls (Patil et al. 2021). By decreasing the surface enrichment of melanin particles, the reflectance peak not only broadens but also shifts to shorter wavelengths.

Liu et al. synthesized melanin-doped polymeric nanoparticles by adding dopamine chloride to mixtures of monomers (methyl methacrylate, divinylbenzene, and 2-hydroxyethyl methacrylate) during emulsion polymerization. To create a non close packing, they dispersed these melanin-doped nanoparticles in 2-hydroxyethyl methacrylate (HEMA) solvent and crosslinked HEMA to produce a photonic hydrogel film. By controlling the melanin concentration in these nanoparticles, they obtained sufficient absorption to produce high color saturation without disrupting the packing order (Liu et al. 2020).

4.3 *Inelastic Scattering*

When the light interacts with melanin, most light is scattered without changing frequency. If the frequency of the scattered light is different from that of the incident light, inelastic scattering (also called Raman scattering) happens. The frequency of Raman scattered light is often smaller than the incident light. The energy difference between incident light and scattered light is determined by the molecular vibration energy, which represents the characteristic information of molecular structures. Raman spectroscopy can detect functional groups, just like IR spectroscopy. Melanin is Raman active with two Raman peaks at around 1380 cm^{-1} and 1580 cm^{-1} , similar to G and D bands in graphene and graphite (Huang et al. 2004; Capozzi et al. 2005). The first peak originates from the linear stretching of C-C bonds within the aromatic rings, and the second peak originates from the in-plane stretching of the rings. These peaks are distinguishable from other biological materials, like proteins, polysaccharides, and carotenoids, which provides an invasive method to identify the existence of eumelanin in feathers, hairs or even fossils (Galván et al. 2013; Li et al. 2018; Peteya et al. 2017). Noble metal substrates (like gold, and silver) can largely enhance Raman signal intensity of melanin due to plasmonic resonances. Ju et al. recently coated melanin onto gold nanoparticles and used the core-shell particles as nanoprobe for Raman imaging (Ju et al. 2015).

5 Outlook

Melanin is a group of dark pigments and it interacts with electromagnetic waves in a unique way. Its special optical properties include broadband absorption across UV to near IR, the capability to rapidly dissipate most absorbed energy to heat, and a high refractive index. These properties make melanin widely used in fields like biocompatible hair dyes, UV protection, photothermal therapy, and structural coloration. Here we conclude by highlighting the challenges and opportunities in the study of melanin's photonic properties and optic-related applications. First, there is still a lack of understanding in the quantitative relations between melanin's hierarchical chemical structure and its broad absorption spectra. This includes the challenges of precisely quantifying melanin's chemical structure and revealing the complex supramolecular interactions in melanin. This quantitative relation will provide a roadmap to developing novel melanin-like materials with tuned absorption. Second, it is still unclear how melanin particles organize into ordered or disordered photonic structures in bird feathers and other living creatures. Addressing this challenge may change the current approaches to fabricating photonic materials. Third, we need to integrate melanin's excellent photonic properties with its biocompatibility, radical quenching, and metal binding capabilities so that we can create multifunctional materials for broader applications. To this end, we believe further development of

this field requires joint efforts from biologists, chemists, physicists, and materials scientists.

References

- Bai W et al (2022) Boosting the optical absorption of melanin-like polymers. *Macromolecules* 55: 3493–3501
- Battistella C et al (2020) Mimicking natural human hair pigmentation with synthetic melanin. *ACS Cent Sci* 6:1179–1188
- Bisaglia M, Mammi S, Bubacco L (2007) Kinetic and structural analysis of the early oxidation products of dopamine. *J Biol Chem* 282:15597–15605
- Bothma JP, De Boor J, Divakar U, Schwenn PE, Meredith P (2008) Device-quality electrically conducting melanin thin films. *Adv Mater* 20:3539–3542
- Brenner M, Hearing VJ (2008) The protective role of melanin against UV damage in human skin†. *Photochem Photobiol* 84:539–549
- Büngeler A, Hämisch B, Strube O (2017) The supramolecular buildup of eumelanin: structures, mechanisms, controllability. *Int J Mol Sci* 18:1901
- Cai Z et al (2014) 2D photonic crystal protein hydrogel coulometer for sensing serum albumin ligand binding. *Anal Chem* 86:4840–4847
- Cao W et al (2020) Selenomelanin: an abiotic selenium analogue of pheomelanin. *J Am Chem Soc* 142:12802–12810
- Cao W et al (2021) Unraveling the structure and function of melanin through synthesis. *J Am Chem Soc* 143:2622–2637
- Capozzi V et al (2005) Raman and optical spectroscopy of eumelanin films. *J Mol Struct* 744:717–721
- Chen C-T et al (2013) Self-assembly of tetramers of 5,6-dihydroxyindole explains the primary physical properties of eumelanin: experiment, simulation, and design. *ACS Nano* 7:1524–1532
- Chen C-T et al (2014) Excitonic effects from geometric order and disorder explain broadband optical absorption in eumelanin. *Nat Commun* 5:3859
- Cho S, Kim S-H (2015) Hydroxide ion-mediated synthesis of monodisperse dopamine–melanin nanospheres. *J Colloid Interface Sci* 458:87–93
- Cho S, Shim TS, Kim JH, Kim D-H, Kim S-H (2017) Selective coloration of melanin nanospheres through resonant Mie scattering. *Adv Mater* 29:1700256
- Corani A et al (2014) Superior photoprotective motifs and mechanisms in eumelanins uncovered. *J Am Chem Soc* 136:11626–11635
- d’Ischia M et al (2013) Melanins and melanogenesis: methods, standards, protocols. *Pigment Cell Melanoma Res* 26:616–633
- Della Vecchia NF et al (2013) Building-block diversity in polydopamine underpins a multifunctional eumelanin-type platform Tunable through a quinone control point. *Adv Funct Mater* 23:1331–1340
- Derby C (2014) Cephalopod ink: production, chemistry, functions and applications. *Mar Drugs* 12: 2700–2730
- Ding P et al (2017) In situ live-cell nucleus fluorescence labeling with bioinspired fluorescent probes. *Anal Chem* 89:7861–7868
- Dong Y et al (2019) Melanin-mimetic multicolor and low-toxicity hair dye. *RSC Adv* 9:33617–33624
- Eliason CM, Shawkey MD (2010) Rapid, reversible response of iridescent feather color to ambient humidity. *Opt Express* 18:21284–21292
- Eliason CM, Shawkey MD (2012) A photonic heterostructure produces diverse iridescent colours in duck wing patches. *J R Soc Interface* 9:2279–2289

- Evayanti LG, Artaria MD (2019) Understanding the characteristics of physical color in human—an article review. In: Proceedings of the international conference of social science. <https://doi.org/10.4108/eai.21-9-2018.2281158>
- Frases S, Salazar A, Dadachova E, Casadevall A (2007) *Cryptococcus neoformans* can utilize the bacterial melanin precursor Homogentisic acid for fungal melanogenesis. *Appl Environ Microbiol* 73:615–621
- Galván I et al (2013) Raman spectroscopy as a non-invasive technique for the quantification of melanins in feathers and hairs. *Pigment Cell Melanoma Res* 26:917–923
- Herrling T, Jung K, Fuchs J (2008) The role of melanin as protector against free radicals in skin and its role as free radical indicator in hair. *Spectrochim Acta A Mol Biomol Spectrosc* 69:1429–1435
- Hong S, Wang Y, Park SY, Lee H (2018) Progressive fuzzy cation- π assembly of biological catecholamines. *Sci Adv* 4(9):eaat7457
- Hu D-N, Simon JD, Sarna T (2008) Role of ocular melanin in ophthalmic physiology and pathology. *Photochem Photobiol* 84:639–644
- Huang Z et al (2004) Raman spectroscopy of in vivo cutaneous melanin. *J Biomed Opt* 9:1198–1205
- Im KM, Kim T-W, Jeon J-R (2017) Metal-chelation-assisted deposition of polydopamine on human hair: a ready-to-use eumelanin-based hair dyeing methodology. *ACS Biomater Sci Eng* 3:628–636
- Ito T, Ito S, Wakamatsu K (2019) Effects of aging on hair color, melanosome morphology, and melanin composition in Japanese females. *Int J Mol Sci* 20:3739
- Jackson JC, Higgins LA, Lin X (2009) Conidiation color mutants of *aspergillus fumigatus* are highly pathogenic to the heterologous insect host *Galleria mellonella*. *PLoS One* 4:e4224
- Ju K-Y, Fischer MC, Warren WS (2018) Understanding the role of aggregation in the broad absorption bands of eumelanin. *ACS Nano* 12:12050–12061
- Ju K-Y, Lee S, Pyo J, Choo J, Lee J-K (2015) Bio-inspired development of a dual-mode nanoprobe for MRI and Raman imaging. *Small* 11:84–89
- Kawamura A et al (2016) Full-color biomimetic photonic materials with iridescent and non-iridescent structural colors. *Sci Rep* 6:33984
- Kaxiras E, Tsolakidis A, Zonios G, Meng S (2006) Structural model of eumelanin. *Phys Rev Lett* 97:218102
- Kohri M et al (2018) Polydopamine-based 3D colloidal photonic materials: structural color balls and fibers from melanin-like particles with polydopamine shell layers. *ACS Appl Mater Interfaces* 10:7640–7648
- Kohri M et al (2019) Ellipsoidal artificial melanin particles as building blocks for biomimetic structural coloration. *Langmuir* 35:5574–5580
- Lee GH et al (2019) Colloidal photonic inks for mechanochromic films and patterns with structural colors of high saturation. *Chem Mater* 31:8154–8162
- Li Q, Clarke JA, Gao K-Q, Peteya JA, Shawkey MD (2018) Elaborate plumage patterning in a cretaceous bird. *PeerJ* 6:e5831
- Li Y et al (2015) Mass spectrometric and spectrophotometric analyses reveal an alternative structure and a new formation mechanism for melanin. *Anal Chem* 87:7958–7963
- Li W et al (2019) Mechanism of UVA degradation of synthetic eumelanin. *Biomacromolecules* 20:4593–4601
- Li W et al (2020) Characterization of broadband complex refractive index of synthetic melanin coatings and their changes after ultraviolet irradiation. *Appl Phys Lett* 117:203701
- Lin J-H, Yu C-J, Yang Y-C, Tseng W-L (2015) Formation of fluorescent polydopamine dots from hydroxyl radical-induced degradation of polydopamine nanoparticles. *Phys Chem Chem Phys* 17:15124–15130
- Liu J, Lemonds TR, Popadić A (2014) The genetic control of aposematic black pigmentation in hemimetabolous insects: insights from *Oncopeltus fasciatus*: the genetic control of black pigmentation in *Oncopeltus*. *Evol Dev* 16:270–277

- Liu Y et al (2013) Dopamine-melanin colloidal nanospheres: an efficient near-infrared photothermal therapeutic agent for in vivo cancer therapy. *Adv Mater* 25:1353–1359
- Liu P et al (2020) A highly colorimetric photonic film composed of non-close-packed melanin-like colloidal arrays. *J Colloid Interface Sci* 580:573–582
- Ma S et al (2016) Selective and sensitive monitoring of cerebral antioxidants based on the dye-labeled DNA/polydopamine conjugates. *Anal Chem* 88:11647–11653
- Maia R, Caetano JVO, B  o SN, Macedo RH (2009) Iridescent structural colour production in male blue-black grassquit feather barbules: the role of keratin and melanin. *J R Soc Interface* 6:S203–S211
- Maia R, D’Alba L, Shawkey MD (2011) What makes a feather shine? A nanostructural basis for glossy black colours in feathers. *Proc R Soc B Biol Sci* 278:1973–1980
- M  thger LM, Denton EJ, Marshall NJ, Hanlon RT (2009) Mechanisms and behavioural functions of structural coloration in cephalopods. *J R Soc Interface* 6(Suppl 2):S149–S163
- Mattoon ER, Cordero RJB, Casadevall A (2021) Fungal melanins and applications in healthcare bioremediation and industry. *J Fungi* 7:488
- Napolitano A, Panzella L, Leone L, d’Ischia M (2013) Red hair benzothiazines and benzothiazoles: mutation-inspired chemistry in the quest for functionality. *Acc Chem Res* 46:519–528
- Nicol  i MPJ, Shawkey MD, Porchetta S, Claus R, D’Alba L (2020) Exposure to UV radiance predicts repeated evolution of concealed black skin in birds. *Nat Commun* 11:2414
- Panzella L et al (2013) Atypical structural and π -electron features of a melanin polymer that lead to superior free-radical-scavenging properties. *Angew Chem Int Ed* 52:12684–12687
- Patil A et al (2021) Structural color production in melanin-based disordered colloidal nanoparticle assemblies in spherical confinement. *Adv Opt Mater* 10:2102162. <https://doi.org/10.1002/adom.202102162>
- Peteya JA, Clarke JA, Li Q, Gao K-Q, Shawkey MD (2017) The plumage and colouration of an enantiornithine bird from the early cretaceous of China. *Palaeontology* 60:55–71
- Qiang W, Li W, Li X, Chen X, Xu D (2014) Bioinspired polydopamine nanospheres: a superquencher for fluorescence sensing of biomolecules. *Chem Sci* 5:3018–3024
- Qu X, Kirschenbaum LJ, Borish ET (2000) Hydroxyterephthalate as a fluorescent probe for hydroxyl radicals: application to hair melanin. *Photochem Photobiol* 71:307–313
- Rageh MM, EL-Gebaly RH, Abou-Shady H, Amin DG (2015) Melanin nanoparticles (MNPs) provide protection against whole-body γ -irradiation in mice via restoration of hematopoietic tissues. *Mol Cell Biochem* 399:59–69
- Reale S, Crucianelli M, Pezzella A, d’Ischia M, De Angelis F (2012) Exploring the frontiers of synthetic eumelanin polymers by high-resolution matrix-assisted laser/desorption ionization mass spectrometry: Eumelanins at their mass limits studied by MALDI mass spectrometry. *J Mass Spectrom* 47:49–53
- Riesz J, Gilmore J, Meredith P (2006) Quantitative scattering of melanin solutions. *Biophys J* 90:4137–4144
- Saranathan V et al (2012) Structure and optical function of amorphous photonic nanostructures from avian feather barbs: a comparative small angle X-ray scattering (SAXS) analysis of 230 bird species. *J R Soc Interface* 9:2563–2580
- Schmaler-Ripcke J et al (2009) Production of pyomelanin, a second type of melanin, via the tyrosine degradation pathway in *Aspergillus fumigatus*. *Appl Environ Microbiol* 75:493–503
- Shawkey MD, Hill GE (2006) Significance of a basal melanin layer to production of non-iridescent structural plumage color: evidence from an amelanotic Steller’s jay (*Cyanocitta stelleri*). *J Exp Biol* 209:1245–1250
- Shih BB et al (2020) Influence of skin melanisation and ultraviolet radiation on biomarkers of systemic oxidative stress. *Free Radic Biol Med* 160:40–46
- Song W, Zhang L, Ness S, Yi J (2017) Wavelength-dependent optical properties of melanosomes in retinal pigmented epithelium and their changes with melanin bleaching: a numerical study. *Biomed Opt Express* 8:3966

- Stark KB et al (2005) Effect of stacking and redox state on optical absorption spectra of melanins—comparison of theoretical and experimental results. *J Phys Chem B* 109:1970–1977
- Stavenga DG, Leertouwer HL, Hariyama T, De Raedt HA, Wilts BD (2012) Sexual dichromatism of the damselfly *Calopteryx japonica* caused by a melanin-chitin multilayer in the male wing veins. *PLoS One* 7:e49743
- Stavenga DG, Leertouwer HL, Marshall NJ, Osorio D (2011) Dramatic colour changes in a bird of paradise caused by uniquely structured breast feather barbules. *Proc R Soc B Biol Sci* 278: 2098–2104
- Stavenga DG, Leertouwer HL, Osorio DC, Wilts BD (2015) High refractive index of melanin in shiny occipital feathers of a bird of paradise. *Light Sci Appl* 4:e243–e243
- Surmacki A, Minias P, Kudelska K (2021) Occurrence and function of melanin-based grey coloration in Western Palaearctic songbirds (Aves: Passeriformes). *Ibis* 163:390–406
- Swift JA (2009) Speculations on the molecular structure of eumelanin. *Int J Cosmet Sci* 31:143–150
- Takeoka Y (2012) Angle-independent structural coloured amorphous arrays. *J Mater Chem* 22: 23299–23309
- Tran ML, Powell BJ, Meredith P (2006) Chemical and structural disorder in eumelanins: a possible explanation for broadband absorbance. *Biophys J* 90:743–752
- Wakamatsu K, Fujikawa K, Zucca FA, Zecca L, Ito S (2003) The structure of neuromelanin as studied by chemical degradative methods: chemical structure of neuromelanin. *J Neurochem* 86: 1015–1023
- Wakamatsu K, Zippin JH, Ito S (2021) Chemical and biochemical control of skin pigmentation with special emphasis on mixed melanogenesis. *Pigment Cell Melanoma Res* 34:730–747
- Wang Y et al (2016) Simultaneous enhancements of UV-shielding properties and photostability of poly(vinyl alcohol) via incorporation of sepia eumelanin. *ACS Sustain Chem Eng* 4:2252–2258
- Wang Y et al (2017) A Novel UV-Shielding and transparent polymer film: when bioinspired dopamine–melanin hollow nanoparticles join polymers. *ACS Appl Mater Interfaces* 9:36281–36289
- Wiernasz DC (1995) Male choice on the basis of female melanin pattern in *Pieris* butterflies. *Anim Behav* 49:45–51
- Xiao M, Dhinojwala A, Shawkey M (2014) Nanostructural basis of rainbow-like iridescence in common bronzing Phaps chalcoptera feathers. *Opt Express* 22:14625
- Xiao M, Shawkey MD, Dhinojwala A (2020) Bioinspired melanin-based optically active materials. *Adv Opt Mater* 8:2000932
- Xiao M et al (2015) Bio-inspired structural colors produced via self-assembly of synthetic melanin nanoparticles. *ACS Nano* 9:5454–5460
- Xiao M et al (2016) Stimuli-responsive structurally colored films from bioinspired synthetic melanin nanoparticles. *Chem Mater* 28:5516–5521
- Xiao M et al (2017) Bioinspired bright noniridescent photonic melanin supraballs. *Sci Adv* 3: e1701151
- Xiao M et al (2018) Elucidation of the hierarchical structure of natural eumelanins. *J R Soc Interface* 15:20180045
- Xiao M et al (2019) Experimental and theoretical evidence for molecular forces driving surface segregation in photonic colloidal assemblies. *Sci Adv* 5:eaax1254
- Xue Q, Cao X, Zhang C, Xian Y (2018) Polydopamine nanodots are viable probes for fluorometric determination of the activity of alkaline phosphatase via the in situ regulation of a redox reaction triggered by the enzyme. *Microchim Acta* 185:1–9
- Yang L et al (2016) Fluorescent nanocomposite for visualizing cross-talk between microRNA-21 and hydrogen peroxide in ischemia-reperfusion injury in live cells and in vivo. *Anal Chem* 88: 11886–11891
- Yang P et al (2019) Tailoring synthetic melanin nanoparticles for enhanced photothermal therapy. *ACS Appl Mater Interfaces* 11:42671–42679

- Yin H et al (2018) Redox modulation of polydopamine surface chemistry: a facile strategy to enhance the intrinsic fluorescence of polydopamine nanoparticles for sensitive and selective detection of Fe^{3+} . *Nanoscale* 10:18064–18073
- Yoshioka S, Kinoshita S (2011) Direct determination of the refractive index of natural multilayer systems. *Phys Rev E* 83:051917
- Zareba M et al (2006) Effects of photodegradation on the physical and antioxidant properties of melanosomes isolated from retinal pigment epithelium. *Photochem Photobiol* 82:1024
- Zhang X et al (2012) Biocompatible polydopamine fluorescent organic nanoparticles: facile preparation and cell imaging. *Nanoscale* 4:5581
- Zhang M et al (2019) Polydopamine-based tumor-targeted multifunctional reagents for computer tomography/fluorescence dual-mode bioimaging-guided photothermal therapy. *ACS Appl Bio Mater* 2:630–637
- Zhang S et al (2020) Mimicking neuromelanin nanoparticles as a selective Pb^{2+} probe. *Anal Chim Acta* 1105:208–213
- Zheng C et al (2022) Permanent low-toxicity hair dye based on Pregrafting melanin with cystine. *ACS Biomater Sci Eng* 8:2858–2863
- Zhou X et al (2019) Artificial allomelanin nanoparticles. *ACS Nano* 13:10980–10990
- Zi J et al (2003) Coloration strategies in peacock feathers. *Proc Natl Acad Sci* 100:12576–12578
- Zou Y et al (2020) Regulating the absorption spectrum of polydopamine. *Sci Adv* 6:eabb4696